


BBR VT CONA CMI

Internal Post-tensioning System with 01 to 61 Strands



European Technical Assessment
ETA – 06/0147

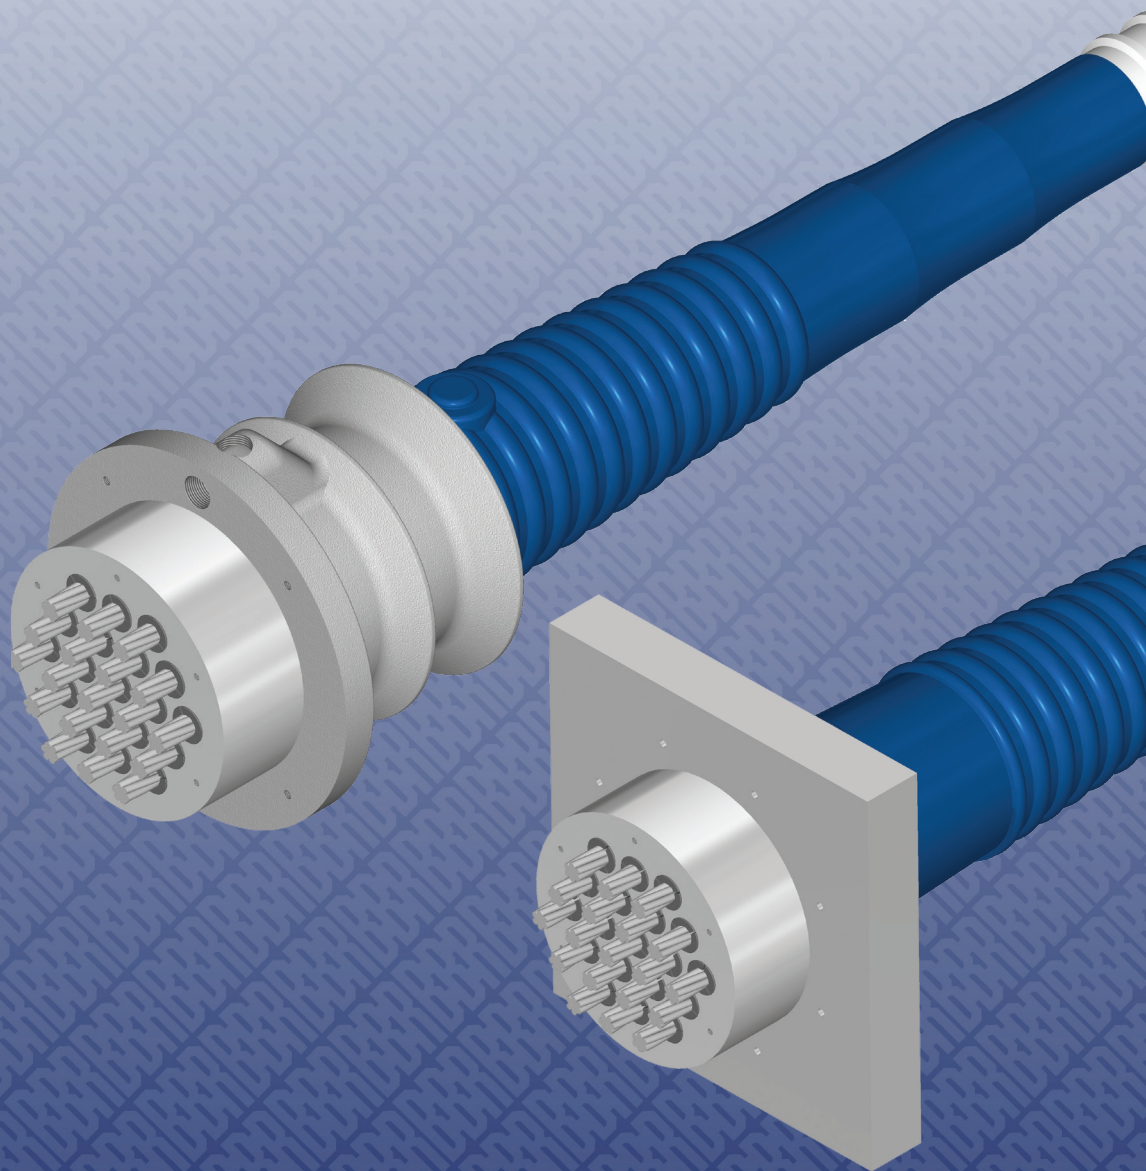

A Global Network of Experts
www.bbrnetwork.com



ETA-06/0147

BBR VT CONA CMI

Internal Post-tensioning System with 01 to 61 Strands

BBR VT International Ltd

Ringstrasse 2, 8603 Schwerzenbach (Switzerland)

www.bbrnetwork.com

0432-CPR-00299-1.1/5

13

Responsible BBR PT Specialist Company



The delivery note accompanying components of the BBR VT CONA CMI Post-tensioning System will contain the CE marking.



Assembly and installation of BBR VT CONA CMI tendons must only be carried out by qualified BBR PT Specialist Companies. Find the local BBR PT Specialist Company by visiting the BBR Network website www.bbrnetwork.com.



European Organisation for Technical Approvals
Europäische Organisation für Technische Zulassungen
Organisation Européenne pour l'Agrément technique

EAD 16004-00-0301

Post-tensioning Kits for Prestressing of Structures

CWA 14646

Requirements for the installation of post-tensioning kits for prestressing of structures and qualification of the specialist company and its personnel



BBR E-Trace is the trading and quality assurance platform of the BBR Network linking the Holder of Approval, BBR VT International Ltd, BBR PT Specialist Companies and the BBR Manufacturing Plant. Along with the established BBR Factory Production Control, BBR E-Trace provides effective supply chain management including installation, delivery notes and highest quality standards, as well as full traceability of components.



Austrian Institute of Construction Engineering
Schenkenstrasse 4 | T +43 1 533 65 50
1010 Vienna | Austria | F +43 1 533 64 23
www.oib.or.at | mail@oib.or.at



European Technical Assessment

ETA-06/0147
of 26.06.2025

General part

**Technical Assessment Body issuing the
European Technical Assessment**

Österreichisches Institut für Bautechnik (OIB)
Austrian Institute of Construction Engineering

Trade name of the construction product

BBR VT CONA CMI – Internal Post-tensioning
System with 01 to 61 Strands

**Product family to which the construction
product belongs**

Post-tensioning kit for prestressing of structures
with internal bonded or unbonded strands

Manufacturer

BBR VT International Ltd
Ringstrasse 2
8603 Schwerzenbach (ZH)
SWITZERLAND

Manufacturing plant

BBR VT International Ltd
Ringstrasse 2
8603 Schwerzenbach (ZH)
SWITZERLAND

**This European Technical Assessment
contains**

133 pages including Annexes 1 to 91, which form
an integral part of this assessment.

**This European Technical Assessment
is issued in accordance with Regulation
(EU) No 305/2011, on the basis of**

European Assessment Document
(EAD) 160004-00-0301 – Post-Tensioning Kits
for Prestressing of Structures.

**This European Technical Assessment
replaces**

European Technical Assessment ETA-06/0147 of
11.03.2024

Table of contents

EUROPEAN TECHNICAL ASSESSMENT	ETA-06/0147 OF 26.06.2025	1
GENERAL PART		1
TABLE OF CONTENTS		2
SPECIFIC PARTS		10
1	TECHNICAL DESCRIPTION OF THE PRODUCT	10
1.1	GENERAL	10
	PT SYSTEM	12
1.2	DESIGNATION AND RANGE OF ANCHORAGES AND COUPLERS	12
1.2.1	Designation	12
1.2.2	Anchorage	12
1.2.3	Fixed and stressing coupler	13
1.2.3.1	General	13
1.2.3.2	Single plane coupler	13
1.2.3.3	Sleeve coupler	13
1.2.4	Movable coupler	14
1.2.5	Restressable tendon	14
1.2.6	Replaceable tendon	14
1.2.7	Encapsulated tendon	15
1.2.8	Electrically isolated tendon	15
1.2.9	Electrically isolated and replaceable tendon	16
1.2.10	Tendon with monostrands	16
1.2.11	Layout of the anchorage recess	16
1.3	DESIGNATION AND RANGE OF THE TENDONS	17
1.3.1	Designation	17
1.3.2	Range	17
1.3.2.1	General	17
1.3.2.2	CONA CMI n06-140	18
1.3.2.3	CONA CMI n06-150	18
1.4	SHEATHS	18
1.4.1	General	18
1.4.2	Degree of filling, f	18
1.4.3	Circular steel strip sheaths	18
1.4.4	Flat corrugated steel duct	19
1.4.5	Pre-bent smooth circular steel duct	19
1.4.6	Corrugated plastic duct	19
1.4.7	Plain plastic duct	20
1.5	FRICTION LOSSES	20
1.6	SUPPORT OF TENDONS	21

- 1.7 SLIP AT ANCHORAGES AND COUPLERS21
- 1.8 CENTRE SPACING AND EDGE DISTANCE FOR ANCHORAGES21
- 1.9 MINIMUM RADII OF CURVATURE22
- 1.10 CONCRETE STRENGTH AT TIME OF STRESSING24
- COMPONENTS.....24
- 1.11 PRESTRESSING STEEL STRANDS24
- 1.12 ANCHORAGE AND COUPLER25
 - 1.12.1 General25
 - 1.12.2 Anchor head.....25
 - 1.12.3 Bearing trumplate.....25
 - 1.12.4 Square plate.....25
 - 1.12.5 Trumpets.....25
 - 1.12.6 Coupler anchor head K and H.....26
 - 1.12.7 Ring wedges26
 - 1.12.8 Additional reinforcement27
 - 1.12.9 Caps27
 - 1.12.9.1 General27
 - 1.12.9.2 Grouting cap.....27
 - 1.12.9.3 Protection caps.....27
 - 1.12.10 Accessories for inlets and outlets28
- 1.13 SHEATHS.....28
 - 1.13.1 Steel strip sheaths.....28
 - 1.13.2 Steel duct.....28
 - 1.13.3 Plastic ducts.....28
- 1.14 MATERIAL SPECIFICATIONS28
- 1.15 PERMANENT CORROSION PROTECTION28
 - 1.15.1 General.....28
 - 1.15.2 Grout.....28
 - 1.15.3 Unbonded tendon29
 - 1.15.4 Monostrand.....29
- 2 SPECIFICATION OF THE INTENDED USES IN ACCORDANCE WITH THE APPLICABLE EUROPEAN ASSESSMENT DOCUMENT (HEREINAFTER EAD)30
 - 2.1 INTENDED USES30
 - 2.2 ASSUMPTIONS30
 - 2.2.1 General.....30
 - 2.2.2 Packaging, transport, and storage.....30
 - 2.2.3 Design.....31
 - 2.2.3.1 General31
 - 2.2.3.2 Fixed and stressing coupler.....31
 - 2.2.3.3 Anchorage Recess31

2.2.3.4	Maximum prestressing force.....	31
2.2.3.5	Reinforcement in the anchorage zone	31
2.2.3.6	Tendons in masonry structures – Load transfer to the structure	32
2.2.4	Installation.....	32
2.2.4.1	General	32
2.2.4.2	Stressing operation.....	33
2.2.4.3	Restressing	33
2.2.4.4	Exchange of tendons.....	34
2.2.4.5	Filling operations	34
2.2.4.5.1	Grouting.....	34
2.2.4.5.2	Filling with grease, wax, and an equivalent soft material	35
2.2.4.5.3	Circulating dry air	35
2.2.4.5.4	Filling records	35
2.2.4.6	Welding	35
2.3	ASSUMED WORKING LIFE	35
3	PERFORMANCE OF THE PRODUCT AND REFERENCES TO THE METHODS USED FOR ITS ASSESSMENT	36
3.1	ESSENTIAL CHARACTERISTICS	36
3.2	PRODUCT PERFORMANCE	37
3.2.1	Mechanical resistance and stability	37
3.2.1.1	Resistance to static load.....	37
3.2.1.2	Resistance to fatigue	37
3.2.1.3	Load transfer to the structure.....	37
3.2.1.4	Friction coefficient.....	37
3.2.1.5	Deviation / deflection (limits) for internal bonded and internal unbonded tendon.....	37
3.2.1.6	Assessment of assembly	38
3.2.1.7	Resistance to static load under cryogenic conditions for applications with anchorage / coupling outside the possible cryogenic zone	38
3.2.1.8	Resistance to static load under cryogenic conditions for applications with anchorage / coupling inside the possible cryogenic zone	38
3.2.1.9	Material properties, component performance, system performance of plastic duct (PL1).....	38
3.2.1.10	Material properties, component performance, system performance of plastic duct to provide an encapsulated tendon (PL2)	38
3.2.1.11	Material properties, component performance, system performance of plastic duct to provide an electrically isolated tendon (PL3).....	38
3.2.1.12	Corrosion protection	38
3.2.2	Safety in case of fire.....	38
3.2.2.1	Reaction to fire	38
3.2.3	Hygiene, health, and the environment.....	38
3.2.3.1	Content, emission and/or release of dangerous substances	38
3.3	ASSESSMENT METHODS	39
3.4	IDENTIFICATION.....	39
4	ASSESSMENT AND VERIFICATION OF CONSTANCY OF PERFORMANCE (HEREINAFTER AVCP) SYSTEM APPLIED, WITH REFERENCE TO ITS LEGAL BASE.....	40
4.1	SYSTEM OF ASSESSMENT AND VERIFICATION OF CONSTANCY OF PERFORMANCE.....	40

4.2	AVCP FOR CONSTRUCTION PRODUCTS FOR WHICH A EUROPEAN TECHNICAL ASSESSMENT HAS BEEN ISSUED	40
5	TECHNICAL DETAILS NECESSARY FOR THE IMPLEMENTATION OF THE AVCP SYSTEM, AS PROVIDED FOR IN THE APPLICABLE EAD	40
5.1	TASKS FOR THE MANUFACTURER	40
5.1.1	Factory production control	40
5.1.2	Declaration of performance	41
5.2	TASKS FOR THE NOTIFIED PRODUCT CERTIFICATION BODY	41
5.2.1	Initial inspection of the manufacturing plant and of factory production control	41
5.2.2	Continuing surveillance, assessment, and evaluation of factory production control	42
5.2.3	Audit-testing of samples taken by the notified product certification body at the manufacturing plant or at the manufacturer's storage facilities	42
	ANNEXES	43
ANNEX 1	OVERVIEW ON ANCHORAGES OF CONA CMI BT	43
ANNEX 2	OVERVIEW ON COUPLERS OF CONA CMI BT	44
ANNEX 3	OVERVIEW ON ANCHORAGES AND COUPLERS OF CONA CMI BT	45
ANNEX 4	OVERVIEW ON ANCHORAGES AND COUPLERS OF CONA CMI SP	46
ANNEX 5	COMPONENTS – ANCHORAGE	47
ANNEX 6	COMPONENTS – ANCHORAGE	48
ANNEX 7	COMPONENTS – COUPLER	49
ANNEX 8	COMPONENTS – ANCHORAGE AND COUPLER	50
ANNEX 9	COMPONENTS – ANCHORAGE AND COUPLER	51
ANNEX 10	COMPONENTS – NUCLEAR	52
ANNEX 11	COMPONENTS – NUCLEAR	53
ANNEX 12	COMPONENTS – ACCESSORY	54
ANNEX 13	COMPONENTS – ACCESSORY	55
ANNEX 14	COMPONENTS – ACCESSORY	56
ANNEX 15	COMPONENTS – ACCESSORY	57
ANNEX 16	COMPONENTS – TRUMPET	58
ANNEX 17	COMPONENTS – TRUMPET	59
ANNEX 18	COMPONENTS – TRUMPET	60
ANNEX 19	PLASTIC DUCT – CIRCULAR DUCT 0206–3706	61
ANNEX 20	PLASTIC DUCT – FLAT DUCT 0206–0506	62
ANNEX 21	SEGMENTAL COUPLER	63
ANNEX 22	MATERIAL SPECIFICATIONS	64
ANNEX 23	BBR VT PLASTIC DUCT – SPECIFICATION OF POLYPROPYLENE	65
ANNEX 24	BBR VT PLASTIC DUCT – PERFORMANCE OF PLASTIC DUCT	66
ANNEX 25	BBR VT PLASTIC DUCT – PERFORMANCE OF PLASTIC DUCT	67
ANNEX 26	BBR VT PLASTIC DUCT – STIFFNESS OF PLASTIC DUCT	68

ANNEX 27	STRAND SPECIFICATIONS	69
ANNEX 28	TENDON RANGES	70
ANNEX 29	TENDON RANGES	71
ANNEX 30	MAXIMUM PRESTRESSING AND OVERSTRESSING FORCES	72
ANNEX 31	MINIMUM RADIUS OF CIRCULAR DUCT FOR $P_{R, MAX} = 130$ kN/M	73
ANNEX 32	MINIMUM RADIUS OF CIRCULAR DUCT FOR $P_{R, MAX} = 140$ kN/M	74
ANNEX 33	MINIMUM RADIUS OF CIRCULAR DUCT FOR $P_{R, MAX} = 150$ kN/M	75
ANNEX 34	MINIMUM RADIUS OF CIRCULAR DUCT FOR $P_{R, MAX} = 200$ kN/M	76
ANNEX 35	MINIMUM RADIUS OF CIRCULAR DUCT FOR $P_{R, MAX} = 230$ kN/M	77
ANNEX 36	MINIMUM RADIUS OF FLAT DUCT	78
ANNEX 37	MINIMUM CENTRE SPACING OF CONA CMI BT – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT	79
ANNEX 38	MINIMUM CENTRE SPACING OF CONA CMI BT – ONLY HELIX AS ADDITIONAL REINFORCEMENT	80
ANNEX 39	MINIMUM CENTRE SPACING OF CONA CMI BT – ONLY STIRRUPS AS ADDITIONAL REINFORCEMENT	81
ANNEX 40	MINIMUM CENTRE SPACING OF CONA CMI SP	82
ANNEX 41	MINIMUM EDGE DISTANCE OF CONA CMI BT – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT	83
ANNEX 42	MINIMUM EDGE DISTANCE OF CONA CMI BT – ONLY HELIX AS ADDITIONAL REINFORCEMENT	84
ANNEX 43	MINIMUM EDGE DISTANCE OF CONA CMI BT – ONLY STIRRUPS AS ADDITIONAL REINFORCEMENT	85
ANNEX 44	MINIMUM EDGE DISTANCE OF CONA CMI SP	86
ANNEX 45	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	87
ANNEX 46	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	88
ANNEX 47	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	89
ANNEX 48	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	90
ANNEX 49	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	91
ANNEX 50	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	92
ANNEX 51	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	93
ANNEX 52	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	94
ANNEX 53	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	95

ANNEX 54	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	96
ANNEX 55	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	97
ANNEX 56	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	98
ANNEX 57	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	99
ANNEX 58	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	100
ANNEX 59	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	101
ANNEX 60	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	102
ANNEX 61	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	103
ANNEX 62	ANCHORAGE ZONE OF CONA CMI SP – MINIMUM CONCRETE STRENGTH – HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE – SQUARE PLATE DIMENSIONS	104
ANNEX 63	MODIFICATION OF CENTRE SPACING AND EDGE DISTANCE OF CONA CMI WITH HELIX AND STIRRUPS AS ADDITIONAL REINFORCEMENT	105
ANNEX 64	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	106
ANNEX 65	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	107
ANNEX 66	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	108
ANNEX 67	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	109
ANNEX 68	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	110
ANNEX 69	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	111
ANNEX 70	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	112
ANNEX 71	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	113
ANNEX 72	ANCHORAGE ZONE OF CONA CMI BT – MINIMUM CONCRETE STRENGTH – HELIX OR ADDITIONAL STIRRUP REINFORCEMENT – CENTRE SPACING AND EDGE DISTANCE	114

electronic copy electronic copy electronic copy electronic copy electronic copy

electronic copy
electronic copy
electronic copy
electronic copy
electronic copy
electronic copy
electronic copy

Translations of the European Technical Assessment in other languages shall fully correspond to the original issued document and should be identified as such.

Communication of the European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may be made with the written consent of Österreichisches Institut für Bautechnik. Any partial reproduction has to be identified as such.

Specific parts

1 Technical description of the product

1.1 General

The European Technical Assessment¹ – ETA – applies to a kit, the PT system

BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands,

comprising the following components, see Annex 1, Annex 2, Annex 3, and Annex 4.

- Tendon

Bonded tendon or unbonded tendon with 01 to 61 tensile elements
- Tensile element

7-wire prestressing steel strand with nominal diameters and nominal tensile strength as given in Table 1.

7-wire prestressing steel strands with nominal diameters and maximum characteristic tensile strength as given in Table 1, factory-provided with a corrosion protection system, comprising corrosion protection filling material and HDPE-sheathing – Monostrand. Tendon with monostrands is installed in one common duct and grouted prior to stressing.

Table 1: Tensile elements

Nominal diameter	Nominal cross-sectional area	Maximum characteristic tensile strength
mm	mm ²	MPa
15.3	140	1 860
15.7	150	

NOTE 1 MPa = 1 N/mm²

- Anchorage and coupler

Anchorage of the prestressing steel strands with ring wedges

 - End anchorage

Fixed (passive) anchor or stressing (active) anchor as end anchorage (FA, SA) for tendons with 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

Fixed (passive) anchor or stressing (active) anchor as end anchorage for replaceable tendons (FAR, SAR) with 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

¹ ETA-06/0147 was firstly issued in 2006 as European technical approval with validity from 25.08.2006, extended in 2011 with validity from 05.07.2011, amended in 2013 with validity from 04.03.2013, converted in 2016 to European Technical Assessment ETA-06/0147 of 31.05.2016, amended in 2017 to European Technical Assessment ETA-06/0147 of 30.10.2017, in 2024 to European Technical Assessment ETA-06/0147 of 11.03.2024, and in 2025 to European Technical Assessment ETA-06/0147 of 26.06.2025.

Fixed (passive) anchor or stressing (active) anchor as end anchorage (FA, SA) for encapsulated tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, and 37 prestressing steel strands

Fixed (passive) anchor or stressing (active) anchor as end anchorage (FAE, SAE) for electrically isolated tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, and 37 prestressing steel strands

Fixed (passive) anchor or stressing (active) anchor as end anchorage (FAER, SAER) for electrically isolated and replaceable tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, and 37 prestressing steel strands

Fixed (passive) anchor or stressing (active) anchor as end anchorage (FAN, SAN) for anchorage nuclear (N) with 55 prestressing steel strands

– Fixed or stressing coupler

Single plane coupler (FK, SK) for tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, and 31 prestressing steel strands

Single plane coupler (FK, SK) for encapsulated tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, and 31 prestressing steel strands

Single plane coupler (FKE, SKE) for electrically isolated tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, and 31 prestressing steel strands

Sleeve coupler (FH, SH) for tendons with 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

Sleeve coupler (FH, SH) for encapsulated tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, and 37 prestressing steel strands

Sleeve coupler (FHE, SHE) for electrically isolated tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, and 37 prestressing steel strands

– Movable coupler

Single plane coupler (BK) for tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, and 31 prestressing steel strands

Sleeve coupler (BH) for tendons with 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

- Bearing trumplate (BT) for tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

- Bearing trumplate (N) for tendon with 55 prestressing steel strands

- Square plate (SP) for tendons with 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

- Helix and additional stirrup reinforcement in the region of the anchorage for tendons with 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands

- Only helix as additional reinforcement in the region of the anchorage for tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, and 37 prestressing steel strands

- Only stirrups as additional reinforcement in the region of the anchorage for tendons with 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, and 55 prestressing steel strands

- Steel sheaths, steel ducts, or plastic ducts

- Corrosion protection for tensile elements, couplers, and anchorages

electronic copy electronic copy electronic copy

electronic copy

 $\frac{e}{e}$

33

ni

tro

elect

Copy

ini

ini

10

3

 \angle

For

nic c

10

py

onic co

| str | |
$$\frac{e}{e}$$

- nic copy

- Bare strands, grouted in inner trumpet A/E and installed inside assembly of bearing trumplate A and trumpet A
- Bare strands, grouted or with grease, wax, or an equivalent soft material placed in square plate and trumpet A SP
- Monostrands, placed and grouted in bearing trumplate A/N and trumpet A/N
- Monostrands, placed and grouted in bearing trumplate E and trumpet E
- Monostrands, placed and grouted in inner trumpet A/E inside bearing trumplate A and trumpet A
- Monostrands, placed and grouted in square plate and trumpet A SP

Bare strands, grouted in bearing trumplate A and trumpet A, bearing trumplate E and trumpet E, bearing trumplate N and trumpet N, or square plate and trumpet A SP are a bonded tendon. Bare strands with grease, wax, or an equivalent soft material placed in bearing trumplate A and trumpet A, bearing trumplate E and trumpet E, bearing trumplate N and trumpet N, or square plate and trumpet A SP are an unbonded tendon. Monostrands grouted in bearing trumplate A/N and trumpet A/N, bearing trumplate E and trumpet E, or square plate and trumpet A SP are an unbonded tendon.

1.2.3 Fixed and stressing coupler

1.2.3.1 General

The prestressing force at the second construction stage may not be greater than that at the first construction stage, neither during construction, nor in the final state, nor due to any load combination. However, if free movement of the coupler is ensured by a housing, the prestressing force at the second construction stage can be greater than at the first construction stage, provided that grouting of first and second construction stages is performed after stressing of the second construction stage. Length of housing is for the expected elongation displacement of the coupler, see Clause 2.2.4.1.

Coupler anchor head K and coupler anchor head H are supported by bearing trumplate A, bearing trumplate E, or square plate.

1.2.3.2 Single plane coupler

The coupling, FK, SK, is achieved by means of a coupler anchor head K, see Annex 2, Annex 3, Annex 4, and Annex 7. The prestressing steel strands of the first construction stage are anchored by means of wedges in machined cones, drilled in parallel. The arrangement of the cones of the first construction stage is identical to that of the anchor heads A of the stressing and fixed anchorages. The prestressing steel strands of the second construction stage are anchored in a circle around the cones of the first construction stage by means of wedges in machined cones, drilled at an inclination of 7 °. The wedges for the second construction stage are secured by holding springs and a cover plate K, see Annex 12.

1.2.3.3 Sleeve coupler

The coupler anchor head H, see Annex 2, Annex 3, Annex 4, Annex 5, and Annex 7 is of the same basic geometry as the anchor head A of the fixed and stressing anchors. Compared to the anchor head A of the fixed and stressing anchors, the coupler anchor head H is deeper and provide an external thread for the coupler sleeve H, see Annex 9. The wedges for the second construction stage are secured by means of a wedge retaining plate, see Annex 13.

The connection between the coupler anchor heads H of the first and second construction stages is achieved by means of coupler sleeve H, coupler FH, SH.

1.2.4 Movable coupler

Anchorage of prestressing steel strands is achieved by wedges and coupler anchor heads. The movable coupler, see Annex 2, is either a single plane coupler, BK, or a sleeve coupler, BH, in a coupler sheathing made of steel or plastic. Length and position of coupler sheathing are for the expected elongation displacement, see Clause 2.2.4.1.

The coupler anchor heads and the coupler sleeves of the movable couplers are identical to the coupler anchor heads and the coupler sleeves of the fixed and stressing couplers, see Clause 1.2.3.2 and Clause 1.2.3.3. The wedges for the first construction stage are secured by means of a wedge retaining plate and the wedges of the second construction stage are secured by wedge retaining plate or holding springs and cover plate, see Annex 5, Annex 12, and Annex 13.

A 100 mm long and at least 3.5 mm thick PE-HD insert is installed at the deviating point at the end of the trumpet. The insert is not required for plastic trumpets where the ducts are slipped over the plastic trumpets.

1.2.5 Restressable tendon

Tendons remaining restressable throughout the working life of the structure are unbonded tendons. This is applicable to

- Bare strands or monostrands with grease, wax, or an equivalent soft material placed in bearing trumplate A and trumpet A or bearing trumplate N and trumpet N
- Bare strands or monostrands with grease, wax, or an equivalent soft material placed in square plate and trumpet A SP
- Monostrands, placed and grouted in bearing trumplate A and trumpet A or bearing trumplate N and trumpet N
- Monostrands, placed and grouted in square plate and trumpet A SP
- Monostrands, grouted in inner trumpet A/E inside bearing trumplate A and trumpet A

Bare strands, grouted in bearing trumplate A and trumpet A, bearing trumplate N and trumpet N, or square plate and trumpet A SP are not restressable.

Significant to a restressable tendon is the excess length of the prestressing steel strands, see Annex 3 and Annex 4. The extent of the excess length depends on the jack used for restressing and where applicable, the elongation for a full release of the prestressing force of the tendon. The protrusions of the prestressing steel strands require a permanent corrosive protection and an adapted protection cap.

1.2.6 Replaceable tendon

Replaceable tendons are unbonded tendons. Replacing tendons in general is available for

- Bare strands with grease, wax, or an equivalent soft material in bearing trumplate A and trumpet A or bearing trumplate N and trumpet N
- Bare strands with grease, wax, or an equivalent soft material in square plate and trumpet A SP
- Bare strands, grouted in inner trumpet A/E and installed inside assembly of bearing trumplate A and trumpet A, can only be completely removed and replaced with a new tendon, see Annex 3, anchorages FAR and SAR for replaceable tendons. Inner trumpet A/E, see Annex 17, inside bearing trumplate A and trumpet A, extends up to anchor head A or steel ring E (optional) if applicable. Adjacent to trumpet A an outer duct continues and adjacent to inner trumpet A/E an inner duct continues, which provide together with trumpet A and inner trumpet A/E a separating layer between the structure and the tendon. After full release of the

prestressing force, the complete tendon with inner trumpet A/E can be pulled out from the structure and replaced by a new tendon.

- Monostrands, grouted in bearing trumplate A and trumpet A or bearing trumplate N and trumpet N, see Clause 1.2.10, can be replaced strand by strand, see Annex 79.
- Monostrands, grouted in square plate and trumpet A SP, see Clause 1.2.10, can be replaced strand by strand, see Annex 81.
- Monostrands, grouted in inner trumpet A/E installed inside assembly of bearing trumplate A and trumpet A, can be replaced either strand by strand or completely removed and replaced with a new tendon, see Annex 3, anchorages FAR and SAR for replaceable tendons. Outer duct adjoined to trumpet A and inner duct adjoined to inner trumpet A/E provide a separating layer between the structure and the tendon. After full release of the prestressing force, the complete tendon with inner trumpet A/E can be pulled out from the structure and replaced by a new tendon.

1.2.7 Encapsulated tendon

Encapsulated tendons comprise the following components.

- Anchorages according to Clause 1.2.2
- Bearing trumplate A, see Annex 8
- Trumpet A and BBR VT Plastic Duct, see Annex 16, Annex 18, Annex 19, and Annex 20, and
- Protection cap A, see Annex 14. For bearing trumplate A 3706 protection cap E 3106 is applied.

Trumpet A is threaded to bearing trumplate A which supports the anchor head A. Protection cap A and protection cap E 3106 encase the anchorage. Trumpet A and BBR VT Plastic Duct are jointed with heat shrinking sleeve. The encapsulation performance of the tendon assembly, i.e., PL2², has been verified according to *fib* bulletin 75.

For couplers FK, SK, FH, and SH a plastic or steel housing that encloses the transition length of the tendon is bolted to a steel cushion plate at the second construction stage. The steel cushion plate is bolted to bearing trumplate A of the first construction stage. The housing is connected to the plastic duct with a heat shrink sleeve at the second construction stage.

Thereby, the complete tendon, including prestressing steel strands, couplers, and anchorages, is fully encapsulated.

1.2.8 Electrically isolated tendon

Electrically isolated tendons (EIT), see Annex 1 and Annex 3, comprise the following components.

- Anchorages according to Clause 1.2.2,
- Fixed or stressing couplers according to Clause 1.2.3,
- Steel ring E, see Annex 9,
- Isolation ring E for electrically isolated tendons only, see Annex 13,
- Bearing trumplate E, see Annex 8,
- Trumpet E and BBR VT Plastic Duct, see Annex 18, Annex 19, and Annex 20 and
- Protection cap E, see Annex 14.

Trumpet E continues through bearing trumplate E up to the steel ring. For electrically isolated tendon, isolation ring E is placed between bearing trumplate E and the steel ring. The steel ring

supports the anchor head A. Protection cap E encases the anchorage SAE, FAE and provides a port as inlet or vent that is sealed with a plug. Trumpet and BBR VT Plastic Duct are jointed with heat shrinking sleeve. The EIT performance of the tendon assembly, i.e., PL3², has been verified according to *fib* bulletin 75.

For couplers FKE, SKE, FHE, and SHE a plastic housing that encloses the transition length of the tendon is bolted to steel cushion plate and isolation ring E at the second construction stage. The steel cushion plate is bolted to bearing trumplate E of the first construction stage. The housing is connected to the plastic duct with a heat shrink sleeve at the second construction stage.

With electrically isolated tendon, the complete tendon, including prestressing steel strands, couplers, and anchorages, is fully encased with isolation material. The integrity of the electrical isolation can be verified and monitored via electrical resistance measurements between tendon and reinforcement of the structure.

1.2.9 Electrically isolated and replaceable tendon

Electrically isolated and replaceable tendons are electrically isolated tendons according to Clause 1.2.8 and are unbonded tendons. Replacing of electrically isolated tendons is available for

- Bare strands with grease, wax, or an equivalent soft material in bearing trumplate E and trumpet E
- Monostrands, grouted in bearing trumplate E and trumpet E, see Clause 1.2.10, can be replaced strand by strand, see Annex 79.

With electrically isolated and replaceable tendon, the complete tendon, including prestressing steel strands, and anchorages FEAR, SAER, is fully encased with isolation material. The integrity of the electrical isolation can be verified and monitored via electrical resistance measurements between tendon and reinforcement of the structure.

The tendon with prestressing steel strands, anchorage including steel ring E and isolation ring E can be replaced.

1.2.10 Tendon with monostrands

The tendon comprises monostrands in one common duct or in an inner trumpet A/E that is grouted prior to stressing. During grouting a sealing plate together with an activation plate is installed at the anchorage to arrange the monostrands and resist the grouting pressure. After grouting the monostrand ends are desheathed. For stressing, the anchor head A is placed on the grouted tendon.

Stressing can be commenced, once compressive strength of the grout is sufficiently developed. This is in general not before a compressive strength of ≥ 10 MPa is attained by the grout.

Tendon with monostrands allows for the smallest deflection radius of the tendon.

Exchange of tendons with monostrands is in general performed according to the Clauses 1.2.6 and 2.2.4.4. Tendons with straight tendon paths – or tendon paths that exhibit slight deviations only – can be exchanged in a strand-by-strand procedure, individually for each monostrand. However, in exchanging the prestressing steel strands, the monostrands are sufficiently completed with corrosion protection filling material. Tendons with inner trumpet A/E can be also completely exchanged with a whole new tendon.

1.2.11 Layout of the anchorage recess

All bearing trumplates, square plates, anchor heads, and coupler anchor heads are placed perpendicular to the axis of the tendon, see Annex 78, Annex 79, Annex 80, and Annex 81.

electronic copy
electronic copy
electronic copy
electronic copy
electronic copy
electronic copy
electronic copy


The dimensions of the anchorage recess are adapted to the prestressing jack used. The ETA holder saves for reference information on the minimum dimensions of the anchorage recess.

The formwork for the anchorage recess should be slightly conical for ease of removal. In case of anchorage fully embedded in concrete, the recess is designed so as to permit a reinforced concrete cover with the required dimensions and in any case with a thickness of at least 20 mm. In case of exposed anchorage, concrete cover of anchorage and bearing trumplate is not required. However, the exposed surfaces of bearing trumplate and steel cap are provided with corrosion protection.

Where required, bursting out of prestressing steel in case of failure of an unbonded tendon is prevented. Sufficient protection is provided by e.g., a cover of reinforced concrete.

1.3 Designation and range of the tendons

1.3.1 Designation

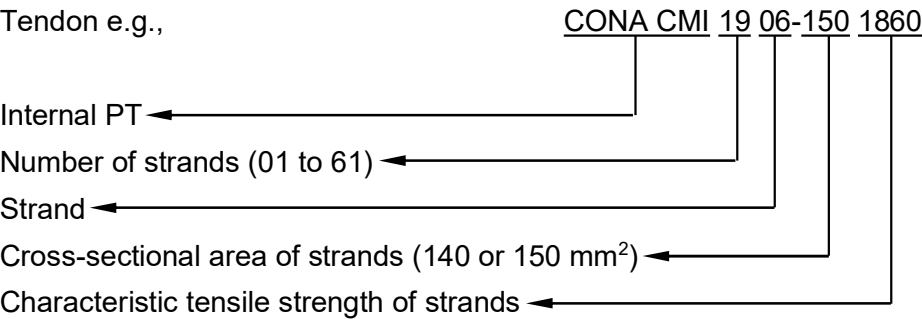

The tendons comprise 01 to 61 tensile elements, 7-wire prestressing steel strands according to Annex 27.

1.3.2 Range

1.3.2.1 General

Prestressing and oversteering forces are given in the corresponding standards and regulations in force at the place of use. The maximum prestressing and oversteering forces according to Eurocode 2 are listed in Annex 30.

The tendons consist of 01, 02, 03, 04, 05, 06, 07, 08, 09, 12, 13, 15, 16, 19, 22, 24, 25, 27, 31, 37, 42, 43, 48, 55, and 61 prestressing steel strands. By omitting prestressing steel strands in the anchorages and couplers in a radially symmetrical way, also tendons with numbers of prestressing steel strands lying between the numbers given above can be installed. Any unnecessary hole either remains undrilled or is provided with a short piece of strand and a wedge is inserted. Omitting prestressing steel strands in the same way also applies to anchorages nuclear (N).

For coupler anchor head K the cones of the outer pitch circle, second construction stage, may be equally redistributed if prestressing steel strands are omitted. However, the overall dimensions of the coupler anchor head K remain unchanged.

With regard to dimensions and reinforcement, anchorages and couplers with omitted prestressing steel strands remains unchanged compared to anchorages and couplers with a full number of prestressing steel strands.

1.3.2.2 CONA CMI n06-140

7-wire prestressing steel strand

Nominal diameter 15.3 mm

Nominal cross-sectional area 140 mm²

Maximum characteristic tensile strength 1 860 MPa

Annex 28 lists the available tendon range for CONA CMI n06-140.

1.3.2.3 CONA CMI n06-150

7-wire prestressing steel strand

Nominal diameter 15.7 mm

Nominal cross-sectional area 150 mm²

Maximum characteristic tensile strength 1 860 MPa

Annex 29 lists the available tendon range for CONA CMI n06-150.

1.4 Sheaths

1.4.1 General

For a bonded tendon, corrugated ducts are either in steel or plastic. For special applications such as loop tendons and unbonded tendons, smooth steel ducts can be used. Alternatively, corrugated plastic ducts may be used as well, if permitted at the place of use.

1.4.2 Degree of filling, f

The degree of filling is defined as

$$f = \frac{\text{cross-sectional area of prestressing steel}}{\text{cross-sectional area of inner diameter of sheath}}$$

Where

f Degree of filling

The degree of filling, f, generally is between 0.35 and 0.50. However, smaller values of degree of filling, 0.35 to 0.40, are used for long tendons or if the tensile elements are installed after concreting. The minimum radius of curvature can be obtained with the equation given in Clause 1.9. In Annex 31, Annex 32, Annex 33, Annex 34, Annex 35, and Annex 36 the degree of filling and corresponding minimum radius of curvature are given.

1.4.3 Circular steel strip sheaths

Steel strip sheath in conformity with EN 523² is used. For diameters exceeding EN 523 the requirements are met analogous. The degree of filling, f, is according to Clause 1.9 and the minimum radius of curvature to Clause 1.9.

Inner diameter of sheath and corresponding minimum radii of curvature, R_{min}, are given in Annex 31, Annex 32, Annex 33, Annex 34, and Annex 35 in which p_{R, max} has been set from 130 kN/m to 230 kN/m respectively. Smaller radii of curvature are acceptable according to the respective standards and regulations in force at the place of use.

The larger inner diameter of sheaths should be selected in the case of long tendons, > 80 m, or if the tensile elements are installed after concreting.

² Standards and Guidelines and other documents referred to in the European Technical Assessment are listed in Annex 90 and Annex 91.

1.4.4 Flat corrugated steel duct

For a tendon with 02, 03, 04, or 05 prestressing steel strands, a flat duct may be used, whereas EN 523 applies accordingly. Minor and major inner dimensions of the flat duct and minimum radii of curvature, both minor and major, are given in Annex 36 in which $p_{R, max}$ has been set from 130 kN/m to 230 kN/m. Smaller radii of curvature are acceptable according to the respective standards and regulations in force at the place of use.

1.4.5 Pre-bent smooth circular steel duct

If permitted at the place of use, a smooth steel duct according to EN 10255, EN 10216-1, EN 10217-1, EN 10219-1, or EN 10305-3 is used. The degree of filling, f , conforms to Clause 1.9 and the minimum radius of curvature to Clause 1.9. The duct is pre-bent and free of any kinks. The minimum wall thickness of the steel duct meets the specification of Table 2.

Table 2: Steel ducts, minimum wall thickness, t_{min}

Number of strands n	Minimum wall thickness t_{min}
—	mm
02–13	1.5
15–25	2.0
27–31	2.5
55	3.0

1.4.6 Corrugated plastic duct

The BBR VT Plastic Ducts are circular and flat ducts made of polypropylene according to Annex 23 with toroidal corrugations. The main dimensions of circular plastic ducts, designation 50 to 130, and flat plastic ducts are given in Annex 19 and Annex 20, respectively. These ducts are required for fully encapsulated tendons, i.e., PL2³, and the circular ducts as well as for electrically isolated tendons, i.e., PL3². The duct performance has been verified according to *fib* bulletin 75 for a temperature range of – 15 °C to + 45 °C.

Couplers to joint sections of plastic ducts and connections to trumpets of anchorages, see Annex 19 and Annex 20, are made with heat shrinking sleeves. For supporting the plastic ducts during installation, in general, no specific stiffeners are required. However, the use of rigid half-shells, see Annex 15, between duct and its supports at all high points along the tendon path is recommended for fully encapsulated as well as electrically isolated tendons in order to efficiently reduce the risk of perforation during stressing.

Inner diameters of circular ducts are given in Annex 19 and inner dimensions of flat ducts are given in Annex 20. For radii of curvature of circular ducts and flat ducts see Clause 1.9.

Segmental coupler for precast segmental bridge construction is given in Annex 21. It offers the corrosion protection level up to PL3, which has been verified according to *fib* bulletin 75. For application of segmental coupler see Annex 84, Annex 85, and Annex 86.

Alternatively, also other corrugated plastic ducts may be used, if permitted at the place of use as well as accepted by the relevant local authority and the ETA holder.

³ PL1, PL2, and PL3 are protection levels according to *fib* bulletin 33.

1.4.7 Plain plastic duct

For a tendon, grouted in inner trumpet A/E and installed inside an assembly of bearing trumplate A and trumpet A, plain plastic pipes are used as outer and inner ducts. After full release of the prestressing force, the complete tendon with inner duct and inner trumpet E can be pulled out from the structure and replaced by a new tendon, exchangeable tendon.

1.5 Friction losses

For the calculation of loss of prestressing force due to friction, Coulomb's law applies. Calculation of friction loss is by the equation

$$F_x = F_0 \cdot e^{-\mu \cdot (\alpha + k \cdot x)}$$

Where

- F_x kN..... Prestressing force at a distance x along the tendon
- F_0 kN..... Prestressing force at x = 0 m
- μrad⁻¹ Friction coefficient, see Table 3
- α rad Sum of the angular displacements over the distance x, irrespective of direction or sign
- krad/m Wobble coefficient, see Table 3
- xm Distance along the tendon from the point where the prestressing force is equal to F_0

NOTE 1 rad = 1 m/m = 1

Table 3: Friction parameters

Duct	Recommended values		Range of values	
	μ	k	μ	k
—	rad ⁻¹	rad/m	rad ⁻¹	rad/m
Steel strip sheath	0.18	0.005	0.17–0.19	0.004–0.007
Steel strip sheath with film of soap ¹⁾	0.13		—	
Smooth steel duct	0.18		0.15–0.24	
Smooth steel duct ¹⁾	0.16		—	
Corrugated plastic duct	0.12		0.10–0.14	
Smooth plastic duct	0.12		0.10–0.14	

¹⁾ For anchorages nuclear (N) and thoroughly aligned prestressing steel strands.
CONA CMI 5506, duct inner diameter ~ 160 mm

NOTE 1 As far as acceptable at the place of use, due to special measures like oiling or for a tendon layout with only few deviations the value of Table 3 can be reduced by 10 to 20 %. Compared to e.g., the use of prestressing steel or sheaths with a film of rust this value increases by more than 100 %.

NOTE 2 As far as acceptable at the place of use, circular steel strip sheath made of steel strips with a film of soap reduce the friction between prestressing steel strands and sheath, see Table 3.

Friction losses in anchorages and couplers to be taken into consideration in design and execution are given in Table 4.

Table 4: Friction losses in anchorage and couplers

Tendon	ΔF_s
—	%
CONA CMI 0206 to 0406	1.2
CONA CMI 0506 to 0906	1.1
CONA CMI 1206 to 3106	0.9
CONA CMI 3706 to 6106	0.8
SAN CONA CMI 5506 ¹⁾	0.2

¹⁾ For anchorages nuclear (N) and thoroughly aligned prestressing steel strands.

Where

ΔF_s % Friction loss in anchorages and first construction stage of fixed couplers. This is taken into account for determination of elongation and prestressing force along the tendon.

1.6 Support of tendons

Spacing of supports of steel strip sheaths and smooth steel ducts is between 1.0 m and 1.8 m. In the region of tendon curvatures, a spacing of 0.8 m, or 0.6 m in case the radius of curvature is smaller than 4.0 m is applied. For corrugated plastic ducts spacing of supports should be 0.6 m to 0.8 m or 0.6 m in case the radius of curvature is smaller than 4.0 m.

The tendons are systematically fastened in their position so that they are not displaced by placing and compacting the concrete. The use of rigid half-shells, see Annex 15, between corrugated plastic duct and its supports at all high points along the tendon path is recommended for fully encapsulated as well as electrically isolated tendons in order to efficiently reduce the risk of perforation during stressing.

1.7 Slip at anchorages and couplers

Slip at stressing anchorages, at fixed anchorages, and at fixed couplers, first and second construction stages, is 6 mm. Slip at moveable couplers is twice this amount. At stressing anchorage and at first construction stage of fixed couplers the slip is 4 mm, provided a prestressing jack with a wedge system and a wedging force of around 25 kN per strand is used.

Slip at anchorages nuclear (N) is maximum 8 mm. However, slip is measured in every project.

1.8 Centre spacing and edge distance for anchorages

In general, spacing and distances are not less than given in Annex 45, Annex 46, Annex 47, Annex 48 Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76. However, centre spacing of tendon anchorages may be reduced in one direction by up to 15 %, but not smaller than the outside diameter of the helix and placing of additional stirrup reinforcement is still possible when additional stirrup reinforcement is required. In this case centre spacing in the perpendicular direction is increased

by the same percentage, see also Annex 63 and Annex 77. The corresponding edge distances are calculated by

$$a_e = \frac{a_c}{2} - 10 \text{ mm} + c$$

$$b_e = \frac{b_c}{2} - 10 \text{ mm} + c$$

Where

- a_c mm..... Centre spacing
- b_c mm..... Centre spacing in the direction perpendicular to a_c
- a_e mm..... Edge distance
- b_e mm..... Edge distance in the direction perpendicular to a_e
- c mm..... Concrete cover

The minimum values for a_c , b_c , a_e , and b_e are given in Annex 37, Annex 38, Annex 39, Annex 40, Annex 41, Annex 42, Annex 43, and Annex 44.

Standards and regulations on concrete cover in force at the place of use are observed.

1.9 Minimum radii of curvature

Minimum radii of curvature, R_{\min} , for tendons with bare prestressing steel strands for circular sheaths, calculated according to the pressure under the prestressing steel strands, $p_{R, \max}$, are given in Annex 31, Annex 32, Annex 33, Annex 34, and Annex 35 and correspond to

- a prestressing force of the tendon of $F_{pm, 0} = 0.85 \cdot n \cdot F_{p0.1}$
- a nominal diameter of the prestressing steel strand Y1860S7 of $d = 15.7 \text{ mm}$
- a maximum pressure under the prestressing steel strands of $p_{R, \max} = 130 \text{ kN/m}$ to 230 kN/m
- a concrete compressive strength of $f_{cm, 0, \text{cube}} \geq 23 \text{ MPa}$.

In case of different tendon parameters or a different pressure under the prestressing steel strands, calculation of minimum radii of curvature of the tendon with circular sheaths can be carried out using the equation

For $n < 5$, with k_n according to Table 5.

$$R_{\min} = \max \left\{ \begin{array}{l} \frac{F_{pm, 0}}{p_{R, \max}} \cdot k_n \\ \text{and} \\ \frac{400 \cdot d}{3\,000} \end{array} \right.$$

For $n \geq 5$.

$$R_{\min} = \max \left\{ \begin{array}{l} \frac{2 \cdot F_{pm, 0} \cdot d}{d_i \cdot p_{R, \max}} \\ \text{and} \\ \frac{400 \cdot d}{3\,000} \end{array} \right.$$

Table 5: Factor k_n

Number of strands n	Factor k_n		
	$f \sim 0.25$	$f \sim 0.30$	$f \sim 0.35$
02	0.68	0.87	—
03	0.61	0.71	0.88
04	0.65		

Where

- R_{min}m Minimum radius of curvature
- $F_{pm, 0}$ kN..... Prestressing force of the tendon
- $F_{p0.1}$ kN..... Characteristic force at 0.1 % proof force of one single prestressing steel strand, see Annex 27
- $p_{R, max}$.. kN/m..... Maximum design pressure under the prestressing steel strands
- d mm..... Nominal diameter of the prestresing steel strand
- d_i mm..... Nominal inner diameter of duct
- k_n —..... Factor to account for number of prestressing steel strands and duct diameter, see Table 5
- n —..... Number of prestressing steel strands
- f —..... Degree of filling, see Clause 1.4.2

Minimum radii of curvature, R_{min} , for tendons with bare prestressing steel strands for flat ducts, calculated according to the pressure under the prestressing steel strands, $p_{R, max}$, are given in Annex 36. Thereby, the tendon parameters are as for circular ducts.

Alternatively, minimum radius of curvature for tendons, R_{min} , can be calculated by

$$R_{min} = \max \begin{cases} 2.8 \cdot \sqrt{F_{pk}} \\ \text{and} \\ 2.5 \text{ m} \end{cases}$$

Where

- F_{pk} MN Maximum force of the tendon, expressed in Mega Newton
- R_{min}m Minimum radius of curvature

For tendons with predominantly static loading, reduced minimum radii of curvature can be used. Recommended values for the pressure under the prestressing steel strands are

- $p_{R, max} = 130\text{--}230$ kN/m for internal bonded tendons
- $p_{R, max} = 800$ kN/m for smooth steel duct and predominantly static loading

In case of reduced minimum radii of curvature, the degree of filling, f , as defined in Clause 1.4.2, is between 0.25 and 0.3 to allow for proper tendon installation. Depending on the concrete strength at the time of stressing, additional reinforcement for splitting forces may be required in the areas of reduced minimum radii of curvature.

Standards and regulations on minimum radii of curvature or on the pressure under the prestressing steel strands in force at the place of use are observed.

Concrete in conformity with EN 206 is used.

For partial stressing with 30 % of the full prestressing force, the actual mean value of concrete compressive strength is at least $0.5 \cdot f_{cm, 0, \text{cube}}$ or $0.5 \cdot f_{cm, 0, \text{cylinder}}$. Intermediate values may be interpolated linearly according to Eurocode 2.

Table 6: Compressive strength of concrete

Specimen for testing			Mean concrete strength $f_{cm, 0}$								
Cube strength, 150 mm cube	$f_{cm, 0, \text{cube}}$	MPa	23	26	28	34	38	43	46	53	60
Cylinder strength, 150 mm cylinder diameter	$f_{cm, 0, \text{cylinder}}$	MPa	19	21	23	28	31	35	38	43	50

Helix, additional reinforcement, centre spacing, and edge distance corresponding to the concrete compressive strengths are taken from Annex 45, Annex 46, Annex 47, Annex 48 Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76, see also the Clauses 1.12.8 and 2.2.3.5.

Components

1.11 Prestressing steel strands

Only 7-wire prestressing steel strands with characteristics according to Table 7 are used, see also Annex 27. The corrosion protection system of the monostrands, comprising corrosion protection filling material and HDPE-sheathing, is as specified in Clause 1.15.4.

Table 7: Prestressing steel strands

Maximum characteristic tensile strength	f_{pk}	MPa	1 860 ¹⁾	
Nominal diameter	d	mm	15.3	15.7
Nominal cross-sectional area	A_p	mm ²	140	150
Mass of prestressing steel	M	kg/m	1.093	1.172

¹⁾ Prestressing steel strands with a characteristic tensile strength below 1 860 MPa may also be used.

In a single tendon, only prestressing steel strands spun in the same direction are used.

In the course of preparing the European Technical Assessment no characteristic has been assessed for the prestressing steel strands. In execution, a suitable prestressing steel strand that conforms to Annex 27 and is according to the standards and regulations in force at the place of use is taken.

1.12 Anchorage and coupler

1.12.1 General

The components of anchorages and couplers are in conformity with the specifications given in Annex 5, Annex 6, Annex 7, Annex 8, and Annex 9, Annex 10 and the technical file⁴. Therein the component dimensions, materials, and material identification data with tolerances are given.

1.12.2 Anchor head

The anchor heads A and N are made of steel and provide regularly arranged conical holes, drilled in parallel, to accommodate prestressing steel strands and wedges, see Annex 5, Annex 6, and Annex 10. The back exits of the bore holes are provided with bell mouth openings or plastic ring cushions. In addition, threaded bores may be provided to attach grouting cap or protection cap and the respective wedge retaining plate. At the back of the anchor head A there may be a step for ease of centring the anchor head A and N on bearing trumplates A, E, or N, on steel ring E, or on square plate.

1.12.3 Bearing trumplate

The bearing trumplate made of cast iron transmits the force via 3 anchorage planes to the concrete. Air-vents are situated at the top and at the interface plane to the anchor head. A ventilation tube can be fitted to these air-vents. On the tendon sided end there is an inner thread to take the trumpet.

The bearing trumplate used in tendons for cryogenic applications is made of spheroidal graphite cast iron, i.e., ductile cast iron.

There are three bearing trumplates. Firstly, bearing trumplate A with trumpet A, see Annex 8, secondly, bearing trumplate E, see Annex 8, for electrically isolated tendons with trumpet E, and thirdly bearing trumplate N, see Annex 10, for anchorage nuclear (N).

1.12.4 Square plate

The square plate is a flat steel plate, see Annex 8, and is connected to the trumpet A SP. In Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, and Annex 62 the main minimum dimensions of the square plate are listed. The square plate may be equipped with a drilled grout inlet, situated at the interface plane to the anchor head, with a connecting pipe to the trumpet.

1.12.5 Trumpets

The conical trumpets A, K, F, and N see Annex 11 and Annex 16, are made either in steel, in PE, or in PP.

The trumpets manufactured in steel have a corrugated or plain surface. In case the transition from trumpet to duct is made in steel, a 100 mm long and at least 3.5 mm thick PE-HD insert is installed at the deviating point of the prestressing steel strands.

⁴ The technical file of the European Technical Assessment is deposited at Österreichisches Institut für Bautechnik.

The conical trumpet N, see Annex 11, is made of steel and has a plain surface. At the duct side end, it is connected to deviator N in PE or PP, see Annex 1 and Annex 11.

The conical trumpets made of PE or PP may have either a corrugated or a plain surface. At the duct-side end there is a radius for the deviation of the prestressing steel strands and a smooth surface, to ensure a good transition to the duct. The opposite end is connected to the bearing trumplate.

The conical trumpets E, and inner trumpet A/E, see Annex 17 and Annex 18, are made of PP or PE and have a similar conical geometry as trumpet A.

1.12.6 Coupler anchor head K and H

The coupler anchor head K, see Annex 7, for the single plane coupler is made of steel and provides in the inner part for anchorage the prestressing steel strands of the first construction stage the same arrangement of holes as the anchor head A for the stressing or fixed anchorage. In the outer pitch circle, there is an arrangement of holes with an inclination of 7 ° to accommodate the prestressing steel strands of the second construction stage. A cover plate is fastened by means of additional threaded bores, see Annex 12.

Coupler anchor head H, see Annex 7, for the sleeve coupler H is made of steel and has the same basic geometry as anchor heads A of the stressing or fixed anchorage. Compared to anchor head A of the fixed and stressing anchor, the coupler anchor head H is deeper and provides an external thread for coupler sleeve H. Wedge retaining plate H, see Annex 13, is fastened by means of additional threaded bores.

The coupler sleeve H is a steel tube with an inner thread and provided with ventilation holes, see Annex 9.

At the back of coupler anchor heads K, H1 and H2 there is a step for ease of centring the coupler anchor head on bearing trumplates A or E, on steel ring E, or square plate.

Ring cushions, see Annex 5, are inserted in coupler anchor head H2.

1.12.7 Ring wedges

The ring wedges, see Annex 5 and Annex 10, are in either two pieces or three pieces. Three different ring wedges are used.

- Ring wedge H in three pieces, fitted with spring ring, is available in two different materials
- Ring wedge F in three pieces, without spring ring or fitted with spring ring
- Ring wedge G in two pieces, without spring ring or fitted with spring ring
- Ring wedge N in three pieces, fitted with spring ring

Within one anchorage or coupler, only one of these ring wedges is used.

In the case of fixed anchors and couplers, the wedges are held in place by a wedge retaining plate, by springs with a wedge retaining plate, or by springs with a cover plate. An alternative is pre-locking each individual strand with $\sim 0.5 \cdot F_{pk}$ and applying a wedge retaining plate as per Clause 1.2.2.

Where

F_{pk} N Characteristic value of maximum force of one single strand

1.12.8 Additional reinforcement

For tendons with 02 to 55 prestressing steel strands in CONA CMI BT system three options for additional reinforcement are available.

- Only helix, up to 37 prestressing steel strands,
- Only additional stirrup reinforcement, or
- Both, helix and additional stirrup reinforcement.

For tendons with 61 prestressing steel strands in CONA CMI BT system and for tendons with 01 to 61 prestressing steel strands in CONA CMI SP system only the option of using both helix and additional stirrup reinforcement is available.

Helix and additional stirrup reinforcement are made of ribbed reinforcing steel. The end of the helix on the anchorage side is welded to the next turn. The helix is placed exactly in the tendon axis. The helix and additional stirrup reinforcement dimensions conform to the values specified in Annex 45, Annex 46, Annex 47, Annex 48, Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76.

If required for a specific project design, the reinforcement given in Annex 45, Annex 46, Annex 47, Annex 48, Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76 may be modified in accordance with the respective regulations in force at the place of use as well as with the relevant approval of the local authority and of the ETA holder to provide equivalent performance.

1.12.9 Caps

1.12.9.1 General

Recessed and exposed anchorages without ventilated protection caps or grouting caps are not executed. All inaccessible or accessible fixed anchorages FA are equipped with protection caps or grouting caps to ensure a fully continuous corrosion protection of the tendon from all wedges of the one end to all wedges of the other end.

1.12.9.2 Grouting cap

The grouting cap A in PE, shown in Annex 1, Annex 2, Annex 3, Annex 4, and Annex 14, is for stressing anchorage SA, accessible fixed anchorage FA and fixed and stressing coupler FK and SK. It is provided with an air-vent and attached to the anchor head A with screws. The grouting cap A is a permanent UV-protected plastic cap that resists a grouting pressure up to maximum 1 500 kPa. The cap is for one-time use and left in place after grouting. The anchorage recess is completed with concrete to provide a concrete cover as required, at least with a thickness of 20 mm at the grouting cap A.

Alternatively, the anchorage recess is not completed with concrete. However, in this case exposed surfaces of steel or cast iron components are provided with corrosion protection.

1.12.9.3 Protection caps

The protection caps A, E, and N, shown in Annex 1, Annex 3, Annex 4, Annex 11, and Annex 14, are provided with an air-vent and attached to the anchorage with screws or threaded rods. The protection caps are permanent and cap A made of steel or plastic and cap E is made of plastic only.

- Protection cap A in steel fully encases anchor head A with ring wedges and is left in place after grouting. The permanent steel cap is used for inaccessible and accessible fixed anchorages FA.
- Protection cap A in plastic, see Annex 14, is a permanent UV-protected plastic cap that fully encases anchor head and ring wedges. The cap is permanent and for one-time use only. The protection cap is used for inaccessible and accessible fixed anchorages FA.
- Protection cap E in plastic, see Annex 14, is a permanent UV-protected plastic cap that fully encases anchor head and ring wedges. The cap is permanent and for one-time use only. Protection cap E is used for fully encapsulated and electrically isolated tendons. In particular, it is attached to electrically isolated inaccessible and accessible fixed anchorages FAE and stressing anchorages SAE. After grouting all inlet and outlet ports of the electrically isolated tendon are sealed with suitable plugs to provide fully electrically isolation.
- Protection cap N in steel, see Annex 11, is a permanent steel cap that fully encases anchor head and ring wedges. The cap is permanent and for one-time use only. The protection cap is used for anchorage nuclear (N).

In restressable tendons, see Annex 3 and Annex 4, adapted longer protection caps are used to fully encase anchor head with excess length of the prestressing steel strands.

1.12.10 Accessories for inlets and outlets

Grouting accessories, see Annex 15, are made of plastic and are available for inlets and outlets to facilitate grouting of the tendons and thus ensure permanent corrosion protection by means of cement grout.

1.13 Sheaths

1.13.1 Steel strip sheaths

The steel strip sheaths are in conformity with the specifications given in Annex 22.

1.13.2 Steel duct

The steel ducts are in conformity with the specifications in Clause 1.4.5.

1.13.3 Plastic ducts

The plastic ducts are in conformity with the specifications given in Annex 19, Annex 20, Annex 23, Annex 24, Annex 25, and Annex 26.

1.14 Material specifications

In Annex 22 the material specifications of the components are given.

1.15 Permanent corrosion protection

1.15.1 General

In the course of preparing the European Technical Assessment, no characteristic has been assessed for components and materials of the corrosion protection system, except plastic ducts, see the Clauses 1.4.6 and 1.13.3. In execution, all components or materials are selected according to the standards and regulations in force at the place of use.

1.15.2 Grout

The sheaths, anchorages, and couplers are completely filled with grout according to EN 447 to protect the tendons from corrosion and to provide bond between the tendons and the structure.

To protect the tendons from corrosion and to provide bond between tendon and structure ducts, anchorages, and couplers are completely filled with grout according to EN 447, special grout

according to EAD 160027-00-0301, or special grout as applicable at the place of use. Complete filling is ensured by grout penetrating from the vents, and from protection caps or grouting caps at the anchorages.

Tendons grouted in inner trumpet A/E and installed inside assembly of bearing trumplate A and trumpet A are unbonded tendons.

1.15.3 Unbonded tendon

To protect the tendons from corrosion, ducts, anchorages, and couplers are completely filled with corrosion protection filling material. Complete filling is ensured by corrosion protection filling material penetrating from the vents, and from protection caps or grouting caps at the anchorages.

Corrosion protection filling material is grease or wax according to EAD 160027-00-0301, or an equivalent soft material as applicable at the place of use. As an alternative, corrosion protection filling material according to the standards and regulations in force at the place of use may be applied.

Tendons grouted in inner trumpet A/E and installed inside assembly of bearing trumplate A and trumpet A are unbonded tendons.

1.15.4 Monostrand

Monostrand is a prestressing steel strand that is factory-provided with a corrosion protection filling material and an extruded HDPE sheathing. The corrosion protection filling material for monostrands is specified in EAD 160027-00-0301 or an equivalent soft material as applicable at the place of use. Monostrands according to the standards and regulations in force at the place of use may be applied.

Tendons with monostrands, installed in bearing trumplate A and trumpet A, or bearing trumplate A, inner trumpet A/E and trumpet A, are grouted prior to stressing.

Tendons with monostrands are unbonded tendons.

2 Specification of the intended uses in accordance with the applicable European Assessment Document (hereinafter EAD)

2.1 Intended uses

The PT system BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands is intended to be used for the prestressing of structures. The specific intended uses are listed in Table 8.

Table 8: Intended uses

Line №	Use category
Use categories according to tendon configuration and material of structure	
1	Internal bonded tendon for concrete and composite structures
2	Internal unbonded tendon for concrete and composite structures
Optional use categories	
3	Internal tendon for cryogenic applications with anchorage outside the possible cryogenic zone
4	Internal tendon for cryogenic applications with anchorage inside the possible cryogenic zone
5	Internal bonded tendon with corrugated plastic duct made of PP
6	Encapsulated tendon
7	Electrically isolated tendon

2.2 Assumptions

2.2.1 General

Concerning product packaging, transport, storage, maintenance, replacement, and repair it is the responsibility of the manufacturer to undertake the appropriate measures and to advise his clients on transport, storage, maintenance, replacement, and repair of the product, as he considers necessary.

2.2.2 Packaging, transport, and storage

Advice on packaging, transport, and storage includes.

- During transport of prefabricated tendons, a minimum diameter of curvature of
 - 1.65 m for tendons up to CONA CMI 1206,
 - 1.80 m for tendons up to CONA CMI 3106, and
 - 2.00 m for tendons larger than CONA CMI SP 3106
 of prestressing steel strands is observed.
- Temporary protection of prestressing steel and components in order to prevent corrosion during transport from production site to job site
- Transportation, storage, and handling of prestressing steel and other components in a manner as to avoid damage by mechanical or chemical impact

- Protection of prestressing steel and other components from moisture
- Keeping tensile elements separate from areas where welding operations are performed

2.2.3 Design

2.2.3.1 General

It is the responsibility of the ETA holder to ensure that all necessary information on design and installation is submitted to those responsible for design and execution of the structures executed with "BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands".

Design of the structure permits correct installation and stressing of the tendons. The reinforcement in the anchorage zone permits correct placing and compacting of concrete.

2.2.3.2 Fixed and stressing coupler

The prestressing force at the second construction stage may not be greater than that at the first construction stage, neither during construction, nor in the final state, nor due to any load combination. However, if free movement of the coupler is ensured by a housing, the prestressing force at the second construction stage can be greater than at the first construction stage, provided that grouting of first and second construction stages is performed after stressing of the second construction stage. Length of housing is for the expected elongation displacement of the coupler, see Clause 2.2.4.1.

2.2.3.3 Anchorage Recess

Clearance is required for handling of prestressing jacks and for stressing. The dimensions of the anchorage recess are adapted to the prestressing jack used. The ETA holder keeps available information on prestressing jacks and appropriate clearance behind the anchorage.

The anchorage recess is designed with such dimensions as to ensure the required concrete cover and at least 20 mm at the protection cap in steel in the final state.

In case of exposed anchorages, concrete cover on anchorage, bearing trumplate and square plate is not required. However, the exposed surface of bearing trumplate, square plate and steel cap is provided with corrosion protection.

Where required, bursting out of prestressing steel in case of failure of an unbonded tendon is prevented. Sufficient protection is provided by e.g., a cover of reinforced concrete.

2.2.3.4 Maximum prestressing force

The prestressing and overstressing forces are specified in the respective standards and regulations in force at the place of use. Annex 30 lists the maximum prestressing and overstressing forces according to Eurocode 2.

2.2.3.5 Reinforcement in the anchorage zone

Additional reinforcement as helix, or additional stirrup reinforcement, or helix and additional stirrup reinforcement given in Annex 45, Annex 46, Annex 47, Annex 48, Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76 are adopted.

Verification of transfer of prestressing forces to structural concrete is not required if centre spacing and edge distances of anchorages and couplers as well as grade and dimensions of additional reinforcement, see Annex 45, Annex 46, Annex 47, Annex 48, Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and

Annex 76 are conformed to. In the case of grouped anchorages, the additional reinforcement of the individual anchorages can be combined, provided appropriate anchorage is ensured. However, number, cross-sectional area and position with respect to the bearing trumplates remains unchanged.

The reinforcement of the structure is not employed as additional reinforcement. Reinforcement exceeding the required reinforcement of the structure may be used as additional reinforcement, provided appropriate placing is possible.

The forces outside the area of the additional reinforcement are verified and, if necessary, dealt with by appropriate reinforcement.

If required for a specific project design, the reinforcement given in Annex 45, Annex 46, Annex 47, Annex 48, Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76 may be modified in accordance with the respective regulations in force at the place of use as well as with the relevant approval of the local authority and of the ETA holder to provide equivalent performance.

2.2.3.6 Tendons in masonry structures – Load transfer to the structure

Post-tensioning kits are primarily used in structures made of concrete. They can, however, be used with other structural materials, e.g., in masonry structures. However, there is no particular assessment in EAD 160004-00-0301 for these applications. Hence, load transfer of prestressing force to masonry structures is via concrete or steel members designed according to the European Technical Assessment, in particular according to the Clauses 1.8, 1.12.8, and 2.2.3 or Eurocode 3 respectively.

The concrete or steel members have such dimensions as to permit a force of $1.1 \cdot F_{pk}$ being transferred into the masonry. The verification is performed according to Eurocode 6 as well as to the respective standards and regulations in force at the place of use.

2.2.4 Installation

2.2.4.1 General

It is assumed that the product will be installed according to the manufacturer's instructions or – in absence of such instructions – according to the usual practice of the building professionals.

Assembly and installation of tendons are only carried out by qualified PT specialist companies with the required resources and experience in the use of multi strand bonded and unbonded post-tensioning systems, see CWA 14646. The respective standards and regulations in force at the place of use are considered. The company's PT site manager has a certificate, stating that she or he has been trained by the ETA holder and that she or he possesses the necessary qualifications and experience with the "BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands".

The sequence of work steps for installation of anchorage, fixed and moveable coupler is described in Annex 82 and Annex 83.

The tendons may be manufactured on site or in the factory, i.e., prefabricated tendons. The tendons are carefully handled during production, transport, storage, and installation. To avoid confusion, on each site only prestressing steel strands with one nominal diameter are used.

Bearing trumplate, anchor head, and coupler anchor head are placed perpendicular to the tendon's axis. Couplers are situated in a straight tendon section. At the anchorages and couplers the tendon layout provides a straight section over a length of at least 250 mm beyond the end of the trumpet. In case of tendons with a minimum or reduced radius of curvature after the trumpet, the following minimum straight lengths after the end of trumpet are recommended.

- Degree of filling $0.35 \leq f \leq 0.50$, minimum straight length = $5 \cdot d_i \geq 250$ mm
- Degree of filling $0.25 \leq f \leq 0.30$, minimum straight length = $8 \cdot d_i \geq 400$ mm

Where

f..... — Degree of filling

d_i mm Nominal inner diameter of duct

Installation is carried out according to Annex 82 and Annex 83.

Before placing the concrete, a final check of the installed tendons or sheaths is carried out.

In the case of the single plane coupler K, the prestressing steel strands are provided with markers to be able to check the depth of engagement.

In case of a movable coupler, it is ensured by means of corresponding position and of length of the coupler sheath, that in the area of coupler sheath and corresponding trumpet area a displacement of the movable coupler of at least $1.15 \cdot \Delta l + 30$ mm is possible without any hindrance, where Δl is the maximum expected displacement of the coupler at stressing. The same applies to the housing of a fixed or stressing coupler when prestressing force at the second construction stage is greater than at the first construction stage.

2.2.4.2 Stressing operation

With a mean concrete compressive strength in the anchorage zone according to the values laid down in Annex 45, Annex 46, Annex 47, Annex 48, Annex 49, Annex 50, Annex 51, Annex 52, Annex 53, Annex 54, Annex 55, Annex 56, Annex 57, Annex 58, Annex 59, Annex 60, Annex 61, Annex 62, Annex 64, Annex 65, Annex 66, Annex 67, Annex 68, Annex 69, Annex 70, Annex 71, Annex 72, Annex 73, Annex 74, Annex 75, and Annex 76 full prestressing may be applied.

Stressing and, if applicable, wedging is carried out using a suitable prestressing jack. The wedging force corresponds to approximately 25 kN per wedge.

Elongation and prestressing forces are continuously checked during the stressing operation. The results of the stressing operation are recorded and the measured elongations compared with the prior calculated values.

After releasing the prestressing force from the prestressing jack, the tendon pulls the prestressing steel strands by the amount of the slip into the anchor head.

Information on the prestressing equipment has been submitted to Österreichisches Institut für Bautechnik. The ETA holder keeps available information on prestressing jacks and appropriate clearance behind the anchorage.

The safety-at-work and health protection regulations shall be complied with.

2.2.4.3 Restressing

Restressing of tendons in combination with release and reuse of wedges is permitted, whereas the wedges bite into a least 15 mm of virgin strand surface and no wedge bite remains inside the final length of the tendon between anchorages.

For tendons remaining restressable throughout the working life of the structure, Grease, wax, or an equivalent soft material is used as filling material or circulating dry air is used as corrosion protection. Moreover, a strand protrusion at the stressing anchor remains with a length,

compatible with the prestressing jack used. The protruding prestressing steel strands are provided with an appropriate corrosion protection and a long protection cap is attached to the anchorage, see Annex 3 and Annex 4.

2.2.4.4 Exchange of tendons

Specifications for exchangeable tendons are defined during the design phase. The tendon layout requires special attention to allow for full release of prestressing force and pulling out, in particular of a grouted tendon. Subject of exchange is either

- The prestressing steel strands as complete tendon
- The prestressing steel strands as stand by strand
- The complete tendon including grouted prestressing steel strands, duct, and inner trumpet
- The complete tendon with grouted monostrands, duct, and inner trumpet

Unless special procedures are considered already in the design phase of the structure, strand protrusions remain at the stressing anchor with a length compatible with the prestressing jack and allowing for release of the complete prestressing force. Moreover, soft corrosion protection filling material according to Clause 2.2.4.5.2 is applied.

Stressing and fixed anchorages are accessible and adequate clearance is provided behind the anchorages.

Tendon with bare strands, grouted in inner trumpet A/E and installed inside assembly of bearing trumplate A and trumpet A, can only be completely removed and replaced with a new tendon. After full release of the prestressing force, the complete tendon with inner trumpet A/E is pulled out from the structure and replaced by a new tendon.

Tendon with grouted monostrands can be exchanged strand by strand. The replacement strands are sufficiently completed with corrosion protection filling material. Tendon with grouted monostrands in inner trumpet A/E and installed inside assembly of bearing trumplate A and trumpet A, can be completely removed and replaced with a new tendon. After full release of the prestressing force, the complete tendon with inner trumpet A/E is pulled out from the structure and replaced by a new tendon.

To remove a tendon with grouted strands or grouted monostrands requires particular attention regarding

- Access to allow for cutting the tendon
- Tendon layout with curvature to allow the tendon to be pulled out
- Access to stressing and fixed anchorages
- Clearance behind stressing and fixed anchorage to pull out the tendon

2.2.4.5 Filling operations

2.2.4.5.1 Grouting

Grouting accessories such as inlets, outlets, caps, vents, etc. require compatibility with the PT system and provide sufficient tightness. Grouting caps or protection caps are always used to ensure proper grouting of tendon and to avoid voids around the wedges. Grout is injected through the inlet holes until it escapes from the outlet tubes with the same consistency. To avoid voids in the hardened grout special measures are applied for long tendons, tendon paths with distinct high points or inclined tendons. All vents and grouting inlets are sealed immediately after grouting. In case of K-couplers, the holes of the second stage, together with wedges and springs are checked for cleanness before and immediately after grouting the first construction stage.

The standards, observed for cement grouting in prestressing ducts, are EN 445, EN 446, and EN 447, EAD 160027-00-0301, or the standards and regulations in force at the place of use applies for ready mixed grout. For nuclear applications, project specific requirements for grout may apply at the place of use.

The results of the grouting operation are recorded in grouting records.

2.2.4.5.2 Filling with grease, wax, and an equivalent soft material

The recommendations of the supplier are relevant for the filling material applied. The filling process with grease, wax, or an equivalent soft material follows a similar procedure as the one specified for grouting. However, a different filling procedure might be possible if permitted at the place of use.

2.2.4.5.3 Circulating dry air

Actively circulating dry air allows for corrosion protection of tendons, provided a permanent monitoring of the drying and circulation system is in place. This is in general only applicable to structures of particular importance. The respective standards and regulations in force at the place of use are observed.

2.2.4.5.4 Filling records

The results of the grouting and filling operation are recorded in detail in filling records.

2.2.4.6 Welding

Ducts may be welded.

The helix may be welded to bearing trumplate and square plate to secure its position.

After installation of the tendons, no further welding operations are carried out on the tendons. In case of welding operations near tendons, precautionary measures are required to avoid damage. However, plastic components may be welded even after installation of the tendons.

2.3 Assumed working life

The European Technical Assessment is based on an assumed working life of the BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands of 100 years, provided that the BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands is subject to appropriate installation, use, and maintenance, see Clause 2.2. These provisions are based upon the current state of the art and the available knowledge and experience.

In normal use conditions, the real working life may be considerably longer without major degradation affecting the basic requirements for construction works⁵.

The indications given as to the working life of the construction product cannot be interpreted as a guarantee, neither given by the product manufacturer or his representative nor by EOTA nor by the Technical Assessment Body, but are regarded only as a means for expressing the expected economically reasonable working life of the product.

⁵ The real working life of a product incorporated in a specific works depends on the environmental conditions to which that works are subject, as well as on the particular conditions of design, execution, use, and maintenance of that works. Therefore, it cannot be excluded that in certain cases the real working life of the product may also be shorter than the assumed working life.

3 Performance of the product and references to the methods used for its assessment

3.1 Essential characteristics

The performances of the PT system for the essential characteristics are given in Table 9. In Annex 89, the combinations of essential characteristics and corresponding intended uses are listed.

Table 9: Essential characteristics and performances of the product

Essential characteristic	Method of assessment	Product performance
Basic requirement for construction works 1: Mechanical resistance and stability		
Resistance to static load	See Clause 3.2.1.1.	See Clause 3.2.1.1.
Resistance to fatigue	See Clause 3.2.1.2.	See Clause 3.2.1.2.
Load transfer to the structure	See Clause 3.2.1.3.	See Clause 3.2.1.3.
Friction coefficient	EAD 160004-00-0301, Clause 2.2.4.	See Clause 3.2.1.4.
Deviation / deflection (limits) for internal bonded and internal unbonded tendon	EAD 160004-00-0301, Clause 2.2.5	See Clause 3.2.1.5.
Assessment of assembly	See Clause 3.2.1.6.	See Clause 3.2.1.6.
Resistance to static load under cryogenic conditions for applications with anchorage / coupling outside the possible cryogenic zone	See Clause 3.2.1.7.	See Clause 3.2.1.7.
Resistance to static load under cryogenic conditions for applications with anchorage / coupling inside the possible cryogenic zone	See Clause 3.2.1.8.	See Clause 3.2.1.8.
Material properties, component performance, system performance of plastic duct (PL1)	See Clause 3.2.1.9.	See Clause 3.2.1.9.
Material properties, component performance, system performance of plastic duct to provide an encapsulated tendon (PL2)	See Clause 3.2.1.10.	See Clause 3.2.1.10.
Material properties, component performance, system performance of plastic duct to provide an electrically isolated tendon (PL3)	See Clause 3.2.1.11.	See Clause 3.2.1.11.
Corrosion protection	See Clause 3.2.1.12.	See Clause 3.2.1.12.
Basic requirement for construction works 2: Safety in case of fire		
Reaction to fire	See Clause 3.2.2.1.	See Clause 3.2.2.1.

Essential characteristic	Method of assessment	Product performance
Basic requirement for construction works 3: Hygiene, health, and the environment		
Content, emission, and/or release, of dangerous substances	See Clause 3.2.3.1.	See Clause 3.2.3.1.
Basic requirement for construction works 4: Safety and accessibility in use		
Not relevant. No characteristic assessed.		—
Basic requirement for construction works 5: Protection against noise		
Not relevant. No characteristic assessed.		—
Basic requirement for construction works 6: Energy economy and heat retention		
Not relevant. No characteristic assessed.		—
Basic requirement for construction works 7: Sustainable use of natural resources		
No characteristic assessed.		—

3.2 Product performance

3.2.1 Mechanical resistance and stability

3.2.1.1 Resistance to static load

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.1. The characteristic values of maximum force, F_{pk} , of tendon with prestressing steel strands according to Annex 27 are listed in Annex 28 and Annex 29.

3.2.1.2 Resistance to fatigue

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.2. Fatigue resistance of anchors and couplers was tested and verified with an upper force of $0.65 \cdot F_{pk}$, a fatigue stress range of 80 MPa, and $2 \cdot 10^6$ load cycles. The characteristic values of maximum force, F_{pk} , of tendon with prestressing steel strands according to Annex 27 are listed in Annex 28 and Annex 29.

3.2.1.3 Load transfer to the structure

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.3. Conformity with the stabilisation and crack width criteria specified for the load transfer test was verified to a force level of $0.80 \cdot F_{pk}$. The characteristic values of maximum force, F_{pk} , of tendons with prestressing steel strands according to Annex 27 are listed in Annex 28 and Annex 29.

3.2.1.4 Friction coefficient

For friction losses including friction coefficient see Clause 1.5.

3.2.1.5 Deviation / deflection (limits) for internal bonded and internal unbonded tendon

For minimum radii of curvature see Clause 1.9.

3.2.1.6 Assessment of assembly

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.7.

3.2.1.7 Resistance to static load under cryogenic conditions for applications with anchorage / coupling outside the possible cryogenic zone

The PT system with and without plastic duct as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.8.

3.2.1.8 Resistance to static load under cryogenic conditions for applications with anchorage / coupling inside the possible cryogenic zone

The PT system with and without plastic duct in the sizes up to 31 prestressing steel strands as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.9.

3.2.1.9 Material properties, component performance, system performance of plastic duct (PL1)

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.10. For the characteristic values of material properties and component performance see Annex 23 and for system performance see Annex 24, Annex 25, and Annex 26.

3.2.1.10 Material properties, component performance, system performance of plastic duct to provide an encapsulated tendon (PL2)

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.11. For the characteristic values of material properties and component performance see Annex 23 and for system performance see Annex 24, Annex 25, and Annex 26.

3.2.1.11 Material properties, component performance, system performance of plastic duct to provide an electrically isolated tendon (PL3)

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.12. For the characteristic values of material properties and component performance see Annex 23 and for system performance see Annex 24, Annex 25, and Annex 26.

3.2.1.12 Corrosion protection

The PT system as described in the ETA meets the acceptance criteria of EAD 160004-00-0301, Clause 2.2.13.

3.2.2 Safety in case of fire

3.2.2.1 Reaction to fire

The performance of components made of steel or cast iron is Class A1 without testing.

The performance of components of other materials has not been assessed.

3.2.3 Hygiene, health, and the environment

3.2.3.1 Content, emission and/or release of dangerous substances

According to the manufacturer's declaration, the PT system does not contain dangerous substances.

– SVOC and VOC

The performance of components made of steel or cast iron that are free of coating with organic material is no emission of SVOC and VOC.

The performance of components of other materials has not been assessed.

- Leachable substances

The product is not intended to be in direct contact to soil, ground water, and surface water.

3.3 Assessment methods

The assessment of the essential characteristics in Clause 3.1 of the PT system, for the intended uses, and in relation to the requirements for mechanical resistance and stability, safety in case of fire, and for hygiene, health and the environment, in the sense of the basic requirements for construction works № 1, 2, and 3 of Regulation (EU) № 305/2011, has been made in accordance with Annex A of EAD 160004-00-0301, Post-tensioning kits for prestressing of structures, for

- Item 1, Internal bonded tendon
- Item 2, Internal unbonded tendon
- Item 4, Internal unbonded tendon
- Item 8, Optional use category: Internal tendon – Cryogenic applications with anchorage / coupling outside the possible cryogenic zone
- Item 9, Optional use category: Internal tendon – Cryogenic applications with anchorage / coupling outside the possible cryogenic zone
- Item 10, Optional use category: Internal tendon – Cryogenic applications with anchorage / coupling inside the possible cryogenic zone
- Item 11, Optional use category: Internal tendon – Cryogenic applications with anchorage / coupling inside the possible cryogenic zone
- Item 12, Optional use category: Internal bonded tendon with plastic (polymer) duct
- Item 13, Optional use category: Encapsulated (bonded) tendon
- Item 14, Optional use category: Electrically isolated (bonded) tendon

3.4 Identification

The European Technical Assessment for the PT system is issued on the basis of agreed data⁶ that identify the assessed product. Changes to materials, to composition, to characteristics of the product, or to the production process could result in these deposited data being incorrect. Österreichisches Institut für Bautechnik should be notified before the changes are introduced, as an amendment of the European Technical Assessment is possibly necessary.

⁶ The technical file of the European Technical Assessment is deposited at Österreichisches Institut für Bautechnik.

4 Assessment and verification of constancy of performance (hereinafter AVCP) system applied, with reference to its legal base

4.1 System of assessment and verification of constancy of performance

According to Commission Decision 98/456/EC the system of assessment and verification of constancy of performance to be applied to the BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands is System 1+. System 1+ is detailed in Commission Delegated Regulation (EU) № 568/2014 of 18 February 2014, Annex, point 1.1, and provides for the following items.

- (a) The manufacturer shall carry out
 - (i) factory production control;
 - (ii) further testing of samples taken at the manufacturing plant by the manufacturer in accordance with the prescribed test plan⁷.
- (b) The notified product certification body shall decide on the issuing, restriction, suspension, or withdrawal of the certificate of constancy of performance of the construction product on the basis of the outcome of the following assessments and verifications carried out by that body
 - (i) an assessment of the performance of the construction product carried out on the basis of testing (including sampling), calculation, tabulated values, or descriptive documentation of the product;
 - (ii) initial inspection of the manufacturing plant and of factory production control;
 - (iii) continuing surveillance, assessment, and evaluation of factory production control;
 - (iv) audit-testing of samples taken by the notified product certification body at the manufacturing plant or at the manufacturer's storage facilities.

4.2 AVCP for construction products for which a European Technical Assessment has been issued

Notified bodies undertaking tasks under System 1+ shall consider the European Technical Assessment issued for the construction product in question as the assessment of the performance of that product. Notified bodies shall therefore not undertake the tasks referred to in Clause 4.1, point (b) (i).

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable EAD

5.1 Tasks for the manufacturer

5.1.1 Factory production control

The kit manufacturer exercises permanent internal control of the production. All the elements, procedures, and specifications adopted by the kit manufacturer are documented in a systematic manner in the form of written policies and procedures.

- Control of the incoming materials

The manufacturer checks the incoming materials to establish conformity with their specifications.

⁷ The prescribed test plan has been deposited with Österreichisches Institut für Bautechnik and is handed over only to the notified product certification body involved in the procedure for the assessment and verification of constancy of performance. The prescribed test plan is also referred to as control plan.

- Inspection and testing

Kind and frequency of inspections, tests, and checks, conducted during production and on the final product normally include.

- Definition of the number of samples taken by the kit manufacturer
- Material properties e.g., tensile strength, hardness, surface finish, chemical composition, etc.
- Determination of the dimensions of components
- Check correct assembly
- Documentation of tests and test results

At least once a year the manufacturer audits the manufacturers of the components given in Annex 88. All tests are performed according to written procedures with suitable calibrated measuring devices. All results of inspections, tests, and checks are recorded in a consistent and systematic way. The basic elements of the prescribed test plan are given in Annex 87, conform to EAD 160004-00-0301, Table 3, and are specified in the quality management plan of the BBR VT CONA CMI – Internal Post-tensioning System with 01 to 61 Strands.

The results of inspections, tests, and checks are evaluated for conformity. Shortcomings request the manufacturer to immediately implement measures to eliminate the defects.

- Control of non-conforming products

Products, which are considered as not conforming to the prescribed test plan, are immediately marked and separated from such products that do conform. Factory production control addresses control of non-conforming products.

- Complaints

Factory production control includes procedures to keep records of all complaints about the PT system.

The records are presented to the notified product certification body involved in continuous surveillance and are kept at least for ten years after the product has been placed on the market. On request, the records are presented to Österreichisches Institut für Bautechnik.

5.1.2 Declaration of performance

The manufacturer is responsible for preparing the declaration of performance. When all the criteria of the assessment and verification of constancy of performance are met, including the certificate of constancy of performance issued by the notified product certification body, the manufacturer draws up the declaration of performance. Essential characteristics to be included in the declaration of performance for the corresponding intended use are given in Table 9. In Annex 89 the combinations of essential characteristics and corresponding intended uses are listed.

5.2 Tasks for the notified product certification body

5.2.1 Initial inspection of the manufacturing plant and of factory production control

The notified product certification body establishes that, in accordance with the prescribed test plan, the manufacturing plant, in particular personnel and equipment, and the factory production control are suitable to ensure a continuous manufacturing of the PT system according to the given technical specifications. For the most important activities, EAD 160004-00-0301, Table 4 summarises the minimum procedure.

5.2.2 Continuing surveillance, assessment, and evaluation of factory production control

The activities are conducted by the notified product certification body and include surveillance inspections. The kit manufacturer is inspected at least once a year. Factory production control is inspected and samples are taken for independent single tensile element tests.

For the most important activities, the control plan according to EAD 160004-00-0301, Table 4 summarises the minimum procedure. It is verified that the system of factory production control and the specified manufacturing process are maintained, taking account of the control plan.

Each manufacturer of the components given in Annex 88 is audited at least once in five years. It is verified that the system of factory production control and the specified manufacturing process are maintained, taking account of the prescribed test plan.

The results of continuous surveillance are made available on demand by the notified product certification body to Österreichisches Institut für Bautechnik. When the provisions of the European Technical Assessment and the prescribed test plan are no longer fulfilled, the certificate of constancy of performance is withdrawn by the notified product certification body.

5.2.3 Audit-testing of samples taken by the notified product certification body at the manufacturing plant or at the manufacturer's storage facilities


During surveillance inspection, the notified product certification body takes samples of components of the PT system for independent testing. Audit-testing is conducted at least once a year by the notified product certification body. For the most important components, Annex 88 summarises the minimum procedures. Annex 88 conforms to EAD 160004-00-0301, Table 4. In particular, at least once a year, the notified product certification body also carries out one single tensile element test series according to EAD 160004-00-0301, Annex C.7 and Clause 3.3.4 on specimens taken from the manufacturing plant or at the manufacturer's storage facility.

Issued in Vienna on 26 June 2025
by Österreichisches Institut für Bautechnik


The original document is signed by

Thomas Rockenschaub
Managing Director


Stressing anchorage, accessible fixed anchorage SA, FA ^{1), 2)}

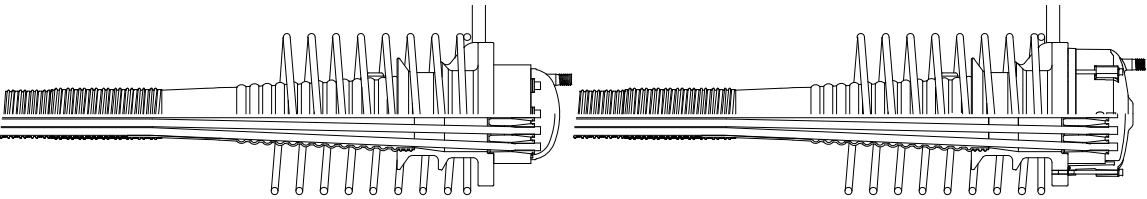


Inaccessible fixed anchorage FA ^{1), 2)}

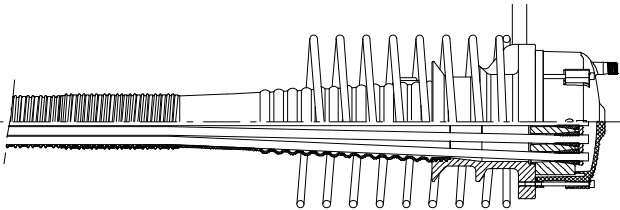


Electrically isolated stressing, electrically isolated accessible fixed anchorage SAE, FAE ¹⁾

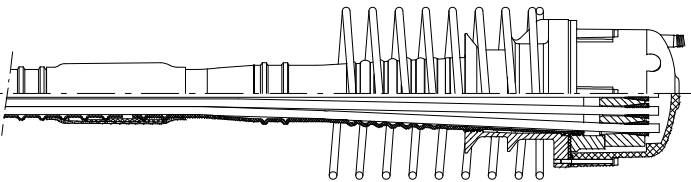

Electrically isolated inaccessible fixed anchorage FAE ¹⁾

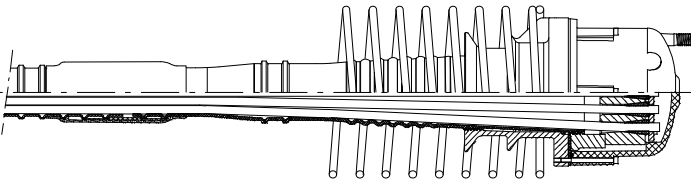


Stressing anchorage nuclear, accessible fixed anchorage nuclear SAN, FAN

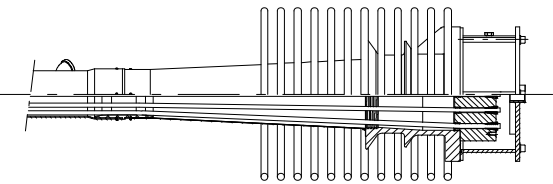


¹⁾ For anchorage sizes up to 5506, either helix or stirrups, or both helix and stirrups can be placed as additional reinforcement.
For anchorage sizes above 5506, 6106, both helix and stirrups shall be placed as additional reinforcement.
²⁾ For anchorages of other than fully encapsulated or electrically isolated tendons, steel caps are available as well.


Fixed and stressing coupler FK, SK ¹⁾

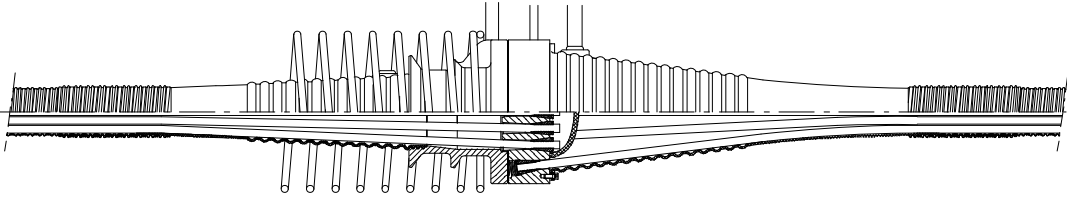


Fixed and stressing coupler FH, SH ¹⁾

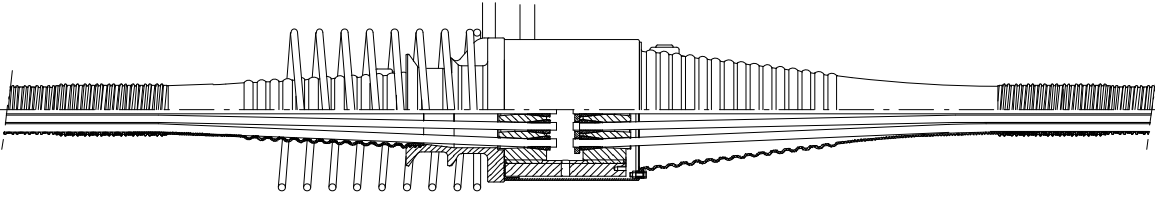

Movable coupler BK

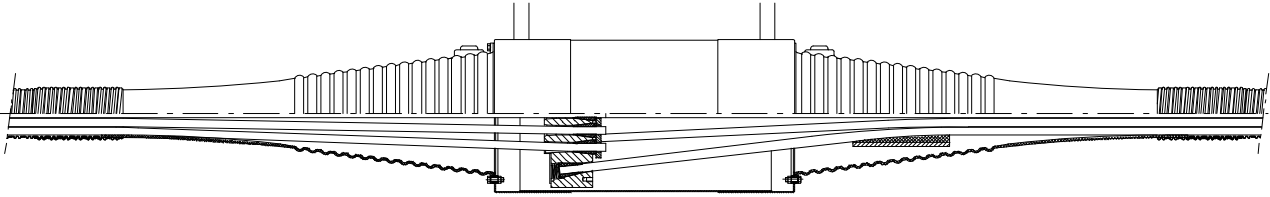


Movable coupler BH

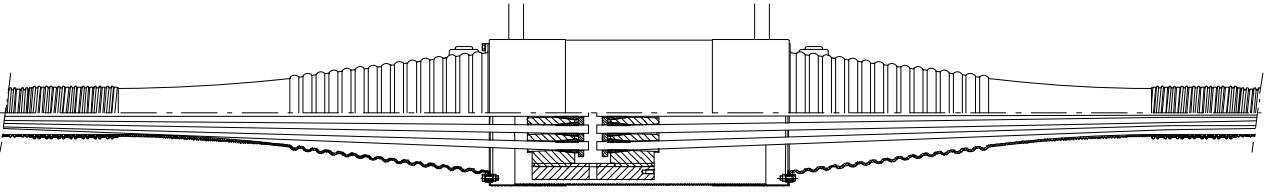


¹⁾ For anchorage sizes up to 5506, either helix or stirrups, or both helix and stirrups can be placed as additional reinforcement.
For anchorage sizes above 5506, 6106, both helix and stirrups shall be placed as additional reinforcement.


Electrically isolated fixed and stressing coupler FKE, SKE ¹⁾

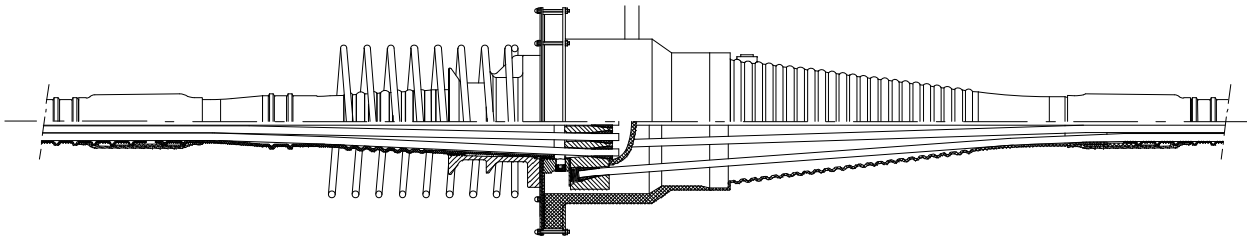


Electrically isolated fixed and stressing coupler FHE, SHE ¹⁾

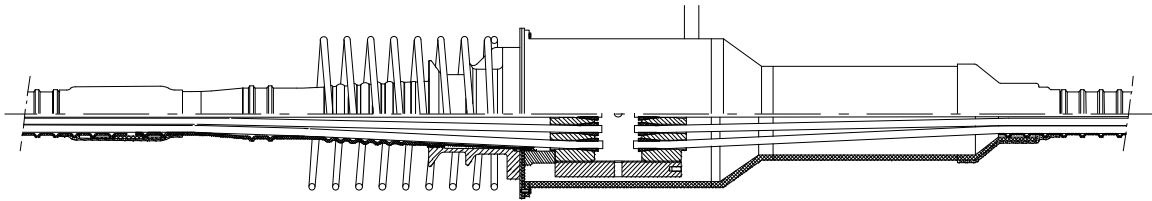

Restressable / exchangeable anchorage with monostrands or grease / wax, SAR ¹⁾

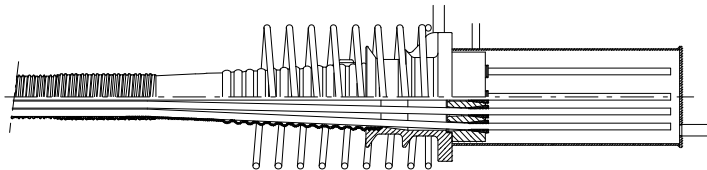


Stressing anchorage, accessible fixed anchorage, replaceable SAR, FAR ^{1), 2)}
With bare strands or monostrands

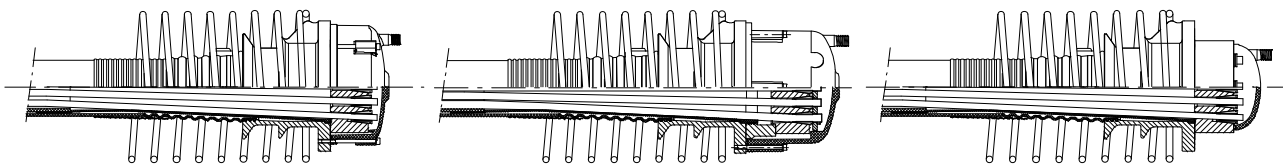


- ¹⁾ For anchorage sizes up to 5506, either helix or stirrups, or both helix and stirrups can be placed as additional reinforcement.
For anchorage sizes above 5506, 6106, both helix and stirrups shall be placed as additional reinforcement.
- ²⁾ For anchorages other than fully encapsulated or electrically isolated tendons, steel caps are available as well.


Stressing anchorage, accessible fixed anchorage FA ¹⁾

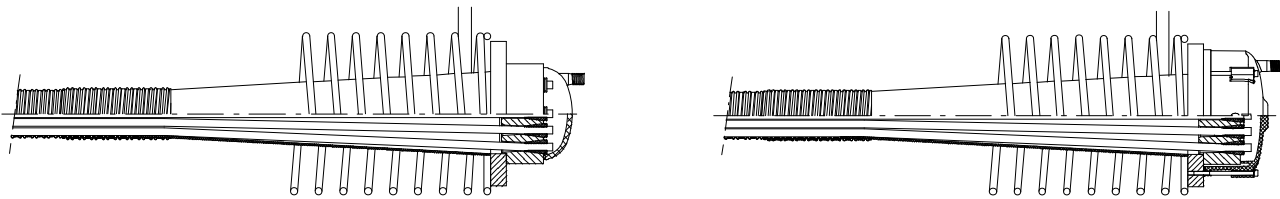


Inaccessible fixed anchorage FA ¹⁾

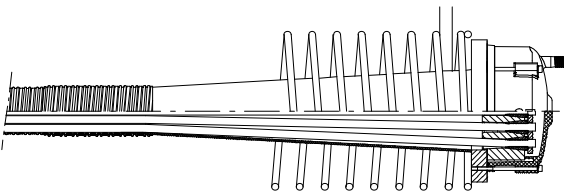


Fixed and stressing coupler FK, SK

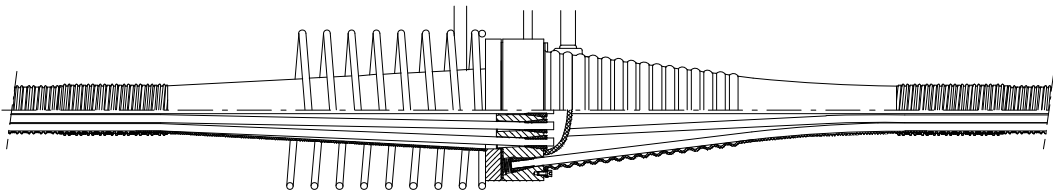


Fixed and stressing coupler FH, SH

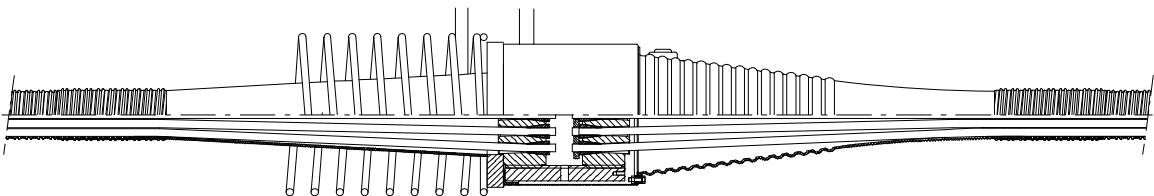


Restressable / exchangeable anchorage

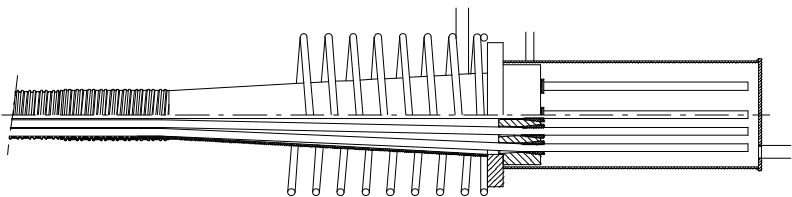

¹⁾ For anchorages other than fully encapsulated or electrically isolated tendons, steel caps are available as well.

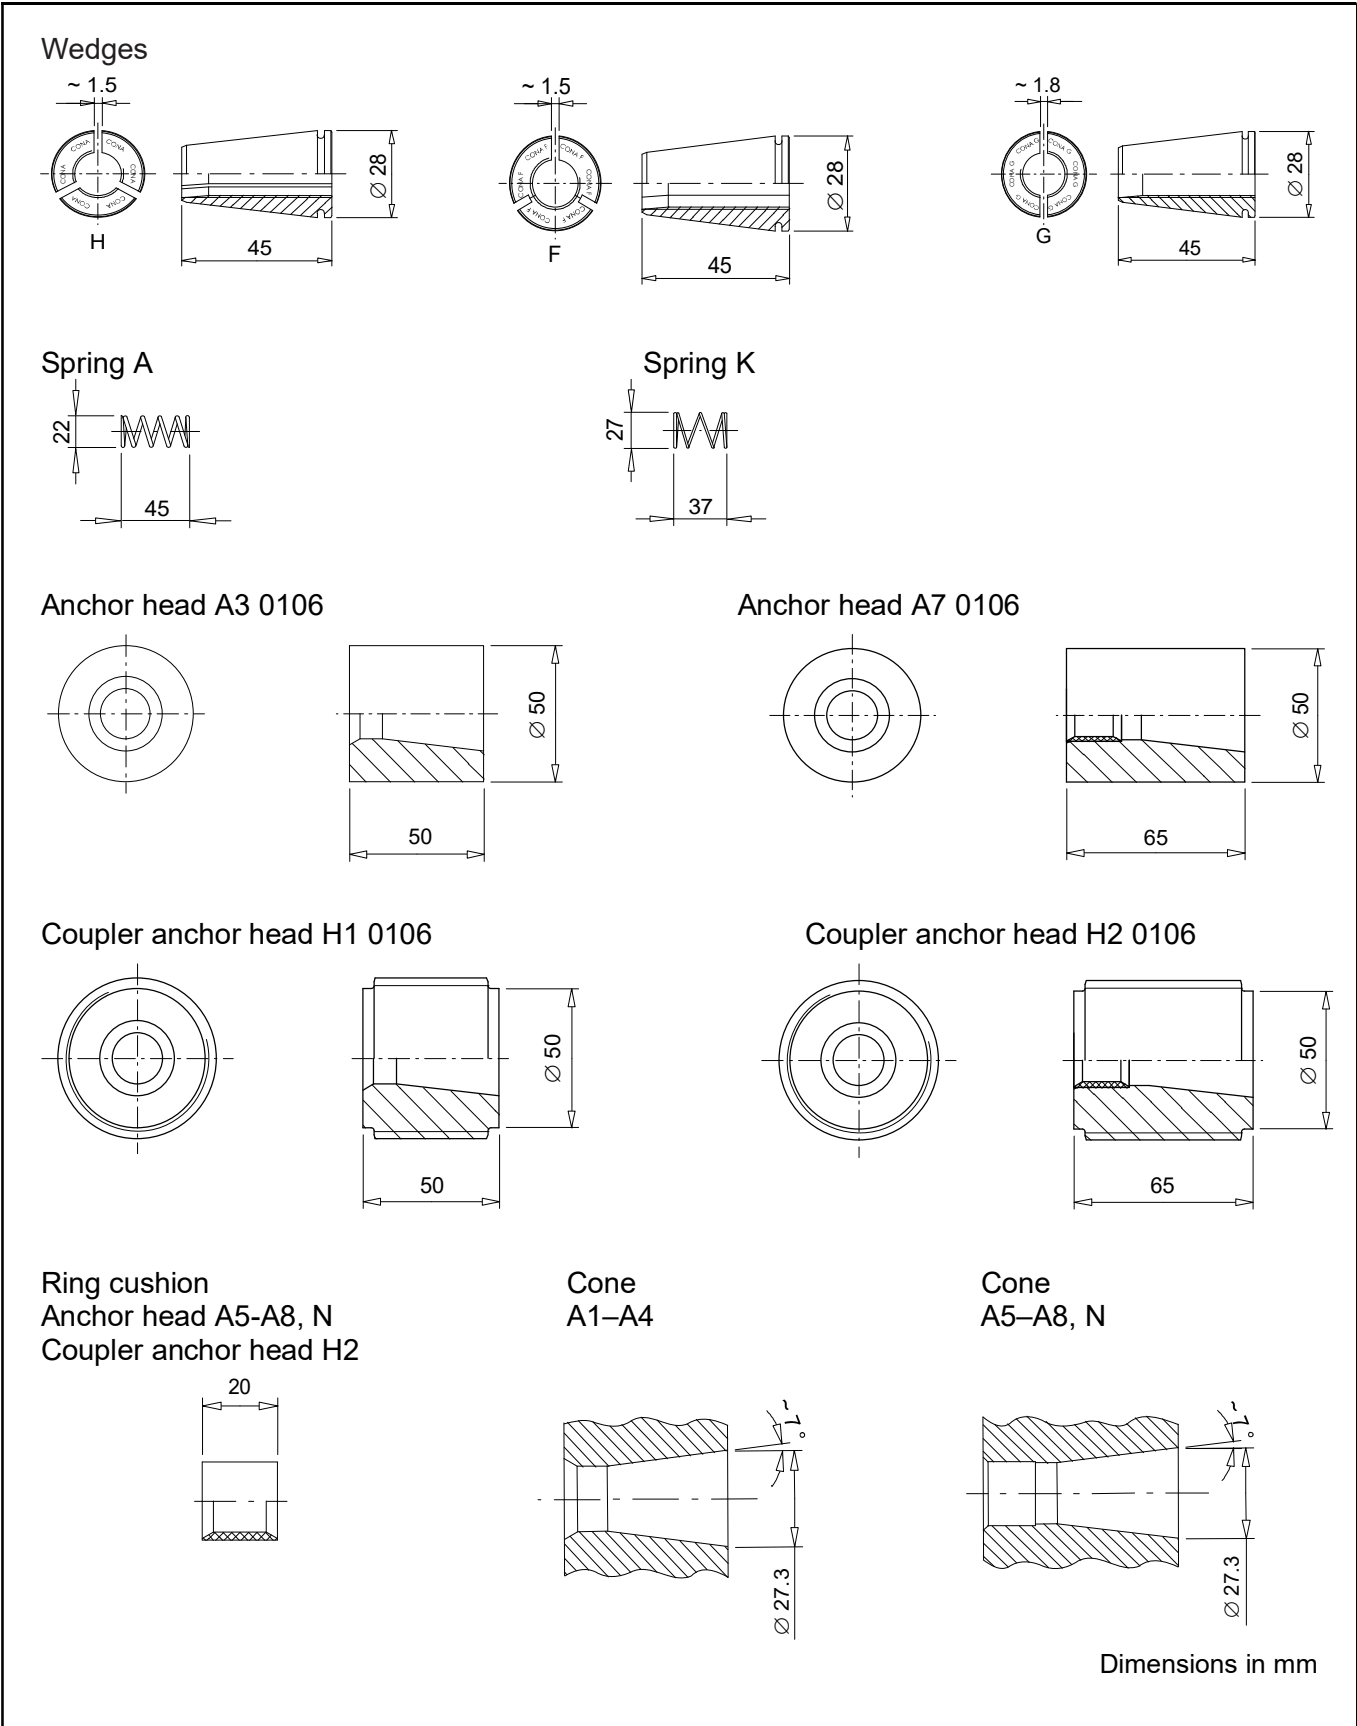

Anchor head A1-A4

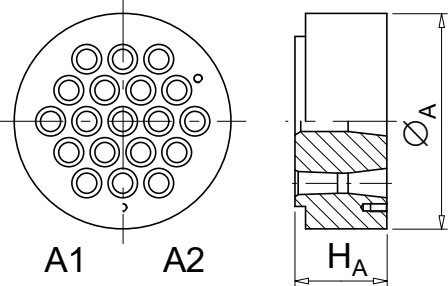


A1

A2

A3

A4

Anchor head A5-A8

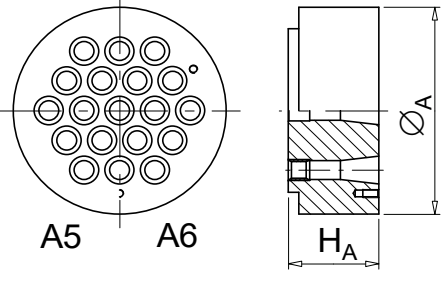

A5


A6

A7

A8

Number of strands		02	03	04	05	06	07	08	09	12	13	15	16	
Anchor head														
Nominal diameter	Ø _A	mm	90	100	100	130	130	130	150	160	160	180	200	200
Height head A1-A4	H _A	mm	50	50	50	50	55	55	60	60	65	72	75	80
Height head A5-A8		mm	65	65	65	65	65	65	65	65	70	72	75	80


Number of strands		19	22	24	25	27	31	37	42	43	48	55	61	
Anchor head														
Nominal diameter	Ø _A	mm	200	225	240	255	255	255	285	300	320	325	335	365
Height head A1-A4	H _A	mm	85	95	100	100	105	110	—	—	—	—	—	—
Height head A5-A8		mm	85	95	100	100	105	110	120	130	130	140	150	155




Internal Post-tensioning System
Components – Anchorage

Annex 6
of European Technical Assessment
ETA-06/0147 of 26.06.2025


Coupler anchor head H1

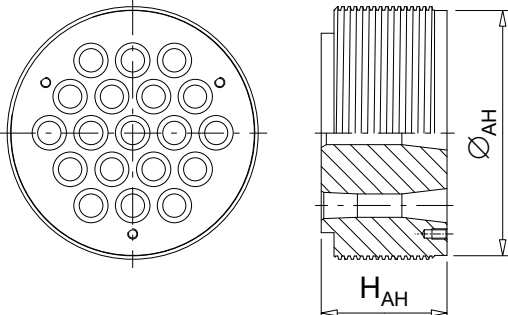

Coupler anchor head H2

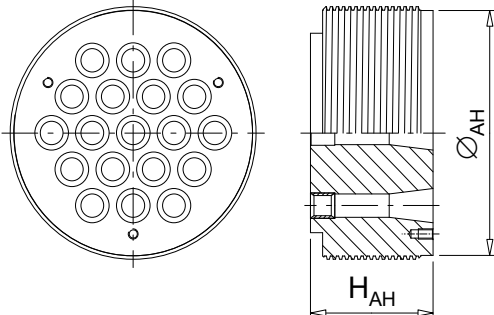


Coupler anchor head K

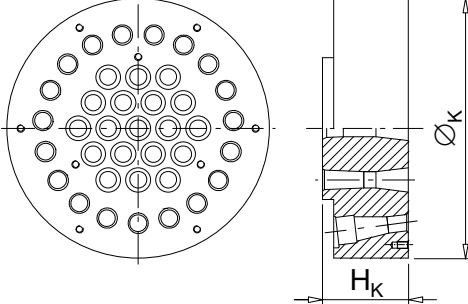

Number of strands		02	03	04	05	06	07	08	09	12	13	15	16
Coupler anchor heads H1 and H2													
Nominal diameter Ø _{AH}	mm	90	95	100	130	130	130	150	160	160	180	200	200
Height head H1	H _{AH}	mm	50	50	55	55	60	65	65	70	80	80	85
Height head H2		mm	65	65	65	65	65	65	65	70	80	80	85
Coupler anchor head K													
Diameter	Ø _K	mm	195	195	195	210	210	210	250	250	250	290	290
Height	H _K	mm	85	85	85	85	85	85	90	90	90	90	95

Number of strands		19	22	24	25	27	31	37	42	43	48	55	61
Coupler anchor heads H1 and H2													
Nominal diameter Ø _{AH}	mm	200	225	240	255	255	255	285	300	320	325	335	365
Height head H1	H _{AH}	mm	95	100	100	100	105	115	—	—	—	—	—
Height head H2		mm	95	100	100	100	105	115	125	135	135	145	160
Coupler anchor head K													
Diameter	Ø _K	mm	290	310	340	390	390	390	—	—	—	—	—
Height	H _K	mm	95	105	120	125	125	130	—	—	—	—	—



Internal Post-tensioning System
Components – Coupler

Annex 7
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Bearing trumplate A

Bearing trumplate E

Square plate ¹⁾





¹⁾ Minimum dimensions see Annex 54 to Annex 62.

Number of strands	02	03	04	05	06	07	08	09	12	13	15	16
Bearing trumplate A												
Diameter Ø _P mm	130	130	130	170	170	170	195	225	225	240	280	280
Height H _P mm	100	100	120	128	128	128	133	150	150	160	195	195
Bearing trumplate E												
Diameter Ø _{BE} mm	145	145	145	170	170	170	—	225	225	—	280	280
Height H _{BE} mm	120	120	120	128	128	128	—	150	150	—	195	195


Number of strands	19	22	24	25	27	31	37	42	43	48	55	61
Bearing trumplate A												
Diameter Ø _P mm	280	310	325	360	360	360	400	425	485	485	485	520
Height H _P mm	195	206	227	250	250	250	275	290	340	340	340	350
Bearing trumplate E												
Diameter Ø _{BE} mm	280	310	325	360	360	360	400	—	—	—	—	—
Height H _{BE} mm	195	206	227	250	250	250	275	—	—	—	—	—

Internal Post-tensioning System
Components – Anchorage and coupler

Annex 8
of European Technical Assessment
ETA-06/0147 of 26.06.2025

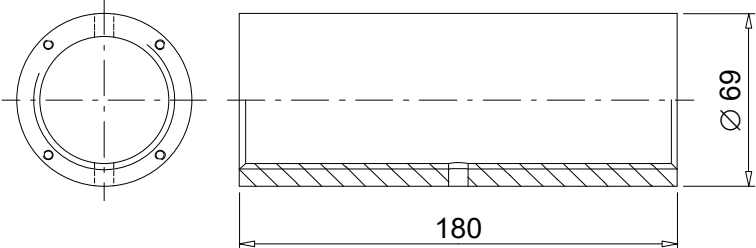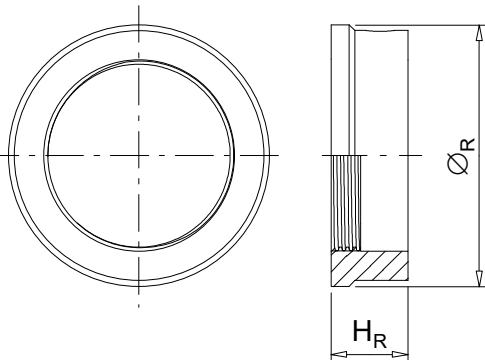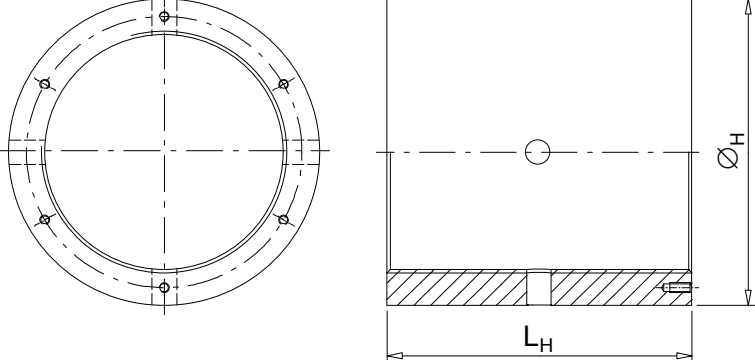
Tension ring		Coupler sleeve H 0106											
													
Steel ring E		Coupler sleeve H											
													
Dimensions in mm													
Number of strands		02	03	04	05	06	07	08	09	12	13	15	16
Coupler sleeve H													
Diameter	Ø _H mm	114	124	133	163	167	170	192	203	213	233	259	259
Length sleeve	L _H mm	180	180	180	180	190	200	200	210	230	230	240	250
Steel ring E													
Diameter	Ø _R mm	100	100	100	130	130	130	—	173	173	—	214	214
Length	H _R mm	59	59	59	59	59	59	—	65	65	—	65	65

Number of strands		19	22	24	25	27	31	37	42	43	48	55	61
Coupler sleeve H													
Diameter	Ø _H mm	269	296	312	327	330	338	373	395	413	425	443	475
Length sleeve	L _H mm	270	270	280	280	300	320	340	360	360	380	410	410
Steel ring E													
Diameter	Ø _R mm	214	238	251	274	274	274	307	—	—	—	—	—
Length	H _R mm	65	65	65	65	65	65	65	—	—	—	—	—




Internal Post-tensioning System
Components – Anchorage and coupler


Annex 9
of European Technical Assessment
ETA-06/0147 of 26.06.2025

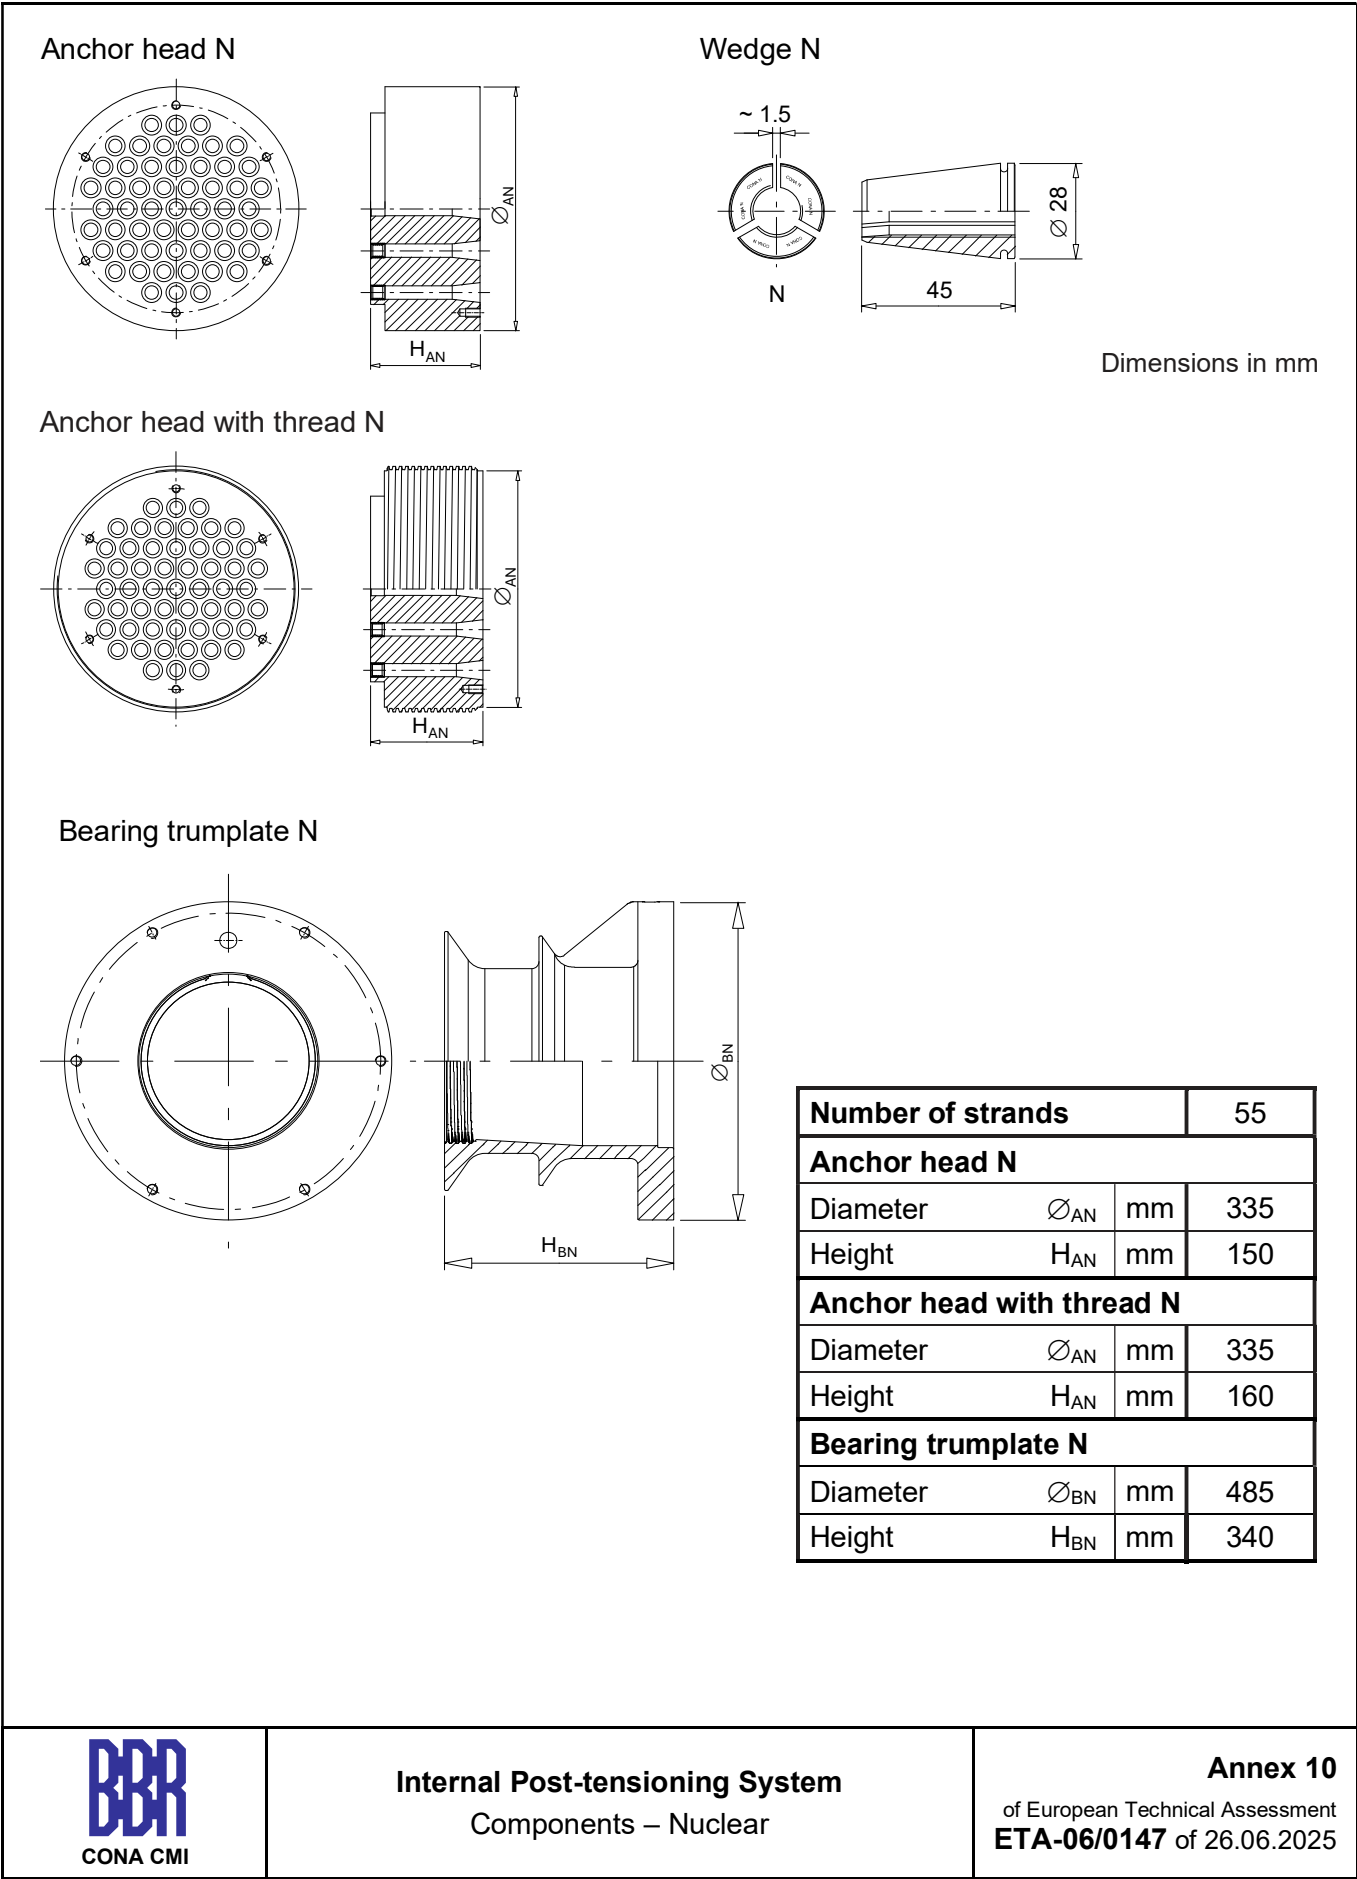


Trumpet N

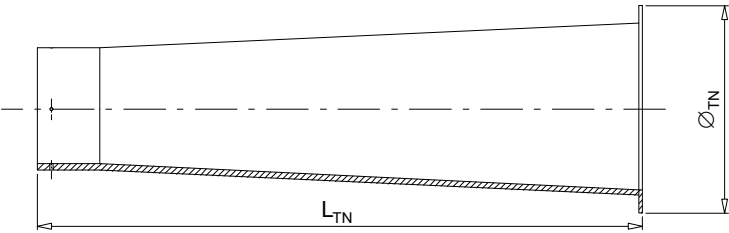

Deviator N

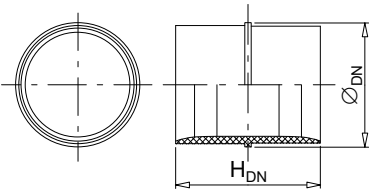


Protection cap N

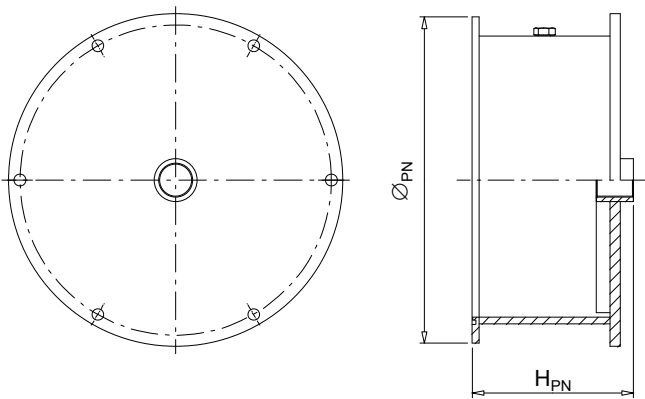


Number of strands			55
Trumpet N			
Diameter	Ø _{TN}	mm	300
Length	L _{TN}	mm	867
Deviator N			
Diameter	Ø _{DN}	mm	180
Length	H _{DN}	mm	210
Protection cap N			
Diameter	Ø _{PN}	mm	485
Height	H _{PN}	mm	≥ 234


Temporary sealing plate

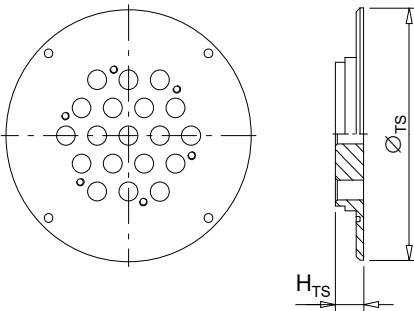

Activation plate

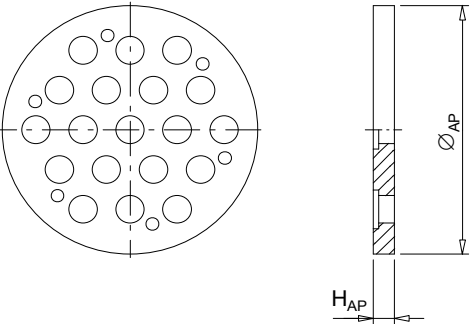

Cover Plate K

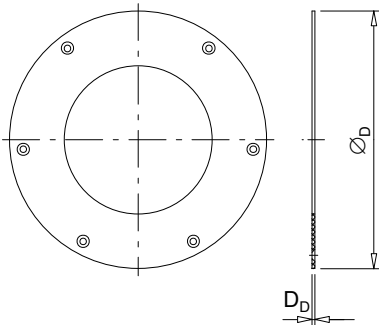

Number of strands			02	03	04	05	06	07	08	09	12	13	15	16
Temporary sealing plate														
Diameter	Ø _{TS}	mm	—	—	129	169	169	169	—	225	225	—	260	260
Height	H _{TS}	mm	—	—	29	29	29	29	—	29	29	—	30	30
Activation plate														
Diameter	Ø _{AP}	mm	—	—	90	120	120	120	—	150	150	—	180	180
Height	H _{AP}	mm	—	—	10	10	10	10	—	15	15	—	15	15
Cover plate K														
Diameter	Ø _D	mm	192	192	192	207	207	207	246	246	246	286	286	286
Thickness	D _D	mm	3	3	3	3	3	3	3	3	3	3	3	3

Number of strands			19	22	24	25	27	31	37	42	43	48	55	61
Temporary sealing plate														
Diameter	Ø _{TS}	mm	260	305	310	350	350	350	360	405	465	465	465	500
Height	H _{TS}	mm	30	30	30	30	30	30	30	35	40	40	40	40
Activation plate														
Diameter	Ø _{AP}	mm	180	200	220	220	220	220	250	280	300	300	315	345
Height	H _{AP}	mm	15	15	15	15	15	15	15	15	15	15	15	15
Cover plate K														
Diameter	Ø _D	mm	286	306	336	386	386	386	—	—	—	—	—	—
Thickness	D _D	mm	3	5	5	5	5	5	—	—	—	—	—	—

Wedge retaining plate H

Wedge retaining plate A, E, and N

Isolation ring E

Isolation ring E with steps


Number of strands		02	03	04	05	06	07	08	09	12	13	15	16
Wedge retaining plate H													
Diameter	Ø _H mm	65	73	91	117	117	117	130	157	157	145	185	185
Thickness	D _H mm	30	30	30	30	30	30	30	30	30	30	30	30
Wedge retaining plate A, E, and N													
Diameter	Ø _A mm	65	73	91	117	117	117	130	157	157	145	185	185
Thickness	D _A mm	5	5	5	5	5	5	8	8	8	10	10	10

Number of strands		19	22	24	25	27	31	37	42	43	48	55	61
Wedge retaining plate H													
Diameter	Ø _H mm	185	205	232	234	234	234	240	275	275	275	310	310
Thickness	D _H mm	30	30	30	30	30	30	30	30	30	30	30	30
Wedge retaining plate A, E, and N													
Diameter	Ø _A mm	185	205	232	234	234	234	240	275	275	275	310	310
Thickness	D _A mm	10	10	10	10	10	10	12	12	12	12	12	12


Internal Post-tensioning System
Components – Accessory

Annex 13
of European Technical Assessment
ETA-06/0147 of 26.06.2025


Grouting Cap A

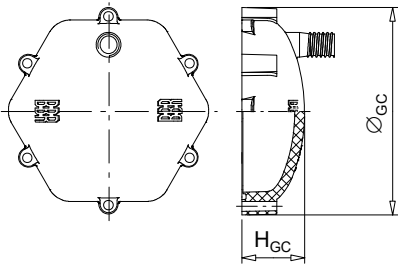

Protection Cap A

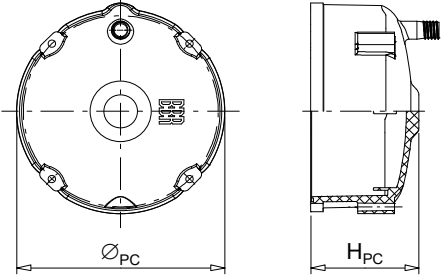

Protection cap E

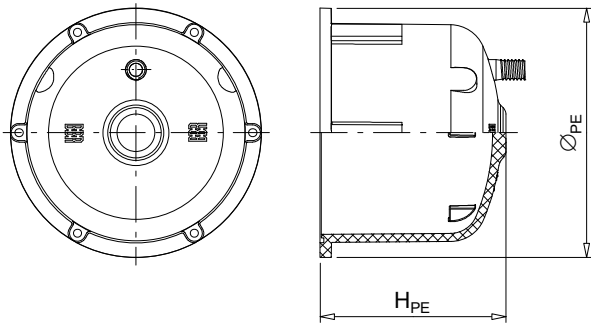

Number of strands			02	03	04	05	06	07	08	09	12	13	15	16
Grouting Cap A														
Diameter	Ø _{GC}	mm	—	—	98	118	118	118	—	158	158	—	188	188
Height	H _{GC}	mm	—	—	52	53	53	53	—	58	58	—	58	58
Protection Cap A														
Diameter	Ø _{PC}	mm	—	—	116	170	170	170	—	218	218	—	257	257
Height	H _{PC}	mm	—	—	98	110	110	110	—	114	114	—	133	133
Protection Cap E														
Diameter	Ø _{PE}	mm	143	143	143	168	168	168	—	229	229	—	276	276
Height	H _{PE}	mm	167	167	167	174	174	174	—	185	185	—	205	205

Number of strands			19	22	24	25	27	31	37	42	43	48	55	61
Grouting Cap A														
Diameter	Ø _{GC}	mm	188	204	234	242	242	242	—	—	—	—	—	—
Height	H _{GC}	mm	58	60	68	68	68	68	—	—	—	—	—	—
Protection Cap A														
Diameter	Ø _{PC}	mm	257	277	277	320	320	320	360	380	400	400	400	400
Height	H _{PC}	mm	133	144	144	162	162	162	175	190	190	200	210	210
Protection Cap E														
Diameter	Ø _{PE}	mm	276	306	316	348	348	348	375	—	—	—	—	—
Height	H _{PE}	mm	205	217	223	233	233	233	253	—	—	—	—	—




Internal Post-tensioning System
Components – Accessory


Annex 14
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Half-shell


Round ID 50, ID 60, ID 75

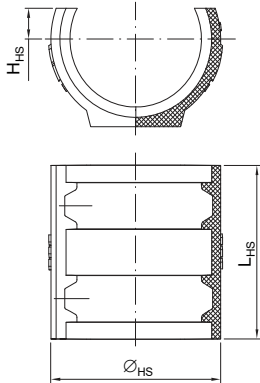


Round ID 85, ID 100, ID 115,
ID130, ID 145

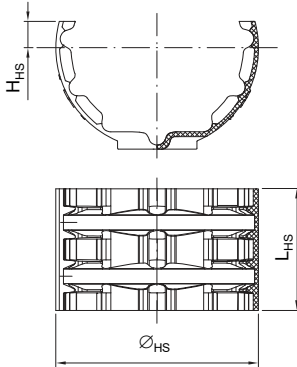


Flat

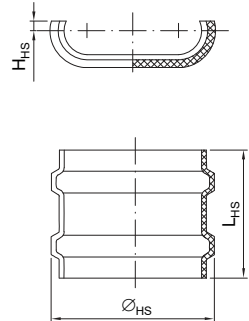


Male grouting adaptor 3/4 " to 23 mm



Female grouting adaptor 23 mm to 3/4 "



Plug 3/4 "



Shape			Flat				
Plastic duct							
Number of strands	—		02	03	04	04	05
Designation	—		22 × 38	21 × 52	21 × 72	25 × 76	21 × 90
Half-shell							
Height	H _{HS}	mm	6	6	6	6	6
Width	Ø _{HS}	mm	58.5	72.5	91.5	96.5	109
Length	L _{HS}	mm	80	80	80	80	80


Shape			Round						
Plastic duct									
Number of strands	mm	02–05	06–07	08–12	13–15	16–19	20–27	28–37	
Designation	mm	50	60	75	85	100	115	130	
Half-shell									
Height	H _{HS}	mm	9	13	13	14	15	15	20
Width	Ø _{HS}	mm	62.0	75.5	93.0	102.5	118.0	138.0	153.0
Length	L _{HS}	mm	85	85	100	79	79	79	92




Internal Post-tensioning System
Components – Accessory

Annex 15
of European Technical Assessment
ETA-06/0147 of 26.06.2025


Trumpet F

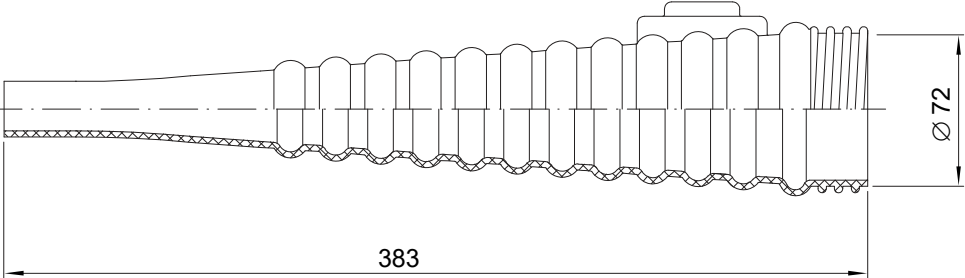

Trumpet A

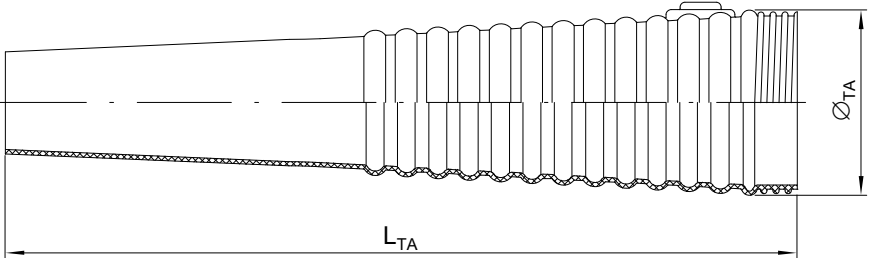

Trumpet K

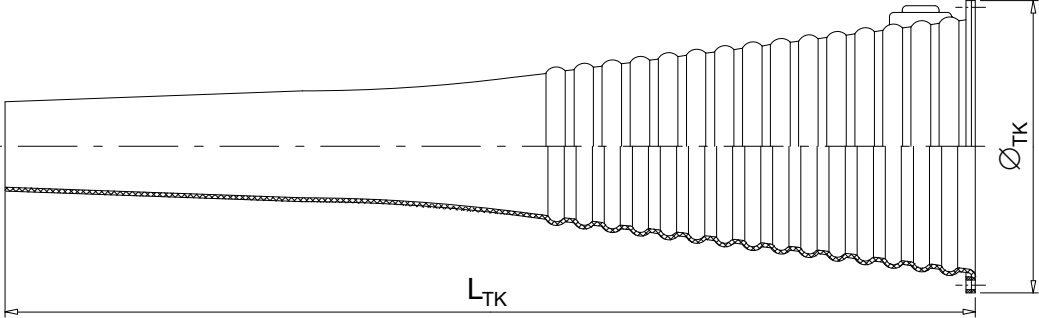

Dimensions in mm

Number of strands			02	03	04	05	06	07	08	09	12	13	15	16
Trumpet A														
Diameter	Ø _{TA}	mm	72	72	72	88	88	88	127	127	127	153	153	153
Length	L _{TA}	mm	197	197	197	325	325	325	618	618	503	689	689	689
Trumpet K														
Diameter	Ø _{TK}	mm	185	185	185	203	203	203	240	240	240	275	275	275
Length	L _{TK}	mm	470	470	470	640	640	640	845	845	730	890	890	890


Number of strands			19	22	24	25	27	31	37	42	43	48	55	61
Trumpet A														
Diameter	Ø _{TA}	mm	153	170	191	191	191	191	219	229	254	254	254	278
Length	L _{TA}	mm	574	710	866	866	866	751	1 060	1 060	1 244	1 244	1 244	1 290
Trumpet K														
Diameter	Ø _{TK}	mm	275	305	330	375	375	375	—	—	—	—	—	—
Length	L _{TK}	mm	775	840	1 090	1 265	1 265	1 150	—	—	—	—	—	—




Internal Post-tensioning System
Components – Trumpet

Annex 16
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Inner trumpet E

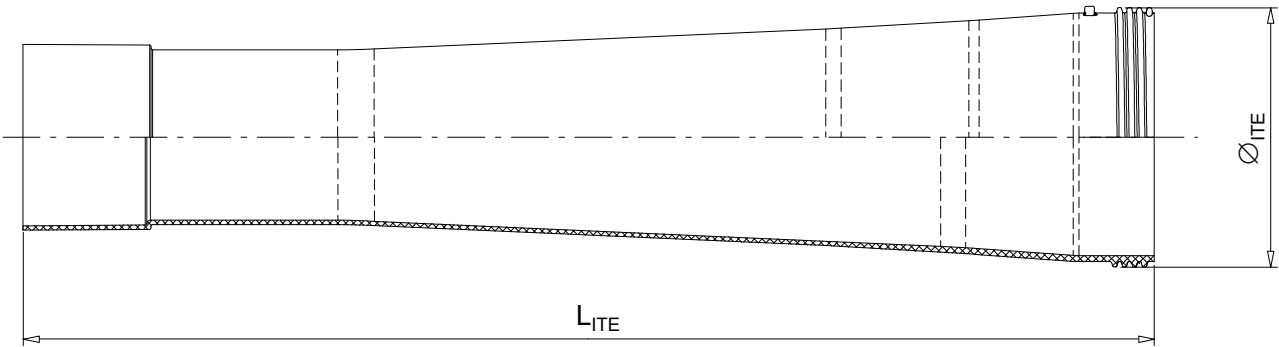


Inner trumpet A

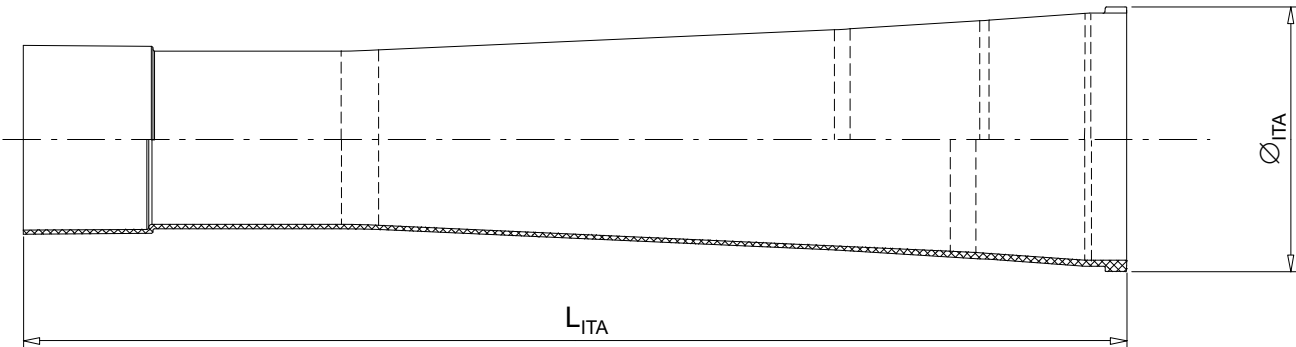


Number of strands		02	03	04	05	06	07	08	09	12	13	15	16
Inner trumpet A													
Diameter	Ø _{ITA} mm	—	—	69	89	89	89	—	128	128	—	158	158
Length	L _{ITA} mm	—	—	190	220	220	220	—	533	533	—	649	648
Inner trumpet E													
Diameter	Ø _{ITE} mm	—	—	74	93	93	93	—	128	128	—	156	156
Length	L _{ITE} mm	—	—	220	250	250	250	—	568	568	—	684	684

Number of strands		19	22	24	25	27	31	37	42	43	48	55	61
Inner trumpet A													
Diameter	Ø _{ITA} mm	158	178	194	202	202	202	224	238	264	264	264	296
Length	L _{ITA} mm	648	600	630	630	630	630	1 020	980	1 170	995	1 070	1 160
Inner trumpet E													
Diameter	Ø _{ITE} mm	156	178	191	201	201	201	—	—	—	—	—	—
Length	L _{ITE} mm	684	635	665	665	665	665	—	—	—	—	—	—


Plastic trumpet A SP 0206–3106

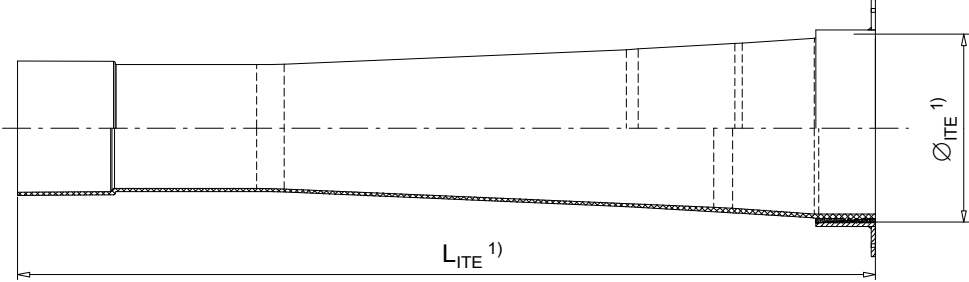

Steel trumpet A SP 0206–6106

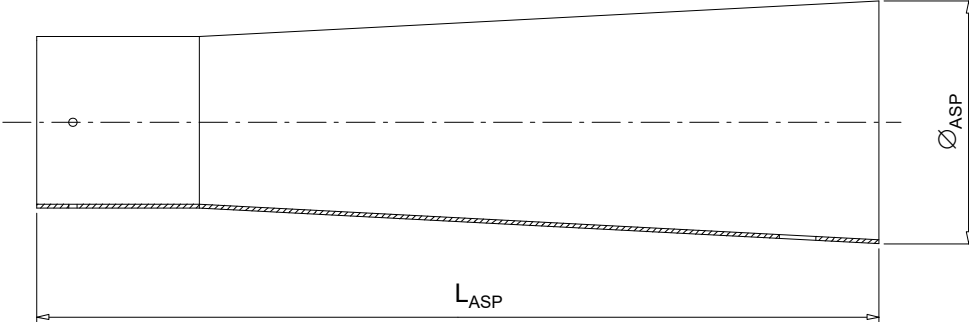

Trumpet E

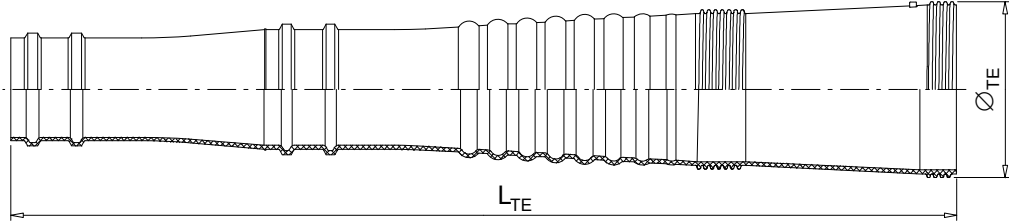

Number of strands			02	03	04	05	06	07	08	09	12	13	15	16
Trumpet A SP														
Diameter	Ø _{ASP}	mm	74	74	74	94	94	94	116	131	131	146	164	164
Length	L _{ASP}	mm	194	264	232	393	330	273	519	679	565	658	799	799
Trumpet E														
Diameter	Ø _{TE}	mm	74	74	74	93	93	93	—	128	128	—	157	157
Height	L _{TE}	mm	312	312	312	428	428	428	—	600	600	—	848	848

Number of strands			19	22	24	25	27	31	37	42	43	48	55	61
Trumpet A SP														
Diameter	Ø _{ASP}	mm	164	184	199	209	209	209	229	243	269	269	269	301
Length	L _{ASP}	mm	680	839	941	989	989	875	1 020	1 068	1 258	1 180	1 126	1 369
Trumpet E														
Diameter	Ø _{TE}	mm	157	178	191	201	201	201	220	—	—	—	—	—
Height	L _{TE}	mm	848	980	1 005	1 040	1 040	1 040	1 200	—	—	—	—	—


¹⁾ See Annex 17.



Internal Post-tensioning System
Components – Trumpet

Annex 18
of European Technical Assessment
ETA-06/0147 of 26.06.2025


BBR VT Plastic Duct – Circular duct – 0206–3706

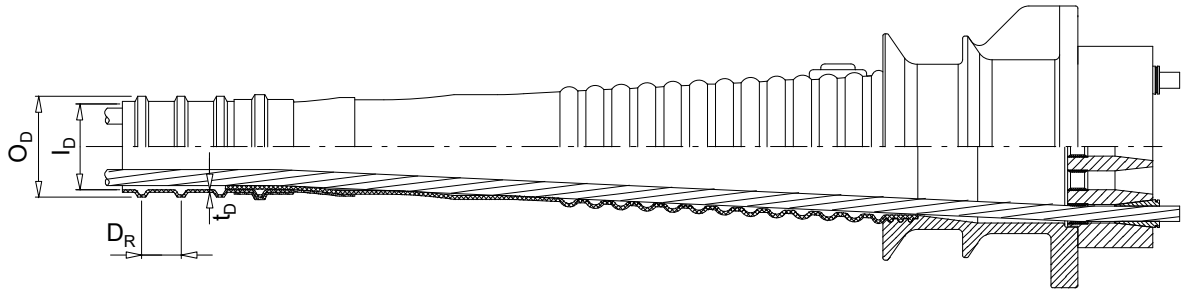

Number of strands n06		02–05	06–07	08–12	13–15	16–19	22–27	31–37
Designation	—	50	60	75	85	100	115	130
Inner diameter	l_D mm	47.5	58.5	76.0	85.0	100.0	115.0	127.0
Outer diameter	O_D mm	58.5	72.5	91.0	100.0	116.0	131.0	150.0
Distance ribs	D_R mm	28.0	38.5	39.0	39.0	39.5	60.0	40.5
Minimum thickness	t_D mm	2.0	2.0	2.5	2.5	3.0	3.5	4.0

NOTE Dimensions rounded to the nearest 0.5 mm.

BBR VT Plastic Duct – Coupler for circular duct – 0206–3706

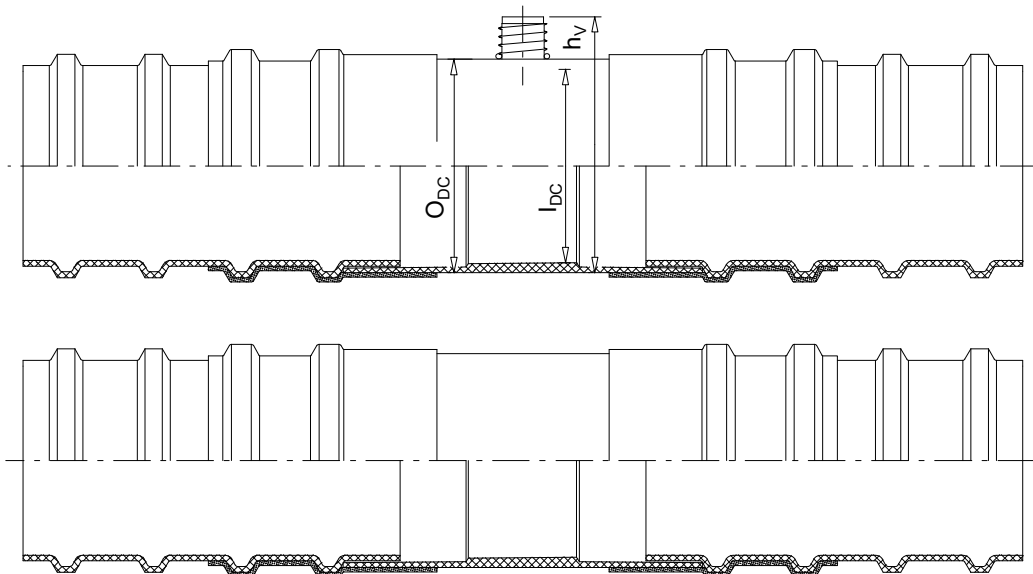

Number of strands n06		02–05	06–07	08–12	13–15	16–19	22–27	31–37
Inner diameter coupler	l_{DC} mm	56.0	69.0	87.0	96.0	112.0	130.5	143.5
Outer diameter coupler	O_{DC} mm	64.0	78.0	96.0	108.0	125.0	142.0	158.0
Vent height	h_v mm	81.5	95.5	114.0	126.0	137.5	154.5	175.0


NOTE Dimensions rounded to the nearest 0.5 mm.



Internal Post-tensioning System
Plastic duct
Circular duct 0206–3706

Annex 19
of European Technical Assessment
ETA-06/0147 of 26.06.2025


BBR VT Plastic Duct – Flat duct

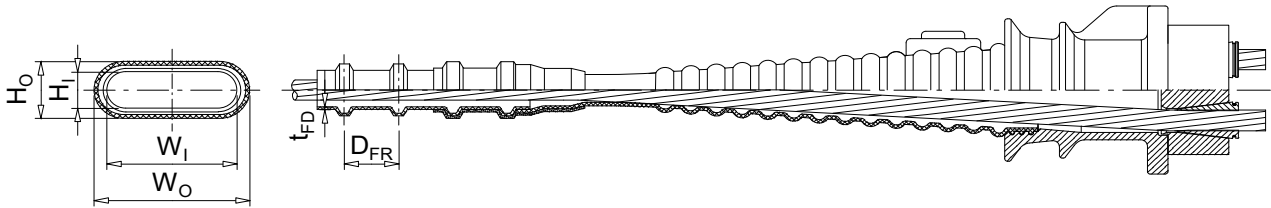

Number of strands n06			02	03	04	04	05
Designation	—		22 × 38	21 × 52	21 × 72	25 × 76	21 × 90
Height, inner dimension	H _I	mm	21.5	21.0	21.0	25.0	20.0
Height, outer dimension	H _O	mm	34.0	35.0	36.0	39.0	35.0
Width, inner dimension	W _I	mm	37.5	52.0	72.0	76.0	94.0
Width, outer dimension	W _O	mm	52.0	66.0	85.5	90.0	104.5
Distance ribs	D _{FR}	mm	40.0	40.0	40.0	40.0	40.5
Minimum thickness	t _{FD}	mm	2.0	2.0	2.0	2.0	2.0

NOTE Dimensions rounded to the nearest 0.5 mm.

BBR VT Plastic Duct – Coupler flat duct – 0406

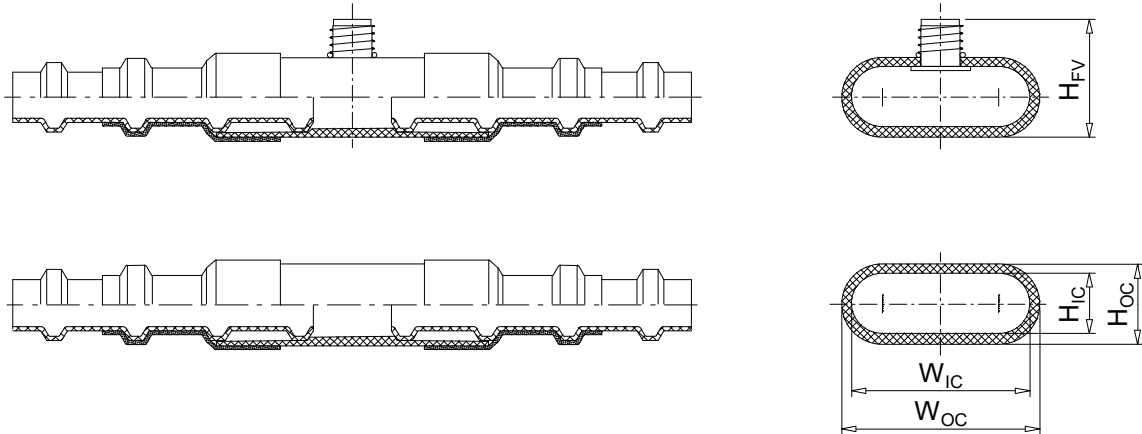

Number of strands n06			02	03	04	04	05
Designation	—		22 × 38	21 × 52	21 × 72	25 × 76	21 × 90
Height, inner dimension	H _{IC}	mm	35.0	35.5	30.5	35.0	37.0
Height, outer dimension	H _{OC}	mm	41.0	39.5	42.5	43.0	42.0
Width, inner dimension	W _{IC}	mm	54.0	67.5	81.5	85.5	105.0
Width, outer dimension	W _{OC}	mm	60.0	71.5	92.5	93.0	111.0
Vent height	H _{FV}	mm	60.0	58.5	59.0	62.5	60.5

NOTE Dimensions rounded to the nearest 0.5 mm.




Internal Post-tensioning System
Plastic duct
Flat duct 0206–0506

Annex 20
of European Technical Assessment
ETA-06/0147 of 26.06.2025

electronic copy electronic copy electronic copy electronic copy electronic copy electronic copy electronic copy electronic copy electronic copy electronic copy

Precast segmental coupler

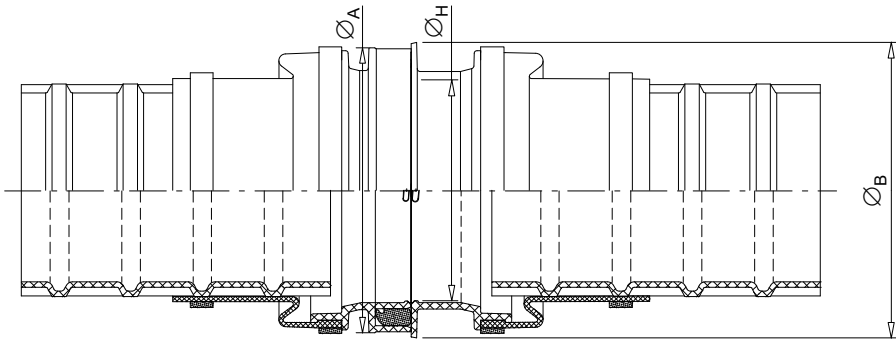

Number of strands n06			02–05	06–07	08–12	13–15	16–19	22–27	31–37
Designation	—		76	76	76	85	100	115	130
Outer diameter	Ø _A	mm	129.5	129.5	129.5	140.0	155.5	174.0	190.5
Outer diameter coupler	Ø _B	mm	135.0	135.0	135.0	145.5	161.0	180.0	196.5
Inner diameter coupler	Ø _H	mm	96.5	96.5	96.5	107.0	122.5	141.0	157.5

NOTE Dimensions rounded to the nearest 0.5 mm.

Material specifications

Component	Standard / Specification
Anchor head A, A CONA CMI 0106 to 6106 Anchor head N, N CONA CMI 5506	EN ISO 683-1 EN ISO 683-2
Coupler anchor head K, K CONA CMI 0206 to 3106 Coupler anchor head H, H CONA CMI 0106 to 6106	EN ISO 683-1 EN ISO 683-2
Bearing trumplate A, CONA CMI 0206 to 6106 Bearing trumplate E, CONA CMI 0206 to 3706 Bearing trumplate N, CONA CMI 5506	EN 1561 EN 1563
Square plate CONA CMI SP 0106 to 6106	EN 10025-2
Coupler sleeve H, H CONA CMI 0106 to 6106	EN 10210-1
Ring wedge H, F, G, and N	EN ISO 683-3 EN ISO 683-7
Ring cushion	EN ISO 17855-1 EN ISO 19069-1
Wedge retaining plate A, E, H, and N, CONA CMI 0206 to 6106 Cover plate K CONA CMI 0206 to 3106	EN 10025-2
Trumpet A, A SP, K, E, and F Inner trumpet A and E Deviator N	EN ISO 17855-1 EN ISO 19069-1
Trumpet A, A SP, K, N	EN 10025-2
Steel ring E	EN 10210-1
Temporary sealing plate Activation plate	EN 10025-2
Isolation ring E	Composite material
Steel cushion plate	EN 10025-2
Grouting cap A Protection cap A Protection cap E Grouting adaptor Plug Half shell	EN ISO 17855-1
Protection cap A Protection cap N	EN 10025-2
Tension ring	EN 10210-1
Spring A and K	EN 10270-1
Helix	Ribbed reinforcing steel, $R_e \geq 500$ MPa
Additional stirrup reinforcement	Ribbed reinforcing steel, $R_e \geq 500$ MPa
Steel strip sheath	EN 523
Steel duct	EN 10255, EN 10216-1, EN 10217-1, EN 10219-1, EN 10305-3
BBR VT Plastic Duct and coupler Precast segmental coupler	Polypropylene (PP) according to Annex 23



Internal Post-tensioning System
Material specifications

Annex 22
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Material properties of plastic duct for PL1, PL2, and PL3

Essential characteristic	Testing	Product performance
Oxidation Induction Time (OIT) at 200 °C	Duct, ASTM D 3895	≥ 25 minutes
Slow-Crack-Growth Resistance	Duct, ASTM F 2136	≥ 25 hours
Notched impact 23 °C 0 °C	Compound, ASTM D 256	≥ 300 J/m ≥ 50 J/m
Melt Flow Rate (MFR) at 230 °C	Compound, Duct, ASTM D 1238	0.3–10 g/10 min
Density	Duct, ASTM D 1505	0.89–0.91 g/cm ³
Flexural Modulus	Compound, ASTM D 790	≥ 750 MPa
Tensile Yield Strength	Compound, ASTM D 638	≥ 20 MPa
Elongation at yield and at break	Compound, ASTM D 638	≥ 5.0 % ≥ 50 %
Thermal expansion coefficient	Compound, ASTM D 696	≤ 125 · 10 ⁻⁶

NOTE For ASTM standards see *fib* bulletin 75.


Component performance of plastic duct for PL1, PL2, and PL3

Essential characteristic	Product performance			
Dimensional requirements	See Annex 19 and Annex 20 Dimensional tolerances according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met.			
Stiffness of duct	See Annex 26			
Longitudinal load resistance of duct system	≥ 10 minutes			
Lateral load resistance of duct	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met.			
Flexibility of duct system	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met.			
Leak tightness of duct system	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met.			
Concrete pressure test on duct	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met.			
Wear resistance of duct	The residual wall thickness after testing is PL1 ≥ 1.0 mm PL2, PL3 ≥ 1.5 mm			
Wear resistance of duct under sustained load	The residual wall thickness after testing is PL1 ≥ 0.5 mm PL2, PL3 ≥ 1.0 mm			
Bond behaviour of duct	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met for			
	Designation	n06 ¹⁾	Designation	n06 ¹⁾
	22 × 38	02	60	07
	21 × 52	03	75	12
	21 × 72	04	85	15
	25 × 76	04	100	19
	21 × 90	05	115	27
	50	05	130	37
Precast segmental duct coupler system where applicable	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.10, 2.2.11, and 2.2.12 are met.			
Fracture resistance of duct system	Characteristic not assessed.			

¹⁾ Maximum number of strands Y1860S7, nominal diameter 15.7 mm

System performance of plastic duct for PL1, PL2, and PL3	
Essential characteristic	Product performance
Leak tightness of anchorage-duct assembly	No leakage with positive and negative pressure for 30 minutes
Full scale duct assembly	Acceptance criteria according to EAD 160004-00-0301, Clauses 2.2.11 and 2.2.12 are met.
Leak tightness of assembled duct system	—
EIT performance of the duct system	Electrical resistance ¹⁾ Duct ≥ 2 000 kΩ Duct with coupler ≥ 2 000 kΩ Duct with coupler and vent ≥ 2 000 kΩ Capacitance ¹⁾ ≤ 3.5 nF Loss factor ¹⁾ ≤ 0.2
EIT performance of anchorage-duct assembly	≥ 15 kΩ

¹⁾ Length of duct immersed in water 1.0 m

	Internal Post-tensioning System BBR VT Plastic Duct – Performance of plastic duct	Annex 25 of European Technical Assessment ETA-06/0147 of 26.06.2025
---	---	---

Stiffness of plastic duct

BBR VT Plastic Duct Designation	(E · I) _{eff} in Nm ²	
	at 23 °C	at 45 °C
22 × 38	3.8	2.9
21 × 52	5.0	3.3
21 × 72	4.6	3.3
25 × 76	10.0	8.8
21 × 90	11.7	13.3
50	54.4	47.7
60	29.6	25.4
75	105	81.3
85	116	98.5
100	348	300
115	339	296
130	427	407

7-wire prestressing steel strands according to prEN 10138-3 ¹⁾

Steel designation			Y1770S7	Y1860S7	Y1770S7	Y1860S7
Tensile strength	R _m	MPa	1 770	1 860	1 770	1 860
Diameter	d	mm	15.3	15.3	15.7	15.7
Nominal cross-sectional area	A _p	mm ²	140	140	150	150
Nominal mass per metre	m	kg/m	1.093		1.172	
Permitted deviation from nominal mass		%	± 2			
Characteristic value of maximum force	F _{pk}	kN	248	260	266	279
Maximum value of maximum force	F _{m, max}	kN	285	299	306	321
Characteristic value of 0.1 % proof force ²⁾	F _{p0.1}	kN	218	229	234	246
Minimum elongation at maximum force, L ₀ ≥ 500 mm	A _{gt}	%	3.5			
Modulus of elasticity	E _p	MPa	195 000 ³⁾			

1) Suitable prestressing steel strands according to standards and regulations in force at the place of use may also be used.

2) For prestressing steel strands according to prEN 10138-3, 09.2000, the value is multiplied by 0.98.

3) Standard value

CONA CMI n06-140

Number of strands	Nominal cross-sectional area of prestressing steel	Nominal mass of prestressing steel	Characteristic value of maximum force of tendon	
			$f_{pk} = 1\,770\text{ MPa}$	$f_{pk} = 1\,860\text{ MPa}$
n	A_p	M	F_{pk}	F_{pk}
—	mm ²	kg/m	kN	kN
01	140	1.1	248	260
02	280	2.2	496	520
03	420	3.3	744	780
04	560	4.4	992	1 040
05	700	5.5	1 240	1 300
06	840	6.6	1 488	1 560
07	980	7.7	1 736	1 820
08	1 120	8.7	1 984	2 080
09	1 260	9.8	2 232	2 340
12	1 680	13.1	2 976	3 120
13	1 820	14.2	3 224	3 380
15	2 100	16.4	3 720	3 900
16	2 240	17.5	3 968	4 160
19	2 660	20.8	4 712	4 940
22	3 080	24.0	5 456	5 720
24	3 360	26.2	5 952	6 240
25	3 500	27.3	6 200	6 500
27	3 780	29.5	6 696	7 020
31	4 340	33.9	7 688	8 060
37	5 180	40.4	9 176	9 620
42	5 880	45.9	10 416	10 920
43	6 020	47.0	10 664	11 180
48	6 720	52.5	11 904	12 480
55	7 700	60.1	13 640	14 300
61	8 540	66.7	15 128	15 860



Internal Post-tensioning System
Tendon ranges

Annex 28
of European Technical Assessment
ETA-06/0147 of 26.06.2025

CONA CMI n06-150

Number of strands	Nominal cross-sectional area of prestressing steel	Nominal mass of prestressing steel	Characteristic value of maximum force of tendon	
			$f_{pk} = 1\,770\text{ MPa}$	$f_{pk} = 1\,860\text{ MPa}$
n	A_p	M	F_{pk}	F_{pk}
—	mm ²	kg/m	kN	kN
01	150	1.2	266	279
02	300	2.3	532	558
03	450	3.5	798	837
04	600	4.7	1 064	1 116
05	750	5.9	1 330	1 395
06	900	7.0	1 596	1 674
07	1 050	8.2	1 862	1 953
08	1 200	9.4	2 128	2 232
09	1 350	10.5	2 394	2 511
12	1 800	14.1	3 192	3 348
13	1 950	15.2	3 458	3 627
15	2 250	17.6	3 990	4 185
16	2 400	18.8	4 256	4 464
19	2 850	22.3	5 054	5 301
22	3 300	25.8	5 852	6 138
24	3 600	28.1	6 384	6 696
25	3 750	29.3	6 650	6 975
27	4 050	31.6	7 182	7 533
31	4 650	36.3	8 246	8 649
37	5 550	43.4	9 842	10 323
42	6 300	49.2	11 172	11 718
43	6 450	50.4	11 438	11 997
48	7 200	56.3	12 768	13 392
55	8 250	64.5	14 630	15 345
61	9 150	71.5	16 226	17 019



Internal Post-tensioning System
Tendon ranges

Annex 29
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Maximum prestressing and overstressing forces

		Maximum prestressing force ¹⁾ 0.9 · F _{p0.1}				Maximum overstressing force ^{1), 2)} 0.95 · F _{p0.1}			
Designation		CONA CMI							
		n06-140		n06-150		n06-140		n06-150	
Characteristic tensile strength	MPa	1 770	1 860	1 770	1 860	1 770	1 860	1 770	1 860
—	—	kN	kN	kN	kN	kN	kN	kN	kN
n Number of strands	01	196	206	211	221	207	218	222	234
	02	392	412	421	443	414	435	445	467
	03	589	618	632	664	621	653	667	701
	04	785	824	842	886	828	870	889	935
	05	981	1 031	1 053	1 107	1 036	1 088	1 112	1 169
	06	1 177	1 237	1 264	1 328	1 243	1 305	1 334	1 402
	07	1 373	1 443	1 474	1 550	1 450	1 523	1 556	1 636
	08	1 570	1 649	1 685	1 771	1 657	1 740	1 778	1 870
	09	1 766	1 855	1 895	1 993	1 864	1 958	2 001	2 103
	12	2 354	2 473	2 527	2 657	2 485	2 611	2 668	2 804
	13	2 551	2 679	2 738	2 878	2 692	2 828	2 890	3 038
	15	2 943	3 092	3 159	3 321	3 107	3 263	3 335	3 506
	16	3 139	3 298	3 370	3 542	3 314	3 481	3 557	3 739
	19	3 728	3 916	4 001	4 207	3 935	4 133	4 224	4 440
	22	4 316	4 534	4 633	4 871	4 556	4 786	4 891	5 141
	24	4 709	4 946	5 054	5 314	4 970	5 221	5 335	5 609
	25	4 905	5 153	5 265	5 535	5 178	5 439	5 558	5 843
	27	5 297	5 565	5 686	5 978	5 592	5 874	6 002	6 310
	31	6 082	6 389	6 529	6 863	6 420	6 744	6 891	7 245
	37	7 259	7 626	7 792	8 192	7 663	8 049	8 225	8 647
	42	8 240	8 656	8 845	9 299	8 698	9 137	9 337	9 815
	43	8 437	8 862	9 056	9 520	8 905	9 355	9 559	10 049
	48	9 418	9 893	10 109	10 627	9 941	10 442	10 670	11 218
	55	10 791	11 336	11 583	12 177	11 391	11 965	12 227	12 854
	61	11 968	12 572	12 847	13 505	12 633	13 271	13 560	14 256

¹⁾ The given values are maximum values according to Eurocode 2. The actual values are taken from the standards and regulations in force at the place of use. Conformity with the stabilisation and crack width criteria in the load transfer test has been verified to a load level of $0.80 \cdot F_{pk}$.

²⁾ Overstressing is permitted if the force in the prestressing jack is measured to an accuracy of $\pm 5\%$ of the final value of the prestressing force.

Where:

F_{pk} Characteristic value of maximum force of tendon

$F_{p0.1}$ Characteristic value of 0.1% proof force of the tendon



Internal Post-tensioning System
Maximum prestressing and overstressing forces


Annex 30
of European Technical Assessment
ETA-06/0147 of 26.06.2025

**Inner diameter of circular duct, d_i , and minimum radius of curvature, R_{min} , for
 $p_{R,max} = 130 \text{ kN/m}$**

Number of strands	$f \approx 0.35$		$f \approx 0.40$		$f \approx 0.45$		$f \approx 0.50$	
n	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}
—	mm	m	mm	m	mm	m	mm	m
1	35	2.0	—	—	—	—	—	—
2	35	2.8	—	—	—	—	—	—
3	40	4.2	—	—	—	—	—	—
4	45	4.2	45	4.2	—	—	—	—
5	50	5.1	50	5.1	—	—	—	—
6	55	5.5	55	5.5	—	—	—	—
7	60	5.9	60	5.9	—	—	—	—
8	65	6.2	60	6.7	60	6.7	—	—
9	70	6.5	65	7.0	60	7.6	60	7.6
12	80	7.6	75	8.1	70	8.7	70	8.7
13	85	7.7	80	8.2	75	8.8	70	9.4
15	90	8.4	85	8.9	80	9.5	75	10.1
16	95	8.5	85	9.5	80	10.1	80	10.1
19	100	9.6	95	10.1	90	10.7	85	11.3
22	110	10.1	100	11.1	95	11.7	90	12.3
24	115	10.5	105	11.5	100	12.1	95	12.8
25	115	11.0	110	11.5	105	12.0	100	12.6
27	120	11.4	115	11.9	105	13.0	100	13.6
31	130	12.0	120	13.0	115	13.6	110	14.2
37	140	13.3	135	13.8	125	14.9	120	15.6
42	150	14.1	140	15.2	135	15.7	125	17.0
43	155	14.0	145	15.0	135	16.1	130	16.7
48	160	15.2	150	16.2	145	16.7	135	18.0
55	175	15.9	160	17.4	155	17.9	145	19.2
61	180	17.1	170	18.1	160	19.3	155	19.9

**Inner diameter of circular duct, d_i , and minimum radius of curvature, R_{min} , for
 $p_{R,max} = 140 \text{ kN/m}$**

Number of strands	$f \approx 0.35$		$f \approx 0.40$		$f \approx 0.45$		$f \approx 0.50$	
	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}
—	mm	m	mm	m	mm	m	mm	m
1	35	2.0	—	—	—	—	—	—
2	35	2.6	—	—	—	—	—	—
3	40	3.9	—	—	—	—	—	—
4	45	3.9	45	3.9	—	—	—	—
5	50	4.7	50	4.7	—	—	—	—
6	55	5.1	55	5.1	—	—	—	—
7	60	5.5	60	5.5	—	—	—	—
8	65	5.8	60	6.3	60	6.3	—	—
9	70	6.0	65	6.5	60	7.0	60	7.0
12	80	7.0	75	7.5	70	8.0	70	8.0
13	85	7.2	80	7.6	75	8.1	70	8.7
15	90	7.8	85	8.3	80	8.8	75	9.4
16	95	7.9	85	8.8	80	9.4	80	9.4
19	100	8.9	95	9.4	90	9.9	85	10.5
22	110	9.4	100	10.3	95	10.9	90	11.5
24	115	9.8	105	10.7	100	11.3	95	11.8
25	115	10.2	110	10.7	105	11.2	100	11.7
27	120	10.6	115	11.0	105	12.1	100	12.7
31	130	11.2	120	12.1	115	12.6	110	13.2
37	140	12.4	135	12.9	125	13.9	120	14.5
42	150	13.1	140	14.1	135	14.6	125	15.8
43	155	13.0	145	13.9	135	14.9	130	15.5
48	160	14.1	150	15.0	145	15.5	135	16.7
55	175	14.7	160	16.1	155	16.6	145	17.8
61	180	15.9	170	16.8	160	17.9	155	18.5

Inner diameter of circular duct, d_i , and minimum radius of curvature, R_{min} , for $p_{R,max} = 150 \text{ kN/m}$								
Number of strands	$f \approx 0.35$		$f \approx 0.40$		$f \approx 0.45$		$f \approx 0.50$	
n	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}
—	mm	m	mm	m	mm	m	mm	m
1	35	2.0	—	—	—	—	—	—
2	35	2.4	—	—	—	—	—	—
3	40	3.7	—	—	—	—	—	—
4	45	3.6	45	3.6	—	—	—	—
5	50	4.4	50	4.4	—	—	—	—
6	55	4.8	55	4.8	—	—	—	—
7	60	5.1	60	5.1	—	—	—	—
8	65	5.4	60	5.8	60	5.8	—	—
9	70	5.6	65	6.1	60	6.6	60	6.6
12	80	6.6	75	7.0	70	7.5	70	7.5
13	85	6.7	80	7.1	75	7.6	70	8.1
15	90	7.3	85	7.7	80	8.2	75	8.8
16	95	7.4	85	8.2	80	8.8	80	8.8
19	100	8.3	95	8.8	90	9.2	85	9.8
22	110	8.8	100	9.6	95	10.1	90	10.7
24	115	9.1	105	10.0	100	10.5	95	11.1
25	115	9.5	110	9.9	105	10.4	100	10.9
27	120	9.8	115	10.3	105	11.3	100	11.8
31	130	10.4	120	11.3	115	11.8	110	12.3
37	140	11.6	135	12.0	125	13.0	120	13.5
42	150	12.3	140	13.1	135	13.6	125	14.7
43	155	12.1	145	13.0	135	13.9	130	14.5
48	160	13.1	150	14.0	145	14.5	135	15.6
55	175	13.8	160	15.0	155	15.5	145	16.6
61	180	14.8	170	15.7	160	16.7	155	17.2
<div>  <div> Internal Post-tensioning System Minimum radius of circular duct for $p_{R,max} = 150 \text{ kN/m}$ </div> <div> Annex 33 of European Technical Assessment ETA-06/0147 of 26.06.2025 </div> </div>								

**Inner diameter of circular duct, d_i , and minimum radius of curvature, R_{min} , for
 $p_{R,max} = 200 \text{ kN/m}$**

Number of strands	$f \approx 0.35$		$f \approx 0.40$		$f \approx 0.45$		$f \approx 0.50$	
	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}
—	mm	m	mm	m	mm	m	mm	m
1	35	2.0	—	—	—	—	—	—
2	35	2.0	—	—	—	—	—	—
3	40	2.8	—	—	—	—	—	—
4	45	2.7	45	2.7	—	—	—	—
5	50	3.3	50	3.3	—	—	—	—
6	55	3.6	55	3.6	—	—	—	—
7	60	3.8	60	3.8	—	—	—	—
8	65	4.0	60	4.4	60	4.4	—	—
9	70	4.2	65	4.5	60	4.9	60	4.9
12	80	4.9	75	5.3	70	5.6	70	5.6
13	85	5.0	80	5.3	75	5.7	70	6.1
15	90	5.5	85	5.8	80	6.2	75	6.6
16	95	5.5	85	6.2	80	6.6	80	6.6
19	100	6.2	95	6.6	90	6.9	85	7.3
22	110	6.6	100	7.2	95	7.6	90	8.0
24	115	6.9	105	7.5	100	7.9	95	8.3
25	115	7.1	110	7.5	105	7.8	100	8.2
27	120	7.4	115	7.7	105	8.4	100	8.9
31	130	7.8	120	8.5	115	8.8	110	9.3
37	140	8.7	135	9.0	125	9.7	120	10.1
42	150	9.2	140	9.8	135	10.2	125	11.0
43	155	9.1	145	9.7	135	10.5	130	10.9
48	160	9.8	150	10.5	145	10.9	135	11.7
55	175	10.3	160	11.3	155	11.6	145	12.5
61	180	11.1	170	11.8	160	12.5	155	12.9




Internal Post-tensioning System
Minimum radius of circular duct
for $p_{R,max} = 200 \text{ kN/m}$

Annex 34
of European Technical Assessment
ETA-06/0147 of 26.06.2025

**Inner diameter of circular duct, d_i , and minimum radius of curvature, R_{min} , for
 $p_{R,max} = 230 \text{ kN/m}$**

Number of strands	$f \approx 0.35$		$f \approx 0.40$		$f \approx 0.45$		$f \approx 0.50$	
	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}	d_i	R_{min}
—	mm	m	mm	m	mm	m	mm	m
1	35	2.0	—	—	—	—	—	—
2	35	2.0	—	—	—	—	—	—
3	40	2.4	—	—	—	—	—	—
4	45	2.4	45	2.4	—	—	—	—
5	50	2.9	50	2.9	—	—	—	—
6	55	3.1	55	3.1	—	—	—	—
7	60	3.3	60	3.3	—	—	—	—
8	65	3.5	60	3.8	60	3.8	—	—
9	70	3.7	65	4.0	60	4.3	60	4.3
12	80	4.3	75	4.6	70	4.9	70	4.9
13	85	4.4	80	4.6	75	4.9	70	5.3
15	90	4.8	85	5.0	80	5.4	75	5.7
16	95	4.8	85	5.4	80	5.7	80	5.7
19	100	5.4	95	5.7	90	6.0	85	6.4
22	110	5.7	100	6.3	95	6.6	90	7.0
24	115	6.0	105	6.5	100	6.9	95	7.2
25	115	6.2	110	6.5	105	6.8	100	7.1
27	120	6.4	115	6.7	105	7.3	100	7.7
31	130	6.8	120	7.4	115	7.7	110	8.0
37	140	7.5	135	7.8	125	8.4	120	8.8
42	150	8.0	140	8.6	135	8.9	125	9.6
43	155	7.9	145	8.5	135	9.1	130	9.4
48	160	8.6	150	9.1	145	9.4	135	10.1
55	175	9.0	160	9.8	155	10.1	145	10.8
61	180	9.7	170	10.2	160	10.9	155	11.2

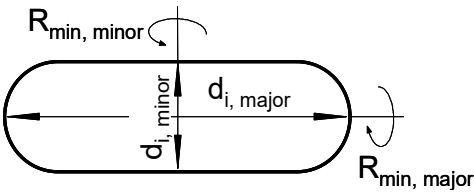

Inner dimensions, d_i , of flat duct and minimum radius of curvature, R_{min}

Number of strands	n	—	02	03	04	05
Inner dimensions	$d_{i, major}$	mm	40	55	70	85
	$d_{i, minor}$	mm	20	20	20	20
$p_{R, max} = 130 \text{ kN/m}$						
Radius of curvature	$R_{min, major}$	m	2.0	2.0	2.0	2.0
	$R_{min, minor}$	m	3.2	4.8	6.4	8.0
$p_{R, max} = 140 \text{ kN/m}$						
Radius of curvature	$R_{min, major}$	m	2.0	2.0	2.0	2.0
	$R_{min, minor}$	m	3.0	4.5	6.0	7.5
$p_{R, max} = 150 \text{ kN/m}$						
Radius of curvature	$R_{min, major}$	m	2.0	2.0	2.0	2.0
	$R_{min, minor}$	m	2.8	4.2	5.6	7.0
$p_{R, max} = 200 \text{ kN/m}$						
Radius of curvature	$R_{min, major}$	m	2.0	2.0	2.0	2.0
	$R_{min, minor}$	m	2.1	3.1	4.2	5.2
$p_{R, max} = 230 \text{ kN/m}$						
Radius of curvature	$R_{min, major}$	m	2.0	2.0	2.0	2.0
	$R_{min, minor}$	m	2.0	2.7	3.6	4.5

Minimum centre spacing of tendon anchorages BT with both, helix and stirrups as additional reinforcement

Tendon			Minimum centre spacing $a_c = b_c$				
$f_{cm, 0, \text{cube}, 150}$	MPa		23	28	34	38	43
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa		19	23	28	31	35
CONA CMI BT 0206	A ¹⁾	mm	210	210	210	210	205
	E ¹⁾	mm	210	210	210	210	210
CONA CMI BT 0306	A	mm	210	210	210	210	205
	E	mm	210	210	210	210	210
CONA CMI BT 0406	A	mm	235	215	210	210	205
	E	mm	235	215	210	210	210
CONA CMI BT 0506	A, E	mm	265	250	250	250	250
CONA CMI BT 0606	A, E	mm	290	265	250	250	250
CONA CMI BT 0706	A, E	mm	310	285	260	255	255
CONA CMI BT 0806	A, E	mm	330	305	280	275	275
CONA CMI BT 0906	A, E	mm	350	320	310	310	310
CONA CMI BT 1206	A, E	mm	405	370	340	325	310
CONA CMI BT 1306	A, E	mm	425	390	355	340	325
CONA CMI BT 1506	A, E	mm	455	415	380	365	365
CONA CMI BT 1606	A, E	mm	470	430	390	375	365
CONA CMI BT 1906	A, E	mm	510	465	425	410	390
CONA CMI BT 2206	A, E	mm	550	500	460	440	420
CONA CMI BT 2406	A, E	mm	575	525	480	460	435
CONA CMI BT 2506	A, E	mm	590	535	485	465	450
CONA CMI BT 2706	A, E	mm	610	555	505	485	460
CONA CMI BT 3106	A, E	mm	650	595	545	520	495
CONA CMI BT 3706	A, E	mm	—	680	680	680	680
CONA CMI BT 4206	A, E	mm	—	735	735	735	735
CONA CMI BT 4306	A, E	mm	—	755	755	755	755
CONA CMI BT 4806	A, E	mm	—	805	805	805	805
CONA CMI BT 5506	A, E, N	mm	—	875	875	875	875
CONA CMI BT 6106	A, E	mm	—	940	940	940	940

- ¹⁾ A Bearing trumplate A
E Bearing trumplate E
N Bearing trumplate N



Internal Post-tensioning System
Minimum centre spacing of CONA CMI BT
Helix and stirrups as additional reinforcement

Annex 37
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum centre spacing of tendon anchorages BT with only helix as additional reinforcement

Tendon			Minimum centre spacing $a_c = b_c$			
$f_{cm, 0, \text{cube}, 150}$	MPa		38	43	53	60
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa		31	35	43	50
CONA CMI BT 0206	A ¹⁾	mm	180	180	180	180
	E ¹⁾	mm	195	195	195	195
CONA CMI BT 0306	A	mm	180	180	180	180
	E	mm	195	195	195	195
CONA CMI BT 0406	A	mm	200	190	190	180
	E	mm	200	200	200	200
CONA CMI BT 0506	A, E	mm	235	230	225	225
CONA CMI BT 0606	A, E	mm	245	235	225	225
CONA CMI BT 0706	A, E	mm	270	240	230	240
CONA CMI BT 0806	A, E	mm	280	270	270	260
CONA CMI BT 0906	A, E	mm	305	305	305	305
CONA CMI BT 1206	A, E	mm	325	310	310	310
CONA CMI BT 1306	A, E	mm	345	340	330	330
CONA CMI BT 1506	A, E	mm	355	350	350	350
CONA CMI BT 1606	A, E	mm	375	365	350	350
CONA CMI BT 1906	A, E	mm	435	390	375	360
CONA CMI BT 2206	A, E	mm	435	420	405	380
CONA CMI BT 2406	A, E	mm	460	445	435	425
CONA CMI BT 2506	A, E	mm	465	445	435	430
CONA CMI BT 2706	A, E	mm	480	465	450	430
CONA CMI BT 3106	A, E	mm	515	485	460	445
CONA CMI BT 3706	A, E	mm	565	520	500	490

¹⁾ ABearing trumplate A
EBearing trumplate E



Internal Post-tensioning System
Minimum centre spacing of CONA CMI BT
Only helix as additional reinforcement

Annex 38
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum centre spacing of tendon anchorages BT with only stirrups as additional reinforcement

Tendon			Minimum centre spacing $a_c = b_c$			
$f_{cm, 0, \text{cube}, 150}$	MPa		38	43	53	60
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa		31	35	43	50
CONA CMI BT 0206	A ¹⁾	mm	180	180	180	180
	E ¹⁾	mm	195	195	195	195
CONA CMI BT 0306	A	mm	180	180	180	180
	E	mm	195	195	195	195
CONA CMI BT 0406	A	mm	200	190	190	180
	E	mm	200	200	200	200
CONA CMI BT 0506	A, E	mm	235	230	225	225
CONA CMI BT 0606	A, E	mm	245	235	225	225
CONA CMI BT 0706	A, E	mm	270	240	230	240
CONA CMI BT 0806	A, E	mm	280	270	270	260
CONA CMI BT 0906	A, E	mm	305	305	305	305
CONA CMI BT 1206	A, E	mm	325	310	310	310
CONA CMI BT 1306	A, E	mm	345	340	330	330
CONA CMI BT 1506	A, E	mm	355	350	350	350
CONA CMI BT 1606	A, E	mm	375	365	350	350
CONA CMI BT 1906	A, E	mm	435	390	375	350
CONA CMI BT 2206	A, E	mm	435	420	405	380
CONA CMI BT 2406	A, E	mm	460	445	435	425
CONA CMI BT 2506	A, E	mm	465	445	435	430
CONA CMI BT 2706	A, E	mm	480	465	450	430
CONA CMI BT 3106	A, E	mm	515	485	460	445
CONA CMI BT 3706	A, E	mm	565	520	500	490
CONA CMI BT 4206	A	mm	—	—	580	550
CONA CMI BT 4306	A	mm	—	—	590	580
CONA CMI BT 4806	A	mm	—	—	610	590
CONA CMI BT 5506	A, N	mm	—	—	670	640

- ¹⁾ ABearing trumplate A
EBearing trumplate E
NBearing trumplate N



Internal Post-tensioning System
Minimum centre spacing of CONA CMI BT
Only stirrups as additional reinforcement

Annex 39
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum centre spacing of tendon anchorages SP with both helix and stirrups as additional reinforcement

Tendon		Minimum centre spacing $a_c = b_c$					
$f_{cm, 0, \text{cube}, 150}$	MPa	26	28	34	38	43	46
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa	21	23	28	31	35	38
CONA CMI SP 0106	mm	120	115	105	100	95	95
CONA CMI SP 0206	mm	170	165	150	145	135	135
CONA CMI SP 0306	mm	205	200	185	175	170	165
CONA CMI SP 0406	mm	235	230	210	200	190	185
CONA CMI SP 0506	mm	265	255	240	225	215	210
CONA CMI SP 0606	mm	290	280	260	245	230	225
CONA CMI SP 0706	mm	315	300	280	270	255	245
CONA CMI SP 0806	mm	335	320	300	285	270	260
CONA CMI SP 0906	mm	355	340	315	300	285	275
CONA CMI SP 1206	mm	410	395	365	345	330	320
CONA CMI SP 1306	mm	425	410	380	360	340	330
CONA CMI SP 1506	mm	455	440	410	390	370	360
CONA CMI SP 1606	mm	470	455	420	400	380	370
CONA CMI SP 1906	mm	510	490	455	435	415	405
CONA CMI SP 2206	mm	550	530	490	465	445	435
CONA CMI SP 2406	mm	575	550	515	485	465	455
CONA CMI SP 2506	mm	585	565	520	495	470	460
CONA CMI SP 2706	mm	605	585	540	515	490	480
CONA CMI SP 3106	mm	650	625	580	555	535	520
CONA CMI SP 3706	mm	715	715	715	715	715	715
CONA CMI SP 4206	mm	765	765	765	765	765	765
CONA CMI SP 4306	mm	775	775	775	775	775	775
CONA CMI SP 4806	mm	830	830	830	830	830	830
CONA CMI SP 5506	mm	905	905	905	905	905	905
CONA CMI SP 6106	mm	960	960	960	960	960	960



Internal Post-tensioning System
Minimum centre spacing of CONA CMI SP

Annex 40
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum edge distance of tendon anchorages BT with both helix and stirrups as additional reinforcement

Tendon			Minimum edge distance $a_e = b_e$				
$f_{cm, 0, \text{cube}, 150}$	MPa		23	28	34	38	43
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa		19	23	28	31	35
CONA CMI BT 0206	A ¹⁾	mm	95 + c	95 + c	95 + c	95 + c	95 + c
	E ¹⁾	mm	100 + c	100 + c	100 + c	100 + c	100 + c
CONA CMI BT 0306	A	mm	95 + c	95 + c	95 + c	95 + c	95 + c
	E	mm	100 + c	100 + c	100 + c	100 + c	100 + c
CONA CMI BT 0406	A	mm	110 + c	100 + c	95 + c	95 + c	95 + c
	E	mm	110 + c	100 + c	100 + c	100 + c	100 + c
CONA CMI BT 0506	A, E	mm	125 + c	115 + c	115 + c	115 + c	115 + c
CONA CMI BT 0606	A, E	mm	135 + c	125 + c	115 + c	115 + c	115 + c
CONA CMI BT 0706	A, E	mm	145 + c	135 + c	120 + c	120 + c	120 + c
CONA CMI BT 0806	A, E	mm	155 + c	145 + c	130 + c	130 + c	130 + c
CONA CMI BT 0906	A, E	mm	165 + c	150 + c	145 + c	145 + c	145 + c
CONA CMI BT 1206	A, E	mm	195 + c	175 + c	160 + c	155 + c	145 + c
CONA CMI BT 1306	A, E	mm	205 + c	185 + c	170 + c	160 + c	155 + c
CONA CMI BT 1506	A, E	mm	220 + c	200 + c	180 + c	175 + c	175 + c
CONA CMI BT 1606	A, E	mm	225 + c	205 + c	185 + c	180 + c	175 + c
CONA CMI BT 1906	A, E	mm	245 + c	225 + c	205 + c	195 + c	185 + c
CONA CMI BT 2206	A, E	mm	265 + c	240 + c	220 + c	210 + c	200 + c
CONA CMI BT 2406	A, E	mm	280 + c	255 + c	230 + c	220 + c	210 + c
CONA CMI BT 2506	A, E	mm	285 + c	260 + c	235 + c	225 + c	215 + c
CONA CMI BT 2706	A, E	mm	295 + c	270 + c	245 + c	235 + c	220 + c
CONA CMI BT 3106	A, E	mm	315 + c	290 + c	265 + c	250 + c	240 + c
CONA CMI BT 3706	A, E	mm	—	330 + c	330 + c	330 + c	330 + c
CONA CMI BT 4206	A, E	mm	—	360 + c	360 + c	360 + c	360 + c
CONA CMI BT 4306	A, E	mm	—	370 + c	370 + c	370 + c	370 + c
CONA CMI BT 4806	A, E	mm	—	395 + c	395 + c	395 + c	395 + c
CONA CMI BT 5506	A, E, N	mm	—	430 + c	430 + c	430 + c	430 + c
CONA CMI BT 6106	A, E	mm	—	460 + c	460 + c	460 + c	460 + c

- ¹⁾ A Bearing trumplate A
E Bearing trumplate E
N Bearing trumplate N
- c Concrete cover in mm. Standards and regulations on concrete cover in force at the place of use are observed.



Internal Post-tensioning System
Minimum edge distance of CONA CMI BT
Helix and stirrups as additional reinforcement

Annex 41
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum edge distance of tendon anchorages BT with only helix as additional reinforcement

Tendon			Minimum edge distance $a_e = b_e$			
$f_{cm, 0, \text{cube}, 150}$	MPa		38	43	53	60
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa		31	35	43	50
CONA CMI BT 0206	A ¹⁾	mm	80 + c	80 + c	80 + c	80 + c
	E ¹⁾	mm	90 + c	90 + c	90 + c	90 + c
CONA CMI BT 0306	A	mm	80 + c	80 + c	80 + c	80 + c
	E	mm	90 + c	90 + c	90 + c	90 + c
CONA CMI BT 0406	A	mm	90 + c	85 + c	85 + c	80 + c
	E	mm	90 + c	90 + c	90 + c	90 + c
CONA CMI BT 0506	A, E	mm	110 + c	105 + c	105 + c	105 + c
CONA CMI BT 0606	A, E	mm	115 + c	110 + c	105 + c	105 + c
CONA CMI BT 0706	A, E	mm	125 + c	110 + c	105 + c	110 + c
CONA CMI BT 0806	A, E	mm	130 + c	125 + c	125 + c	120 + c
CONA CMI BT 0906	A, E	mm	145 + c	145 + c	145 + c	145 + c
CONA CMI BT 1206	A, E	mm	155 + c	145 + c	145 + c	145 + c
CONA CMI BT 1306	A, E	mm	165 + c	160 + c	155 + c	155 + c
CONA CMI BT 1506	A, E	mm	170 + c	165 + c	165 + c	165 + c
CONA CMI BT 1606	A, E	mm	180 + c	175 + c	165 + c	165 + c
CONA CMI BT 1906	A, E	mm	210 + c	185 + c	180 + c	170 + c
CONA CMI BT 2206	A, E	mm	210 + c	200 + c	195 + c	180 + c
CONA CMI BT 2406	A, E	mm	220 + c	215 + c	210 + c	205 + c
CONA CMI BT 2506	A, E	mm	225 + c	215 + c	210 + c	205 + c
CONA CMI BT 2706	A, E	mm	230 + c	225 + c	215 + c	205 + c
CONA CMI BT 3106	A, E	mm	250 + c	235 + c	220 + c	215 + c
CONA CMI BT 3706	A, E	mm	275 + c	250 + c	240 + c	235 + c

¹⁾ ABearing trumplate A

EBearing trumplate E

c Concrete cover in mm. Standards and regulations on concrete cover in force at the place of use are observed.



Internal Post-tensioning System
Minimum edge distance of CONA CMI BT
Only helix as additional reinforcement

Annex 42
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum edge distance of tendon anchorages BT with only stirrups as additional reinforcement

Tendon			Minimum edge distance $a_e = b_e$			
$f_{cm, 0, \text{cube}, 150}$	MPa		38	43	53	60
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa		31	35	43	50
CONA CMI BT 0206	A ¹⁾	mm	80 + c	80 + c	80 + c	80 + c
	E ¹⁾	mm	90 + c	90 + c	90 + c	90 + c
CONA CMI BT 0306	A	mm	80 + c	80 + c	80 + c	80 + c
	E	mm	90 + c	90 + c	90 + c	90 + c
CONA CMI BT 0406	A	mm	90 + c	85 + c	85 + c	80 + c
	E	mm	90 + c	90 + c	90 + c	90 + c
CONA CMI BT 0506	A, E	mm	110 + c	105 + c	105 + c	105 + c
CONA CMI BT 0606	A, E	mm	115 + c	110 + c	105 + c	105 + c
CONA CMI BT 0706	A, E	mm	125 + c	110 + c	105 + c	110 + c
CONA CMI BT 0806	A, E	mm	130 + c	125 + c	125 + c	120 + c
CONA CMI BT 0906	A, E	mm	145 + c	145 + c	145 + c	145 + c
CONA CMI BT 1206	A, E	mm	155 + c	145 + c	145 + c	145 + c
CONA CMI BT 1306	A, E	mm	165 + c	160 + c	155 + c	155 + c
CONA CMI BT 1506	A, E	mm	170 + c	165 + c	165 + c	165 + c
CONA CMI BT 1606	A, E	mm	180 + c	175 + c	165 + c	165 + c
CONA CMI BT 1906	A, E	mm	210 + c	185 + c	180 + c	165 + c
CONA CMI BT 2206	A, E	mm	210 + c	200 + c	195 + c	180 + c
CONA CMI BT 2406	A, E	mm	220 + c	215 + c	210 + c	205 + c
CONA CMI BT 2506	A, E	mm	225 + c	215 + c	210 + c	205 + c
CONA CMI BT 2706	A, E	mm	230 + c	225 + c	215 + c	205 + c
CONA CMI BT 3106	A, E	mm	250 + c	235 + c	220 + c	215 + c
CONA CMI BT 3706	A, E	mm	275 + c	250 + c	240 + c	235 + c
CONA CMI BT 4206	A,	mm	—	—	280 + c	265 + c
CONA CMI BT 4306	A	mm	—	—	285 + c	280 + c
CONA CMI BT 4806	A	mm	—	—	295 + c	285 + c
CONA CMI BT 5506	A, N	mm	—	—	325 + c	310 + c

¹⁾ ABearing trumplate A

EBearing trumplate E

NBearing trumplate N

c Concrete cover in mm. Standards and regulations on concrete cover in force at the place of use are observed.



Internal Post-tensioning System
Minimum edge distance of CONA CMI BT
Only stirrups as additional reinforcement

Annex 43
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Minimum edge distance of tendon anchorages SP with both helix and stirrups as additional reinforcement

Tendon		Minimum edge distance $a_e = b_e$					
$f_{cm, 0, \text{cube}, 150}$	MPa	26	28	34	38	43	46
$f_{cm, 0, \text{cylinder}, \varnothing 150}$	MPa	21	23	28	31	35	38
CONA CMI SP 0106	mm	50 + c	50 + c	45 + c	40 + c	40 + c	40 + c
CONA CMI SP 0206	mm	75 + c	75 + c	65 + c	65 + c	60 + c	60 + c
CONA CMI SP 0306	mm	95 + c	90 + c	85 + c	80 + c	75 + c	75 + c
CONA CMI SP 0406	mm	110 + c	105 + c	95 + c	90 + c	85 + c	85 + c
CONA CMI SP 0506	mm	125 + c	120 + c	110 + c	105 + c	100 + c	95 + c
CONA CMI SP 0606	mm	135 + c	130 + c	120 + c	115 + c	105 + c	105 + c
CONA CMI SP 0706	mm	150 + c	140 + c	130 + c	125 + c	120 + c	115 + c
CONA CMI SP 0806	mm	160 + c	150 + c	140 + c	135 + c	125 + c	120 + c
CONA CMI SP 0906	mm	170 + c	160 + c	150 + c	140 + c	135 + c	130 + c
CONA CMI SP 1206	mm	195 + c	190 + c	175 + c	165 + c	155 + c	150 + c
CONA CMI SP 1306	mm	205 + c	195 + c	180 + c	170 + c	160 + c	155 + c
CONA CMI SP 1506	mm	220 + c	210 + c	195 + c	185 + c	175 + c	170 + c
CONA CMI SP 1606	mm	225 + c	220 + c	200 + c	190 + c	180 + c	175 + c
CONA CMI SP 1906	mm	245 + c	235 + c	220 + c	210 + c	200 + c	195 + c
CONA CMI SP 2206	mm	265 + c	255 + c	235 + c	225 + c	215 + c	210 + c
CONA CMI SP 2406	mm	280 + c	265 + c	250 + c	235 + c	225 + c	220 + c
CONA CMI SP 2506	mm	285 + c	275 + c	250 + c	240 + c	225 + c	220 + c
CONA CMI SP 2706	mm	295 + c	285 + c	260 + c	250 + c	235 + c	230 + c
CONA CMI SP 3106	mm	315 + c	305 + c	280 + c	270 + c	260 + c	250 + c
CONA CMI SP 3706	mm	350 + c	350 + c	350 + c	350 + c	350 + c	350 + c
CONA CMI SP 4206	mm	375 + c	375 + c	375 + c	375 + c	375 + c	375 + c
CONA CMI SP 4306	mm	380 + c	380 + c	380 + c	380 + c	380 + c	380 + c
CONA CMI SP 4806	mm	405 + c	405 + c	405 + c	405 + c	405 + c	405 + c
CONA CMI SP 5506	mm	445 + c	445 + c	445 + c	445 + c	445 + c	445 + c
CONA CMI SP 6106	mm	470 + c	470 + c	470 + c	470 + c	470 + c	470 + c


c..... Concrete cover in mm. Standards and regulations on concrete cover in force at the place of use are observed.



Internal Post-tensioning System
Minimum edge distance of CONA CMI SP

Annex 44
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

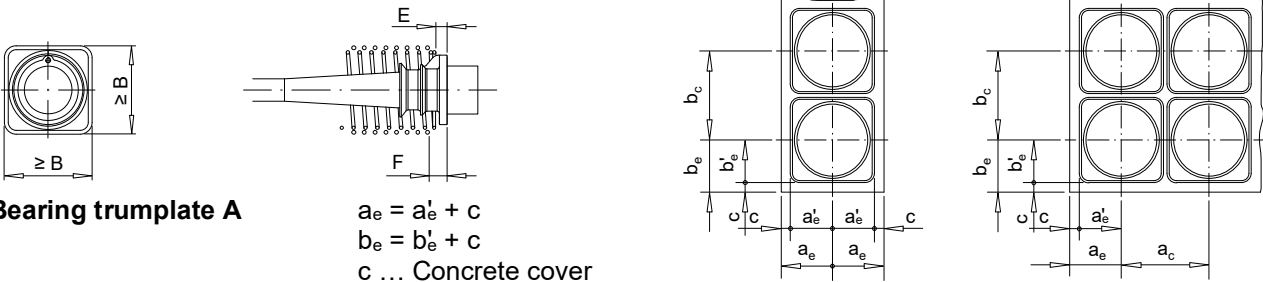




Bearing trumplate A

$$a_e = a'_e + c$$

$$b_e = b'_e + c$$

c ... Concrete cover

BBR VT CONA CMI BT			0206					0306					0406				
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	300					450					600				
Char. value of maximum force	F _{pk}	kN	558					837					1 116				
Char. value of 0.1% proof force	F _{p0.1}	kN	492					738					984				
Max. prestressing force	0.90 · F _{p0.1}	kN	443					664					886				
Max. overstressing force	0.95 · F _{p0.1}	kN	467					701					935				
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35
Helix																	
Outer diameter		mm	160	160	160	160	155	160	160	160	160	155	180	160	160	160	155
Bar diameter		mm	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10
Length approximately		mm	185	185	185	185	185	185	185	185	185	185	185	185	185	185	185
Pitch		mm	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45
Number of pitches		—	5	5	5	5	5	5	5	5	5	5	5	5	5	5	5
Distance	E	mm	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15
Additional stirrup reinforcement																	
Number of stirrups		—	3	3	3	3	3	4	3	4	4	3	3	3	4	4	3
Bar diameter		mm	8	8	8	8	8	8	10	8	8	10	12	12	10	10	12
Spacing		mm	55	55	55	55	55	45	55	45	45	55	60	55	45	45	55
Distance from anchor plate	F	mm	30	30	30	30	30	30	30	30	30	30	30	30	30	30	30
Minimum outer dimensions	B × B	mm	190	190	190	190	190	190	190	190	190	190	220	200	190	190	190
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	210	210	210	210	205	210	210	210	210	205	235	215	210	210	205
Min. edge distance + c	a _e ¹⁾ , b _e ¹⁾	mm	95	95	95	95	95	95	95	95	95	95	110	100	95	95	95


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.






Internal Post-tensioning System
Anchorage zone of CONA CMI BT
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance

Annex 45
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

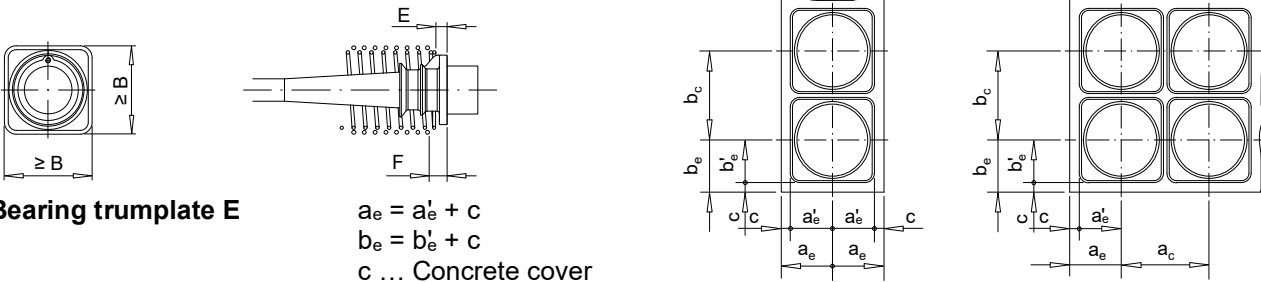Stressing and fixed anchorage or coupler – Centre spacing and edge distance



BBR VT CONA CMI BT			0206					0306					0406				
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	300					450					600				
Char. value of maximum force	F _{pk}	kN	558					837					1 116				
Char. value of 0.1% proof force	F _{p0.1}	kN	492					738					984				
Max. prestressing force	0.90 · F _{p0.1}	kN	443					664					886				
Max. oversteressing force	0.95 · F _{p0.1}	kN	467					701					935				
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35
Helix																	
Outer diameter	mm	175	175	175	175	175	175	175	175	175	175	175	180	175	175	175	175
Bar diameter	mm	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10
Length approximately	mm	185	185	185	185	185	185	185	185	185	185	185	185	185	185	185	185
Pitch	mm	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45
Number of pitches	—	5	5	5	5	5	5	5	5	5	5	5	5	5	5	5	5
Distance	E	mm	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15
Additional stirrup reinforcement																	
Number of stirrups	—	3	3	3	3	3	4	3	4	4	3	3	3	4	4	3	3
Bar diameter	mm	8	8	8	8	8	8	10	8	8	10	12	12	10	10	12	12
Spacing	mm	55	55	55	55	55	45	55	45	45	55	60	55	45	45	55	55
Distance from anchor plate	F	mm	30	30	30	30	30	30	30	30	30	30	30	30	30	30	30
Minimum outer dimensions	B × B	mm	195	195	195	195	195	195	195	195	195	195	220	200	195	195	195
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	210	210	210	210	210	210	210	210	210	210	235	215	210	210	210
Min. edge distance + c	a _e ¹ , b _e ¹	mm	100	100	100	100	100	100	100	100	100	100	110	100	100	100	100


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.






Internal Post-tensioning System
Anchorage zone of CONA CMI BT
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance

Annex 46
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

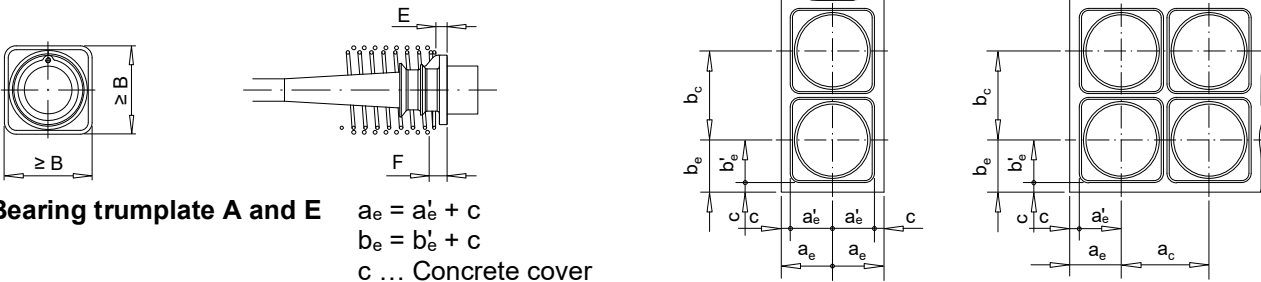

BBR VT CONA CMI BT			0506					0606					0706				
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm²	750					900					1 050				
Char. value of maximum force	F _{pk}	kN	1 395					1 674					1 953				
Char. value of 0.1% proof force	F _{p0.1}	kN	1 230					1 476					1 722				
Max. prestressing force	0.90 · F _{p0.1}	kN	1 107					1 328					1 550				
Max. overstressing force	0.95 · F _{p0.1}	kN	1 169					1 402					1 636				
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35
Helix																	
Outer diameter	mm	200	195	195	195	195	200	200	195	195	195	230	200	200	200	200	
Bar diameter	mm	10	10	10	10	10	10	10	10	10	10	12	12	12	12	12	
Length approximately	mm	230	205	205	245	230	253	230	205	245	230	254	256	231	231	231	
Pitch	mm	45	50	50	60	50	45	50	50	60	50	45	50	50	50	50	
Number of pitches	—	6	5	5	5	5	6	5	5	5	5	6	6	5	5	5	
Distance	E mm	18	18	18	18	18	18	18	18	18	18	18	18	18	18	18	
Additional stirrup reinforcement																	
Number of stirrups	—	4	4	4	3	4	5	4	5	3	4	5	4	4	4	4	
Bar diameter ²⁾	mm	12	12	12	12	12	12	12	12	12	12	14	14	12	14	14	
Spacing	mm	55	50	50	65	50	50	55	45	65	50	55	60	55	55	55	
Distance from anchor plate	F mm	33	33	33	33	33	33	33	33	33	33	33	33	33	33	33	
Minimum outer dimensions	B × B mm	250	230	230	230	230	270	250	230	230	230	290	270	240	240	240	
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	265	250	250	250	250	290	265	250	250	250	310	285	260	255	255
Min. edge distance + c	a _e ¹ , b _e ¹	mm	125	115	115	115	115	135	125	115	115	115	145	135	120	120	120


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ Bar diameter of 14 mm can be replaced by 16 mm.



Internal Post-tensioning System
Anchorage zone of CONA CMI BT
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance

Annex 47
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

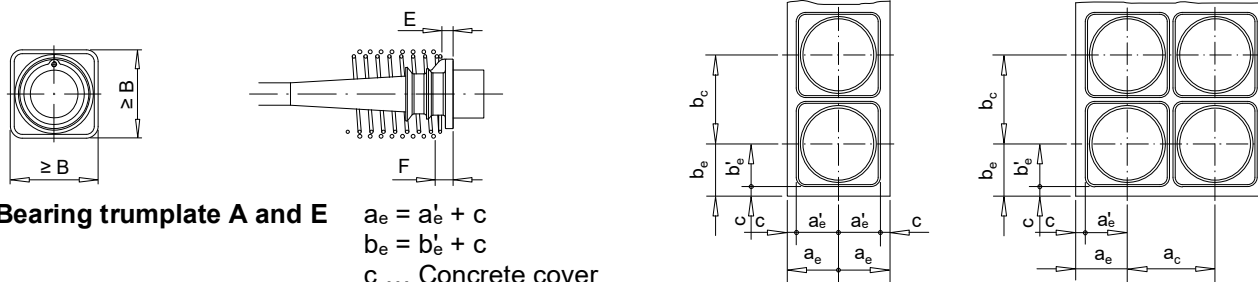

BBR VT CONA CMI BT			0806						0906						1206					
Strand arrangement																				
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																				
Tendon																				
Cross-sectional area	A _p	mm ²	1 200						1 350						1 800					
Char. value of maximum force	F _{pk}	kN	2 232						2 511						3 348					
Char. value of 0.1% proof force	F _{p0.1}	kN	1 968						2 214						2 952					
Max. prestressing force	0.90 · F _{p0.1}	kN	1 771						1 993						2 657					
Max. oversteering force	0.95 · F _{p0.1}	kN	1 870						2 103						2 804					
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																				
Minimum concrete strength																				
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43			
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35			
Helix																				
Outer diameter	mm	270	230	225	220	220	280	260	255	250	250	330	280	275	260	250				
Bar diameter ²⁾	mm	14	12	12	12	12	14	12	12	12	12	14	14	14	14	14				
Length approximately	mm	282	256	231	256	256	282	281	281	281	281	332	332	332	332	282				
Pitch	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50				
Number of pitches	—	6	6	5	6	6	6	6	6	6	6	7	7	7	7	6				
Distance	E mm	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20				
Additional stirrup reinforcement																				
Number of stirrups	—	4	6	5	4	5	5	5	5	4	5	7	6	5	5	6				
Bar diameter ²⁾	mm	12	12	12	14	14	12	14	12	14	14	12	14	16	16	14				
Spacing	mm	70	45	50	55	50	60	55	55	65	55	60	55	70	70	50				
Distance from anchor plate	F mm	33	33	33	33	33	35	35	35	35	35	35	35	35	35	35				
Minimum outer dimensions	B × B mm	310	290	260	260	260	330	300	290	290	290	390	350	320	310	290				
Centre spacing and edge distance																				
Minimum centre spacing	a _c , b _c	mm	330	305	280	275	275	350	320	310	310	310	405	370	340	325	310			
Min. edge distance + c	a _e ['] , b _e [']	mm	155	145	130	130	130	165	150	145	145	145	195	175	160	155	145			

¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.


²⁾ Bar diameter of 14 mm can be replaced by 16 mm.






Internal Post-tensioning System
Anchorage zone of CONA CMI BT
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance

Annex 48
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

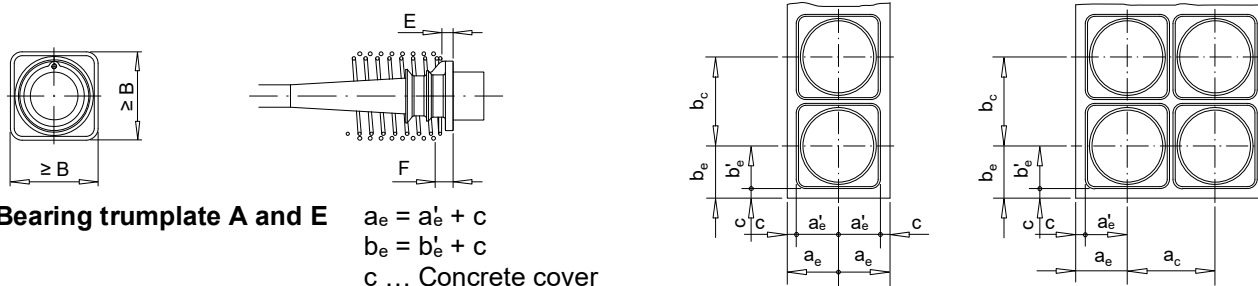Stressing and fixed anchorage or coupler – Centre spacing and edge distance







BBR VT CONA CMI BT			1306						1506						1606																					
Strand arrangement																																				
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																																				
Tendon																																				
Cross-sectional area			A _p		mm ²		1 950			2 250			2 400																							
Char. value of maximum force			F _{pk}		kN		3 627			4 185			4 464																							
Char. value of 0.1% proof force			F _{p0.1}		kN		3 198			3 690			3 936																							
Max. prestressing force			0.90 · F _{p0.1}		kN		2 878			3 321			3 542																							
Max. overstressing force			0.95 · F _{p0.1}		kN		3 038			3 506			3 739																							
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																																				
Minimum concrete strength																																				
Cube			f _{cm, 0, cube, 150}		MPa		23		28		34		38		43																					
Cylinder			f _{cm, 0, cylinder, Ø 150}		MPa		19		23		28		31		35																					
Helix																																				
Outer diameter			mm		375		330		300		280		270		375		330		315		305		305		375		330		320		310		305			
Bar diameter ²⁾			mm		14		14		14		14		14		14		14		14		14		14		14		14		14		14					
Length approximately			mm		382		357		382		332		282		432		432		382		332		332		432		432		432		382		332			
Pitch			mm		50		50		50		50		50		50		50		50		50		50		50		50		50		50					
Number of pitches			—		8		8		8		7		6		9		9		8		7		7		9		9		9		8		7			
Distance			E		mm		23		23		23		23		27		27		27		27		27		27		27		27		27					
Additional stirrup reinforcement																																				
Number of stirrups			—		7		6		6		6		7		7		6		5		6		5		7		6		5		6		6			
Bar diameter ²⁾			mm		12		14		14		14		14		14		16		16		16		16		14		16		16		16		16			
Spacing			mm		55		60		55		60		45		60		65		65		55		60		60		65		65		60		60			
Distance from anchor plate			F		mm		40		40		40		40		42		42		42		42		42		42		42		42		42		42			
Minimum outer dimensions			B × B		mm		410		370		340		320		310		440		400		360		350		350		450		410		370		360		350	
Centre spacing and edge distance																																				
Minimum centre spacing			a _c , b _c		mm		425		390		355		340		325		455		415		380		365		365		470		430		390		375		365	
Min. edge distance + c			a _e ['] , b _e [']		mm		205		185		170		160		155		220		200		180		175		175		225		205		185		180		175	

¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.

²⁾ Bar diameter of 14 mm can be replaced by 16 mm.

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

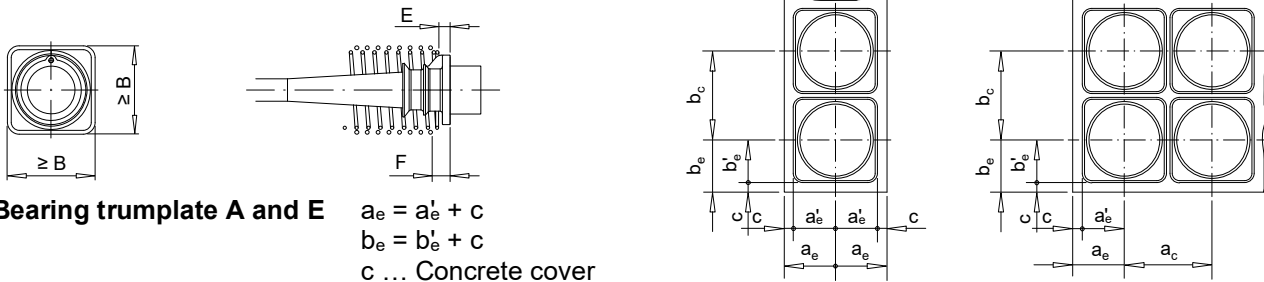


BBR VT CONA CMI BT			1906					2206					2406				
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	2 850					3 300					3 600				
Char. value of maximum force	F _{pk}	kN	5 301					6 138					6 696				
Char. value of 0.1 % proof force	F _{p0.1}	kN	4 674					5 412					5 904				
Max. prestressing force	0.90 · F _{p0.1}	kN	4 207					4 871					5 314				
Max. oversteering force	0.95 · F _{p0.1}	kN	4 440					5 141					5 609				
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35
Helix																	
Outer diameter	mm	420	360	360	330	325	475	420	390	360	340	475	430	410	360	360	
Bar diameter ²⁾	mm	14	14	14	14	14	14	14	14	14	14	14	14	14	14	14	
Length approximately	mm	457	457	432	432	382	482	482	432	432	382	532	532	482	482	432	
Pitch	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	
Number of pitches	—	10	10	9	9	8	10	10	9	9	8	11	11	10	10	9	
Distance	E mm	27	27	27	27	27	31	31	31	31	31	32	32	32	32	32	
Additional stirrup reinforcement																	
Number of stirrups	—	7	7	7	7	7	6	7	8	7	8	7	7	7	7	8	
Bar diameter	mm	16	16	16	16	16	20	20	20	20	16	20	20	20	20	20	
Spacing	mm	65	65	65	65	60	80	75	65	65	50	80	80	70	65	55	
Distance from anchor plate	F mm	42	42	42	42	42	46	46	46	46	46	47	47	47	47	47	
Minimum outer dimensions	B × B mm	490	450	410	390	370	530	480	440	420	400	560	510	460	440	420	
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	510	465	425	410	390	550	500	460	440	420	575	525	480	460	435
Min. edge distance + c	a _e ¹ , b _e ¹	mm	245	225	205	195	185	265	240	220	210	200	280	255	230	220	210

¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.

²⁾ Bar diameter of 14 mm can be replaced by 16 mm.

Stressing and fixed anchorage or coupler – Centre spacing and edge distance



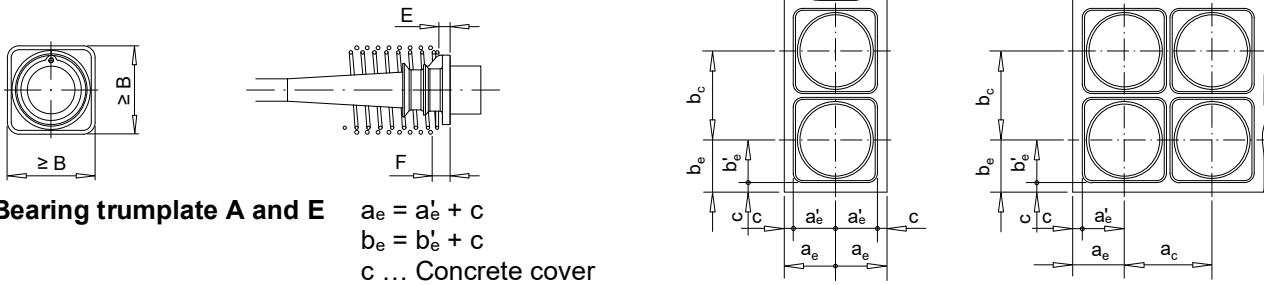


Bearing trumplate A and E

$$a_e = a'_e + c$$

$$b_e = b'_e + c$$

c ... Concrete cover

BBR VT CONA CMI BT		2506					2706					3106					
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	3 750					4 050					4 650				
Char. value of maximum force	F _{pk}	kN	6 975					7 533					8 649				
Char. value of 0.1% proof force	F _{p0.1}	kN	6 150					6 642					7 626				
Max. prestressing force	0.90 · F _{p0.1}	kN	5 535					5 978					6 863				
Max. overstressing force	0.95 · F _{p0.1}	kN	5 843					6 310					7 245				
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35
Helix																	
Outer diameter	mm	520	430	420	390	380	520	475	440	420	390	560	520	475	430	430	
Bar diameter ²⁾	mm	14	14	14	14	14	14	14	14	14	14	14	14	14	14	14	
Length approximately	mm	532	532	482	482	432	532	532	482	482	432	532	532	582	482	432	
Pitch	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	
Number of pitches	—	11	11	10	10	9	11	11	10	10	9	11	11	12	10	9	
Distance	E	mm	35	35	35	35	35	35	35	35	35	35	35	35	35	35	
Additional stirrup reinforcement																	
Number of stirrups	—	7	6	7	7	7	8	7	7	8	8	9	8	8	8	8	
Bar diameter	mm	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	
Spacing	mm	80	90	70	60	60	80	80	75	60	60	80	75	70	65	60	
Distance from anchor plate	F	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	
Minimum outer dimensions	B × B	mm	570	520	470	450	430	590	540	490	470	440	630	580	530	500	480
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	590	535	485	465	450	610	555	505	485	460	650	595	545	520	495
Min. edge distance + c	a _e , b _e	mm	285	260	235	225	215	295	270	245	235	220	315	290	265	250	240


- ¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
- ²⁾ Bar diameter of 14 mm can be replaced by 16 mm.






Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance

Annex 51
of European Technical Assessment
ETA-06/0147 of 26.06.2025


Stressing and fixed anchorage or coupler – Centre spacing and edge distance



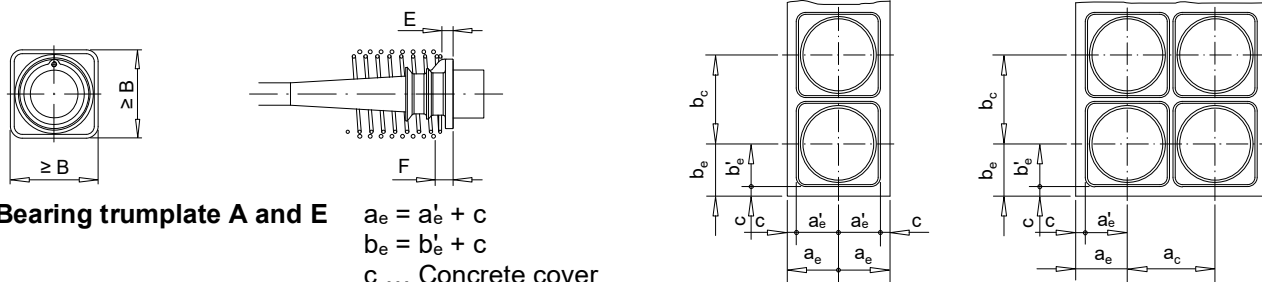


BBR VT CONA CMI BT			3706						4206						4306					
Strand arrangement																				
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																				
Tendon																				
Cross-sectional area	A _p	mm ²	5 550						6 300						6 450					
Char. value of maximum force	F _{pk}	kN	10 323						11 718						11 997					
Char. value of 0.1% proof force	F _{p0.1}	kN	9 102						10 332						10 578					
Max. prestressing force	0.90 · F _{p0.1}	kN	8 192						9 299						9 520					
Max. oversteering force	0.95 · F _{p0.1}	kN	8 647						9 815						10 049					
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																				
Minimum concrete strength																				
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43			
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35			
Helix																				
Outer diameter	mm	—	580	580	580	580	—	630	630	630	630	—	670	670	670	670	—			
Bar diameter	mm	—	16	16	16	16	—	16	16	16	16	—	16	16	16	16	—			
Length approximately	mm	—	533	533	533	533	—	583	583	583	583	—	583	583	583	583	—			
Pitch	mm	—	50	50	50	50	—	50	50	50	50	—	50	50	50	50	—			
Number of pitches	—	—	11	11	11	11	—	12	12	12	12	—	12	12	12	12	—			
Distance	E mm	—	40	40	40	40	—	45	45	45	45	—	45	45	45	45	—			
Additional stirrup reinforcement																				
Number of stirrups	—	—	9	9	9	9	—	10	10	10	10	—	10	10	10	10	—			
Bar diameter	mm	—	20	20	20	20	—	20	20	20	20	—	20	20	20	20	—			
Spacing	mm	—	70	70	70	70	—	70	70	70	70	—	70	70	70	70	—			
Distance from anchor plate	F mm	—	50	50	50	50	—	55	55	55	55	—	55	55	55	55	—			
Minimum outer dimensions	B × B mm	—	660	660	660	660	—	720	720	720	720	—	740	740	740	740	—			
Centre spacing and edge distance																				
Minimum centre spacing	a _c , b _c	mm	—	680	680	680	680	—	735	735	735	735	—	755	755	755	755			
Min. edge distance + c	a _e , b _e	mm	—	330	330	330	330	—	360	360	360	360	—	370	370	370	370			

¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

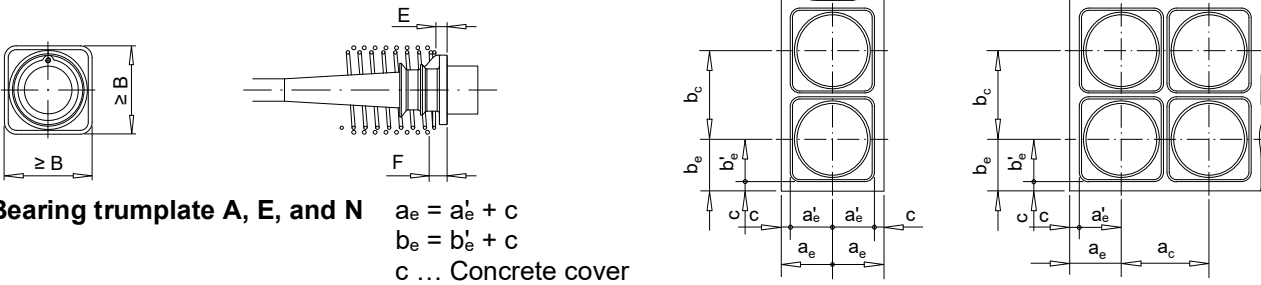

BBR VT CONA CMI BT			4806					5506					6106				
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	7 200					8 250					9 150				
Char. value of maximum force	F _{pk}	kN	13 392					15 345					17 019				
Char. value of 0.1% proof force	F _{p0.1}	kN	11 808					13 530					15 006				
Max. prestressing force	0.90 · F _{p0.1}	kN	10 627					12 177					13 505				
Max. overstressing force	0.95 · F _{p0.1}	kN	11 218					12 854					14 256				
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0, cube, 150}	MPa	23	28	34	38	43	23	28	34	38	43	23	28	34	38	43
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	19	23	28	31	35	19	23	28	31	35	19	23	28	31	35
Helix																	
Outer diameter	mm	—	710	710	710	710	—	780	780	780	780	—	850	850	850	850	—
Bar diameter	mm	—	16	16	16	16	—	20	20	20	20	—	20	20	20	20	—
Length approximately	mm	—	633	633	633	633	—	760	760	760	760	—	790	790	790	790	—
Pitch	mm	—	50	50	50	50	—	60	60	60	60	—	60	60	60	60	—
Number of pitches	—	—	13	13	13	13	—	13	13	13	13	—	14	14	14	14	—
Distance	E mm	—	45	45	45	45	—	50	50	50	50	—	55	55	55	55	—
Additional stirrup reinforcement																	
Number of stirrups	—	—	11	11	11	11	—	11	11	11	11	—	12	12	12	12	—
Bar diameter	mm	—	20	20	20	20	—	20	20	20	20	—	20	20	20	20	—
Spacing	mm	—	70	70	70	70	—	75	75	75	75	—	75	75	75	75	—
Distance from anchor plate	F mm	—	55	55	55	55	—	55	55	55	55	—	60	60	60	60	—
Minimum outer dimensions	B × B mm	—	790	790	790	790	—	860	860	860	860	—	920	920	920	920	—
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	—	805	805	805	805	—	875	875	875	875	—	940	940	940	940
Min. edge distance + c	a _e ', b _e '	mm	—	395	395	395	395	—	430	430	430	430	—	460	460	460	460


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.



Internal Post-tensioning System
Anchorage zone of CONA CMI BT
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance

Annex 53
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

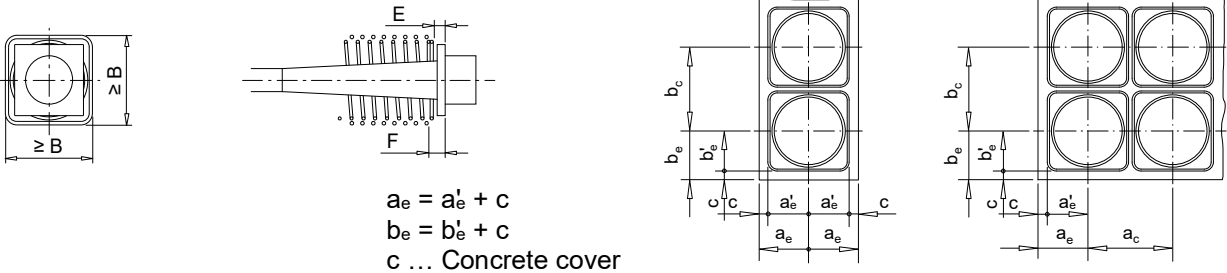

BBR VT CONA CMI SP			0106						
Strand arrangement									
7-wire prestressing steel strand – Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾									
Tendon									
Cross-sectional area	A _p	mm²	150						
Char. value of maximum force	F _{pk}	kN	279						
Char. value of 0.1 % proof force	F _{p0.1}	kN	246						
Maximum prestressing force	0.90 · F _{p0.1}	kN	221						
Maximum overstressing force	0.95 · F _{p0.1}	kN	234						
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions									
Minimum concrete strength									
Cube	f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa									
Outer diameter	mm	100	100	75	75	75	75		
Bar diameter	mm	10	10	10	8	8	8		
Length approximately	mm	100	100	78	76	76	76		
Pitch	mm	45	45	45	45	45	45		
Number of pitches	—	3	3	2.5	2.5	2.5	2.5		
Distance	E	mm	20	20	20	20	20	20	
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa									
Number of stirrups	—	2	2	2	2	2	2	2	
Bar diameter	mm	6	6	6	6	6	6	6	
Spacing	mm	80	75	70	65	60	60	60	
Distance from anchor plate	F	mm	40	40	40	40	40	40	
Minimum outer dimensions	B × B	mm	100	95	85	80	75	75	
Centre spacing and edge distance									
Minimum centre spacing	a _c , b _c	mm	120	115	105	100	95	95	
Min. edge distance + c	a _e ^o , b _e ^o	mm	50	50	45	40	40	40	
Square plate dimensions ²⁾									
Side length	S _{SP}	mm	80	80	80	80	80	80	
Thickness	T _{SP}	mm	20	20	20	20	20	20	


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
 Anchorage zone of CONA CMI SP
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 54
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

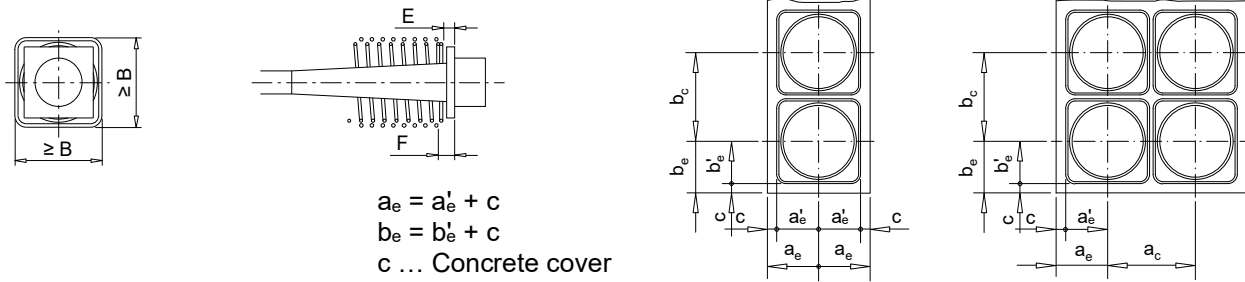Stressing and fixed anchorage or coupler – Centre spacing and edge distance



BBR VT CONA CMI SP			0206					0306					0406							
Strand arrangement																				
7-wire prestressing steel strand																				
Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																				
Tendon																				
Cross-sectional area	A _p	mm ²	300					450					600							
Char. value of maximum force	F _{pk}	kN	558					837					1 116							
Char. value of 0.1 % proof force	F _{p0.1}	kN	492					738					984							
Max. prestressing force	0.90 · F _{p0.1}	kN	443					664					886							
Maximum overstressing force	0.95 · F _{p0.1}	kN	467					701					935							
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																				
Minimum concrete strength																				
Cube	f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																				
Outer diameter	mm	130	130	100	100	100	100	165	160	130	130	120	120	195	190	165	150	145	140	
Bar diameter	mm	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10	10	
Length approximately	mm	145	145	123	123	123	123	168	168	145	145	145	145	190	190	168	168	168	168	
Pitch	mm	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	
Number of pitches	—	4	4	3.5	3.5	3.5	3.5	4.5	4.5	4	4	4	4	5	5	4.5	4.5	4.5	4.5	
Distance	E	mm	20	20	20	20	20	20	20	20	20	20	20	25	25	25	25	25	25	
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																				
Number of stirrups	—	2	2	3	3	2	2	3	3	6	5	5	5	4	3	5	4	4	4	
Bar diameter	mm	6	6	6	6	6	6	10	10	8	8	8	8	10	10	10	10	10	10	
Spacing	mm	110	110	60	55	90	90	80	80	30	35	35	35	65	90	45	55	50	50	
Distance from anchor plate	F	mm	40	40	40	40	40	40	40	40	40	40	40	45	45	45	45	45	45	
Minimum outer dimensions	B × B	mm	150	145	130	125	115	115	185	180	165	155	150	145	215	210	190	180	170	165
Centre spacing and edge distance																				
Minimum centre spacing	a _c , b _c	mm	170	165	150	145	135	135	205	200	185	175	170	165	235	230	210	200	190	185
Min. edge distance + c	a _e ', b _e '	mm	75	75	65	65	60	60	95	90	85	80	75	75	110	105	95	90	85	85
Square plate dimensions ²⁾																				
Side length	S _{SP}	mm	140	140	140	140	135	135	145	145	145	140	140	140	155	155	155	155	150	150
Thickness	T _{SP}	mm	20	20	20	20	20	20	20	20	20	20	20	20	25	25	25	25	25	25


- ¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
- ²⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
Anchorage zone of CONA CMI SP
Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 55
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

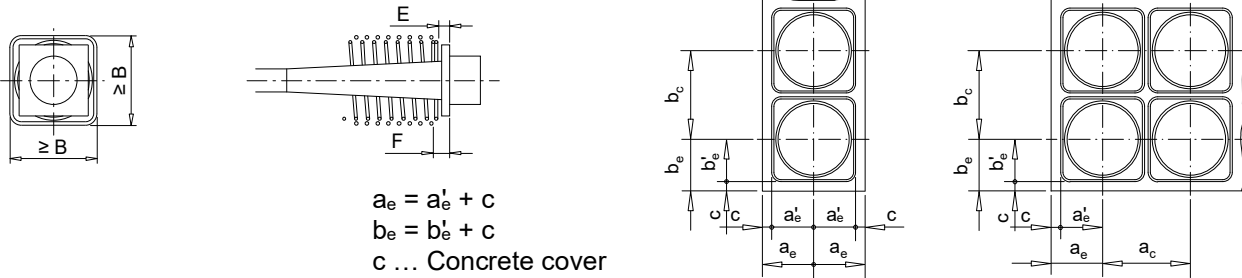

BBR VT CONA CMI SP			0506							0606							0706										
Strand arrangement																											
7-wire prestressing steel strand																											
Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																											
Tendon																											
Cross-sectional area		A _p	mm ²	750							900							1 050									
Char. value of maximum force		F _{pk}	kN	1 395							1 674							1 953									
Char. value of 0.1 % proof force		F _{p0.1}	kN	1 230							1 476							1 722									
Maxi. prestressing force 0.90 · F _{p0.1}			kN	1 107							1 328							1 550									
Maximum overstressing force 0.95 · F _{p0.1}			kN	1 169							1 402							1 636									
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																											
Minimum concrete strength																											
Cube		f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46						
Cylinder		f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38						
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																											
Outer diameter		mm	215	200	185	170	160	160	250	230	210	180	175	175	260	255	220	210	195	190							
Bar diameter		mm	10	10	10	10	10	10	10	10	12	12	12	12	10	10	12	12	12	12							
Length approximately		mm	235	213	210	185	185	185	235	235	212	212	187	187	258	258	237	237	212	212							
Pitch		mm	45	45	50	50	50	50	45	45	50	50	50	50	45	45	50	50	50	50							
Number of pitches		—	6	5.5	5	4.5	4.5	4.5	6	6	5	5	4.5	4.5	6.5	6.5	5.5	5.5	5	5							
Distance		E mm	30	30	30	30	30	30	35	35	35	35	35	35	35	35	35	35	35	35							
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																											
Number of stirrups		—	2	2	5	4	4	3	3	2	4	3	3	3	5	4	5	5	5	4							
Bar diameter		mm	12	12	10	10	10	12	12	12	12	12	12	12	12	12	12	12	12	12							
Spacing		mm	175	170	50	60	60	80	115	185	70	95	90	90	70	85	60	60	55	70							
Distance from anchor plate		F mm	50	50	50	50	50	50	55	55	55	55	55	55	55	55	55	55	55	55							
Minimum outer dimensions		B × B mm	245	235	220	205	195	190	270	260	240	225	210	205	295	280	260	250	235	225							
Centre spacing and edge distance																											
Minimum centre spacing		a _c , b _c mm	265	255	240	225	215	210	290	280	260	245	230	225	315	300	280	270	255	245							
Min. edge distance + c		a _e ¹ , b _e ¹ mm	125	120	110	105	100	95	135	130	120	115	105	105	150	140	130	125	120	115							
Square plate dimensions ²⁾																											
Side length		S _{SP} mm	185	185	185	185	180	180	190	190	190	190	185	185	205	205	205	200	195	195							
Thickness		T _{SP} mm	30	30	30	30	30	30	35	35	35	35	35	35	35	35	35	35	35	35							


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
Anchorage zone of CONA CMI SP
Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 56
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

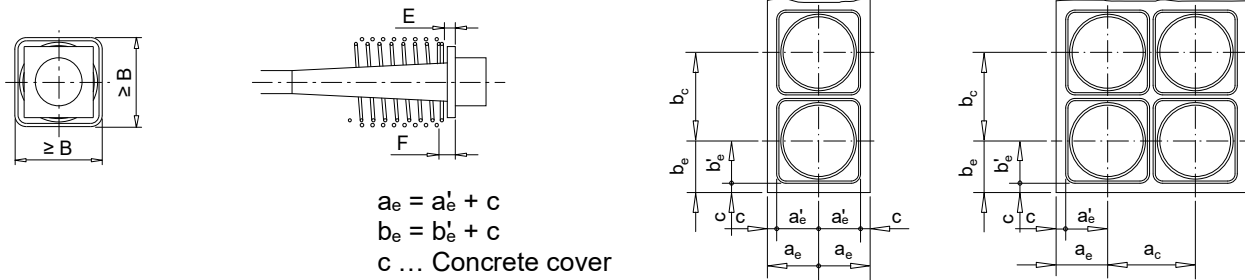

BBR VT CONA CMI SP			0806								0906								1206							
Strand arrangement																										
7-wire prestressing steel strand Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																										
Tendon																										
Cross-sectional area A _p mm²			1 200								1 350								1 800							
Char. value of maximum force F _{pk} kN			2 232								2 511								3 348							
Char. value of 0.1 % proof force F _{p0.1} kN			1 968								2 214								2 952							
Max. prestressing force 0.90 · F _{p0.1} kN			1 771								1 993								2 657							
Maximum overstressing force 0.95 · F _{p0.1} kN			1 870								2 103								2 804							
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																										
Minimum concrete strength																										
Cube f _{cm, 0, cube, 150} MPa			26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46						
Cylinder f _{cm, 0, cylinder, Ø 150} MPa			21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38						
Helix, ribbed reinforcing steel, R_e ≥ 500 MPa																										
Outer diameter			mm	280	270	230	215	205	200	295	280	240	225	215	215	325	320	290	280	270	260					
Bar diameter ²⁾			mm	10	10	12	12	12	12	10	10	10	10	12	12	12	12	12	14	14	14					
Length approximately			mm	280	258	237	237	237	212	280	280	260	260	262	212	327	327	312	289	289	239					
Pitch			mm	45	45	50	50	50	50	45	45	50	50	50	50	45	45	50	50	50	50					
Number of pitches			—	7	6.5	5.5	5.5	5.5	5	7	7	6	6	6	5	8	8	7	6.5	6.5	5.5					
Distance			E mm	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35					
Additional stirrup reinforcement, ribbed reinforcing steel, R_e ≥ 500 MPa																										
Number of stirrups			—	5	4	3	3	3	3	5	4	4	4	3	4	7	6	7	6	6	6					
Bar diameter ²⁾			mm	12	12	16	16	16	16	12	12	16	16	16	16	14	14	16	16	16	16					
Spacing			mm	70	90	120	110	105	100	75	75	90	85	110	75	55	55	55	60	60	55					
Distance from anchor plate			F mm	55	55	55	55	55	55	55	55	55	55	55	55	55	55	55	55	55	55					
Minimum outer dimensions			B × B mm	315	300	280	265	250	240	330	320	295	280	265	255	385	375	345	325	310	300					
Centre spacing and edge distance																										
Minimum centre spacing			a _c , b _c mm	335	320	300	285	270	260	355	340	315	300	285	275	410	395	365	345	330	320					
Min. edge distance + c			a _e ', b _e ' mm	160	150	140	135	125	120	170	160	150	140	135	130	195	190	175	165	155	150					
Square plate dimensions ³⁾																										
Side length			S _{SP} mm	225	225	225	220	215	215	255	255	250	245	240	240	265	265	265	260	255	250					
Thickness			T _{SP} mm	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35	35					

¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.

²⁾ Bar diameter of 14 mm can be replaced by 16 mm.


³⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
Anchorage zone of CONA CMI SP
Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 57
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

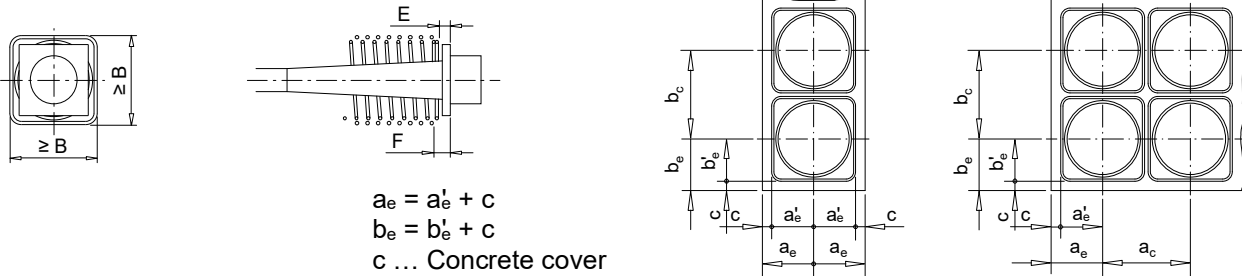

BBR VT CONA CMI SP			1306							1506							1606										
Strand arrangement																											
7-wire prestressing steel strand Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																											
Tendon																											
Cross-sectional area		A _p	mm ²	1 950							2 250							2 400									
Char. value of maximum force		F _{pk}	kN	3 627							4 185							4 464									
Char. value of 0.1 % proof force		F _{p0.1}	kN	3 198							3 690							3 936									
Max. prestressing force		0.90 · F _{p0.1}	kN	2 878							3 321							3 542									
Maximum overstressing force		0.95 · F _{p0.1}	kN	3 038							3 506							3 739									
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																											
Minimum concrete strength																											
Cube		f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46						
Cylinder		f _{cm, 0, cylinder, ∅ 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38						
Helix, ribbed reinforcing steel, R_e ≥ 500 MPa																											
Outer diameter		mm	340	330	305	290	280	270	370	350	325	300	290	280	390	370	340	330	310	310							
Bar diameter ²⁾		mm	12	12	12	14	14	14	14	14	14	14	14	14	14	14	14	14	14	14							
Length approximately		mm	350	327	312	314	289	264	389	364	339	339	314	289	389	389	364	339	339	289							
Pitch		mm	45	45	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50							
Number of pitches		—	8.5	8	7	7	6.5	6	8.5	8	7.5	7.5	7	6.5	8.5	8.5	8	7.5	7.5	6.5							
Distance		E mm	40	40	40	40	40	40	45	45	45	45	45	45	45	45	45	45	45	45							
Additional stirrup reinforcement, ribbed reinforcing steel, R_e ≥ 500 MPa																											
Number of stirrups		—	7	6	6	6	6	6	7	6	6	6	6	6	7	6	7	6	6	7							
Bar diameter ²⁾		mm	14	14	16	16	16	16	14	14	16	16	16	16	14	14	16	16	16	16							
Spacing		mm	65	65	65	65	60	60	70	70	70	70	65	65	70	70	60	70	65	55							
Distance from anchor plate		F mm	60	60	60	60	60	60	65	65	65	65	65	65	65	65	65	65	65	65							
Minimum outer dimensions		B × B mm	405	390	360	340	320	310	435	420	390	370	350	340	450	435	400	380	360	350							
Centre spacing and edge distance																											
Minimum centre spacing		a _c , b _c	mm	425	410	380	360	340	330	455	440	410	390	370	360	470	455	420	400	380	370						
Min. edge distance + c		a _e ¹ , b _e ¹	mm	205	195	180	170	160	155	220	210	195	185	175	170	225	220	200	190	180	175						
Square plate dimensions ³⁾																											
Side length		S _{SP}	mm	285	285	280	275	270	270	320	320	315	310	305	300	330	330	325	320	315	305						
Thickness		T _{SP}	mm	40	40	40	40	40	40	45	45	45	45	45	45	45	45	45	45	45	45						


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ Bar diameter of 14 mm can be replaced by 16 mm.
³⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
 Anchorage zone of CONA CMI SP
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 58
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

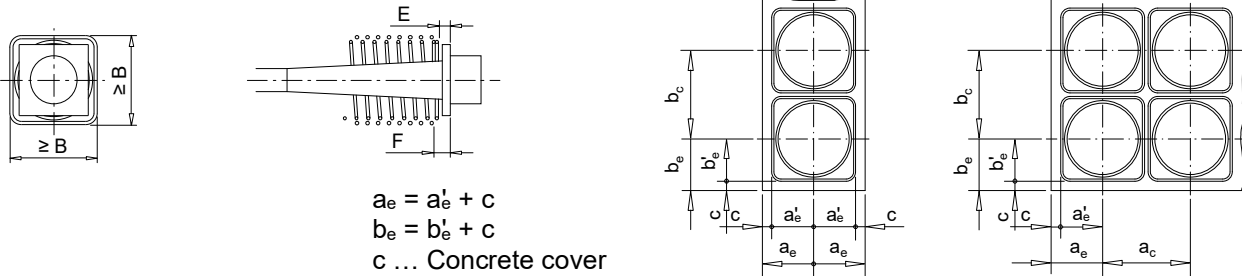

BBR VT CONA CMI SP			1906							2206							2406						
Strand arrangement																							
7-wire prestressing steel strand																							
Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																							
Tendon																							
Cross-sectional area	A _p	mm²	2 850							3 300							3 600						
Char. value of maximum force	F _{pk}	kN	5 301							6 138							6 696						
Char. value of 0.1 % proof force	F _{p0.1}	kN	4 674							5 412							5 904						
Max. prestressing force	0.90 · F _{p0.1}	kN	4 207							4 871							5 314						
Maximum overstressing force	0.95 · F _{p0.1}	kN	4 440							5 141							5 609						
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																							
Minimum concrete strength																							
Cube	f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46			
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38			
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																							
Outer diameter	mm	435	410	380	350	340	340	460	430	400	360	350	350	480	460	410	370	360	360				
Bar diameter	mm	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16				
Length approximately	mm	391	391	391	366	341	291	441	441	416	391	366	316	466	441	416	416	391	341				
Pitch	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50				
Number of pitches	—	8.5	8.5	8.5	8	7.5	6.5	9.5	9.5	9	8.5	8	7	10	9.5	9	9	8.5	7.5				
Distance	E mm	50	50	50	45	45	45	55	55	55	55	55	55	55	55	55	55	55	55				
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																							
Number of stirrups	—	7	6	9	8	7	7	7	6	9	8	8	7	7	6	9	8	8	7				
Bar diameter ³⁾	mm	14	16	16	16	16	16	16	16	16	16	16	16	20	20	20	20	20	20				
Spacing	mm	70	85	50	55	60	55	80	80	55	60	55	55	90	100	70	70	70	80				
Distance from anchor plate	F mm	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75				
Minimum outer dimensions	B × B mm	490	470	435	415	395	385	530	510	470	445	425	415	550	530	495	465	445	435				
Centre spacing and edge distance																							
Minimum centre spacing	a _c , b _c	mm	510	490	455	435	415	405	550	530	490	465	445	435	575	550	515	485	465	455			
Min. edge distance + c	a _e ¹ , b _e ¹	mm	245	235	220	210	200	195	265	255	235	225	215	210	280	265	250	235	225	220			
Square plate dimensions ²⁾																							
Side length	S _{SP}	mm	340	340	335	325	320	310	370	370	365	355	345	345	390	390	385	375	370	370			
Thickness	T _{SP}	mm	50	50	50	45	45	45	55	55	55	55	55	55	55	55	55	55	55	55			


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1860 MPa may also be used.
²⁾ Bar diameter of 14 mm can be replaced by 16 mm.
³⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.



Internal Post-tensioning System
 Anchorage zone of CONA CMI SP
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 59
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

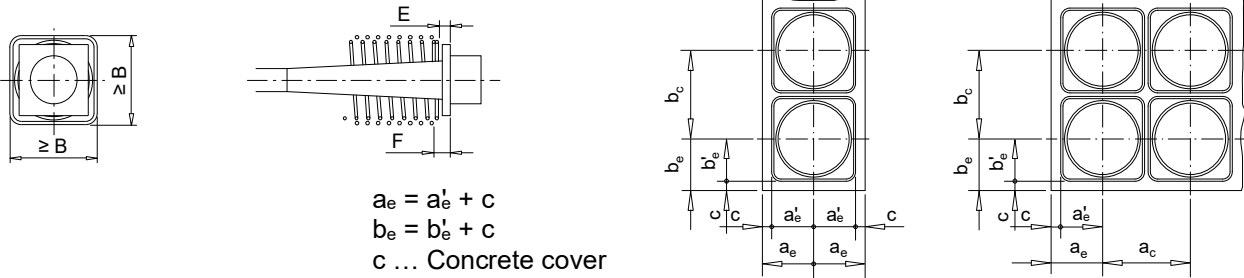

BBR VT CONA CMI SP	2506							2706							3106												
Strand arrangement																											
7-wire prestressing steel strand Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																											
Tendon																											
Cross-sectional area	A _p	mm ²	3 750							4 050							4 650										
Char. value of maximum force	F _{pk}	kN	6 975							7 533							8 649										
Char. value of 0.1 % proof force	F _{p0.1}	kN	6 150							6 642							7 626										
Max. prestressing force	0.90 · F _{p0.1}	kN	5 535							5 978							6 863										
Maximum overstressing force	0.95 · F _{p0.1}	kN	5 843							6 310							7 245										
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																											
Minimum concrete strength																											
Cube	f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46							
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38							
Helix, ribbed reinforcing steel, R_e ≥ 500 MPa																											
Outer diameter	mm	500	480	420	380	370	370	520	500	450	400	390	380	560	540	480	430	430	430								
Bar diameter	mm	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16								
Length approximately	mm	466	466	441	441	391	366	491	491	441	441	416	391	516	516	466	466	416	391								
Pitch	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50								
Number of pitches	—	10	10	9.5	9.5	8.5	8	10.5	10.5	9.5	9.5	9	8.5	11	11	10	10	9	8.5								
Distance	E mm	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60								
Additional stirrup reinforcement, ribbed reinforcing steel, R_e ≥ 500 MPa																											
Number of stirrups	—	7	6	9	8	8	6	6	5	7	6	6	6	8	7	10	9	8	8								
Bar diameter	mm	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20								
Spacing	mm	100	100	70	70	70	80	100	100	80	90	85	70	80	95	60	65	70	65								
Distance from anchor plate	F mm	80	80	80	80	80	80	80	80	80	80	80	80	80	80	80	80	80	80								
Minimum outer dimensions	B × B mm	565	545	500	475	450	440	585	565	520	495	470	460	630	605	560	535	515	500								
Centre spacing and edge distance																											
Minimum centre spacing	a _c , b _c	mm	585	565	520	495	470	460	605	585	540	515	490	480	650	625	580	555	535								
Min. edge distance + c	a _e ^a , b _e ^a	mm	285	275	250	240	225	220	295	285	260	250	235	230	315	305	280	270	260								
Square plate dimensions ²⁾																											
Side length	S _{SP}	mm	405	405	405	395	385	385	415	415	410	400	395	395	440	440	435	425	420								
Thickness	T _{SP}	mm	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60	60								


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
 Anchorage zone of CONA CMI SP
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 60
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

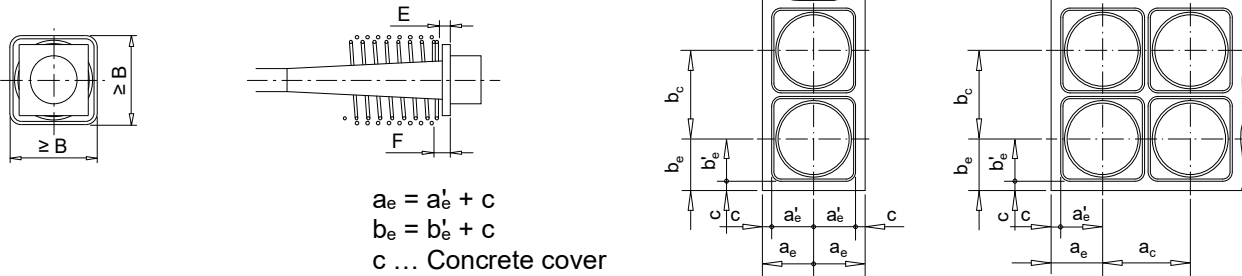

BBR VT CONA CMI SP		3706						4206						4306							
Strand arrangement																					
7-wire prestressing steel strand																					
Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																					
Tendon																					
Cross-sectional area	A _p	mm ²	5 550						6 300						6 450						
Char. value of maximum force	F _{pk}	kN	10 323						11 718						11 997						
Char. value of 0.1 % proof force	F _{p0.1}	kN	9 102						10 332						10 578						
Max. prestressing force	0.90 · F _{p0.1}	kN	8 192						9 299						9 520						
Maximum overstressing force	0.95 · F _{p0.1}	kN	8 647						9 815						10 049						
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																					
Minimum concrete strength																					
Cube	f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46	
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38	
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																					
Outer diameter	mm	620	620	620	620	620	620	660	660	660	660	660	660	670	670	670	670	670	670	670	
Bar diameter	mm	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	16	
Length approximately	mm	566	566	566	566	566	566	616	616	616	616	616	616	666	666	666	666	666	666	666	
Pitch	mm	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	
Number of pitches	—	12	12	12	12	12	12	13	13	13	13	13	13	14	14	14	14	14	14	14	
Distance	E mm	70	70	70	70	70	70	75	75	75	75	75	75	75	75	75	75	75	75	75	
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																					
Number of stirrups	—	11	11	11	11	11	11	11	11	11	11	11	11	11	11	11	11	11	11	11	
Bar diameter	mm	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	20	
Spacing	mm	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	75	
Distance from anchor plate	F mm	90	90	90	90	90	90	95	95	95	95	95	95	95	95	95	95	95	95	95	
Minimum outer dimensions	B × B mm	695	695	695	695	695	695	745	745	745	745	745	745	755	755	755	755	755	755	755	
Centre spacing and edge distance																					
Minimum centre spacing	a _c , b _c	mm	715	715	715	715	715	715	765	765	765	765	765	765	775	775	775	775	775	775	
Min. edge distance + c	a _e ', b _e '	mm	350	350	350	350	350	350	375	375	375	375	375	375	380	380	380	380	380	380	
Square plate dimensions ²⁾																					
Side length	S _{SP}	mm	480	480	480	480	480	480	510	510	510	510	510	510	520	520	520	520	520	520	
Thickness	T _{SP}	mm	70	70	70	70	70	70	75	75	75	75	75	75	75	75	75	75	75	75	


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1860 MPa may also be used.
²⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.






Internal Post-tensioning System
 Anchorage zone of CONA CMI SP
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 61
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Stressing and fixed anchorage or coupler – Centre spacing and edge distance

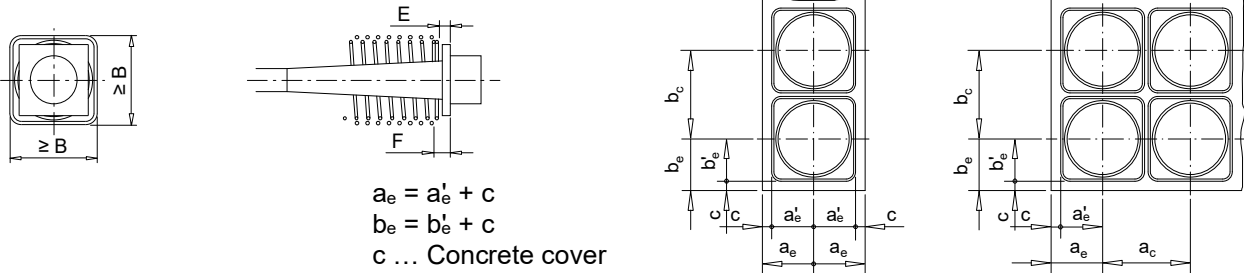

BBR VT CONA CMI SP		4806						5506						6106							
Strand arrangement																					
7-wire prestressing steel strand																					
Nominal diameter 15.7 mm ... Nominal cross-sectional area 150 mm² ... Maximum characteristic tensile strength 1 860 MPa ¹⁾																					
Tendon																					
Cross-sectional area	A _p	mm ²	7 200						8 250						9 150						
Char. value of maximum force	F _{pk}	kN	13 392						15 345						17 019						
Char. value of 0.1 % proof force	F _{p0.1}	kN	11 808						13 530						15 006						
Max. prestressing force	0.90 · F _{p0.1}	kN	10 627						12 177						13 505						
Maximum overstressing force	0.95 · F _{p0.1}	kN	11 218						12 854						14 256						
Minimum concrete strength / Helix / Additional reinforcement / Centre spacing and edge distance / Square plate dimensions																					
Minimum concrete strength																					
Cube	f _{cm, 0, cube, 150}	MPa	26	28	34	38	43	46	26	28	34	38	43	46	26	28	34	38	43	46	
Cylinder	f _{cm, 0, cylinder, Ø 150}	MPa	21	23	28	31	35	38	21	23	28	31	35	38	21	23	28	31	35	38	
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																					
Outer diameter	mm	720	720	720	720	720	720	790	790	790	790	790	790	860	860	860	860	860	860	860	
Bar diameter	mm	20	20	20	20	20	20	25	25	25	25	25	25	25	25	25	25	25	25	25	
Length approximately	mm	860	860	860	860	860	860	940	940	940	940	940	940	985	985	985	985	985	985	985	
Pitch	mm	60	60	60	60	60	60	70	70	70	70	70	70	60	60	60	60	60	60	60	
Number of pitches	—	15	15	15	15	15	15	14	14	14	14	14	14	17	17	17	17	17	17	17	
Distance	E mm	80	80	80	80	80	80	90	90	90	90	90	90	90	90	90	90	90	90	90	
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																					
Number of stirrups	—	11	11	11	11	11	11	12	12	12	12	12	12	13	13	13	13	13	13	13	
Bar diameter	mm	20	20	20	20	20	20	16	16	16	16	16	16	16	16	16	16	16	16	16	
Spacing	mm	75	75	75	75	75	75	70	70	70	70	70	70	70	70	70	70	70	70	70	
Distance from anchor plate	F mm	100	100	100	100	100	100	110	110	110	110	110	110	110	110	110	110	110	110	110	
Minimum outer dimensions	B × B mm	810	810	810	810	810	810	885	885	885	885	885	885	940	940	940	940	940	940	940	
Centre spacing and edge distance																					
Minimum centre spacing	a _c , b _c	mm	830	830	830	830	830	905	905	905	905	905	905	960	960	960	960	960	960	960	
Min. edge distance + c	a _e ^a , b _e ^a	mm	405	405	405	405	405	445	445	445	445	445	445	470	470	470	470	470	470	470	
Square plate dimensions ²⁾																					
Side length	S _{SP}	mm	550	550	550	550	550	595	595	595	595	595	595	620	620	620	620	620	620	620	
Thickness	T _{SP}	mm	80	80	80	80	80	90	90	90	90	90	90	90	90	90	90	90	90	90	


¹⁾ Prestressing steel strand with nominal diameter of 15.3 mm, cross-sectional area of 140 mm² or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ The square plate dimensions are minimum values, therefore larger or thicker plates may be used.



Internal Post-tensioning System
 Anchorage zone of CONA CMI SP
 Minimum concrete strength – Helix and stirrups as additional reinforcement – Centre spacing and edge distance – Square plate dimensions

Annex 62
 of European Technical Assessment
ETA-06/0147 of 26.06.2025

Modification of centre spacing and edge distance

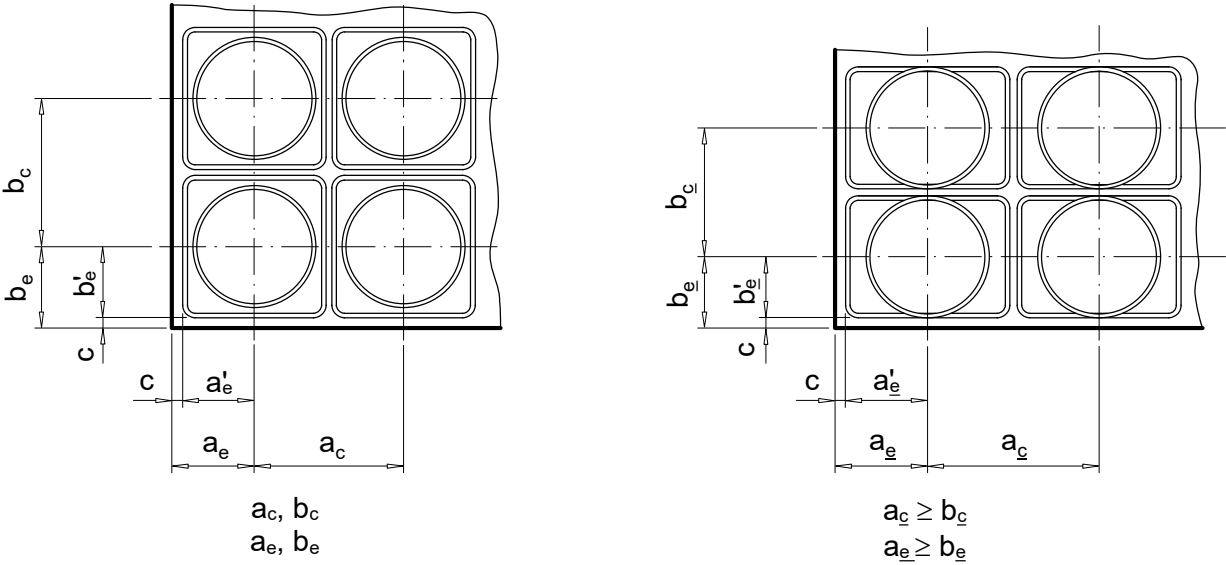

Modification of centre spacing and edge distance are in accordance with Clause 1.8.

$$b_c \geq \begin{cases} 0.85 \cdot b_c \\ \text{and} \\ \geq \text{Helix, outside diameter } ^1) \end{cases}$$

$$a_c \geq \frac{A_c}{b_c}$$

$$A_c = a_c \cdot b_c \leq a_c \cdot b_c$$

Corresponding edge distances

$$a_e = \frac{a_c}{2} - 10 \text{ mm} + c$$

and

$$b_e = \frac{b_c}{2} - 10 \text{ mm} + c$$



c..... Concrete cover

¹⁾ Except the dimensions of helix, the outer dimensions of the additional stirrup reinforcement are adjusted accordingly. Further modifications of reinforcement are in accordance with the Clauses 1.12.8 and 2.2.3.5.




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only



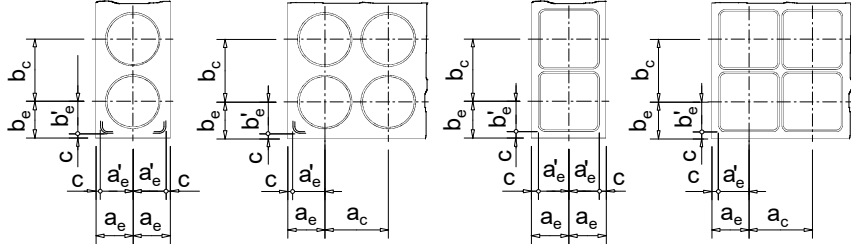

Stirrups only



$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A

Technical data of anchorages																	
BBR VT CONA CMI BT			0206								0306						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area		A _p	mm ²	300								450					
Char. maximum force		F _{pk}	kN	558								837					
Char. 0.1 % proof force		F _{p0.1}	kN	492								738					
Max. prestressing force		0.90 · F _{p0.1}	kN	443								664					
Max. overstressing force		0.95 · F _{p0.1}	kN	467								701					
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube		f _{cm, 0}	MPa	38	43	53	60	38	43	53	60						
Cylinder		f _{cm, 0}	MPa	31	35	43	50	31	35	43	50						
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter		∅ A	mm	155	—	155	—	155	—	155	—	155	—	155	—	155	—
Bar diameter			mm	8	—	8	—	8	—	8	—	8	—	8	—	8	—
Length, approximately			mm	153	—	153	—	153	—	153	—	153	—	153	—	153	—
Pitch			mm	45	—	45	—	45	—	45	—	45	—	45	—	45	—
Number of pitches			—	4	—	4	—	4	—	4	—	4	—	4	—	4	—
Distance		E	mm	15	—	15	—	15	—	15	—	15	—	15	—	15	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups			—	—	5	—	5	—	5	—	5	—	5	—	5	—	5
Bar diameter			mm	—	10	—	10	—	10	—	10	—	10	—	10	—	10
Spacing			mm	—	45	—	45	—	45	—	45	—	45	—	45	—	45
Distance		F	mm	—	15	—	15	—	15	—	15	—	15	—	15	—	15
Minimum outer dimensions		B × B	mm	—	160	—	160	—	160	—	160	—	160	—	160	—	160
Centre spacing and edge distance																	
Minimum centre spacing		a _c , b _c	mm	180	180	180	180	180	180	180	180	180	180	180	180	180	180
Min. edge distance + c		a _e ¹ , b _e ¹	mm	80	80	80	80	80	80	80	80	80	80	80	80	80	80

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup
reinforcement – Centre spacing and edge distance

Annex 64
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only



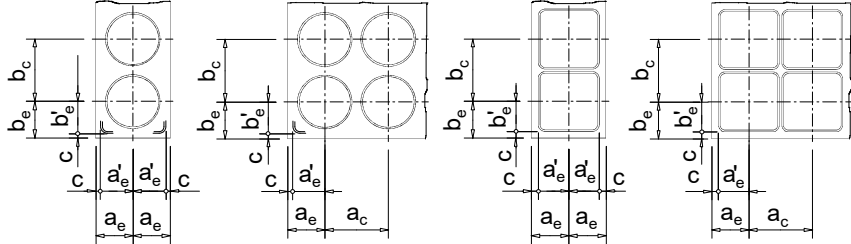

Stirrups only



$a_e = a'_e + c$
 $b_e = b'_e + c$
c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate E

Technical data of anchorages																	
BBR VT CONA CMI BT			0206								0306						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area		A _p	mm ²	300								450					
Char. maximum force		F _{pk}	kN	558								837					
Char. 0.1 % proof force		F _{p0.1}	kN	492								738					
Max. prestressing force		0.90 · F _{p0.1}	kN	443								664					
Max. overstressing force		0.95 · F _{p0.1}	kN	467								701					
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube		f _{cm, 0}	MPa	38	43	53	60	38	43	53	60	38	43	53	60	38	43
Cylinder		f _{cm, 0}	MPa	31	35	43	50	31	35	43	50	31	35	43	50	31	35
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter		∅ A	mm	170	—	170	—	170	—	170	—	170	—	170	—	170	—
Bar diameter			mm	8	—	8	—	8	—	8	—	8	—	8	—	8	—
Length, approximately			mm	153	—	153	—	153	—	153	—	153	—	153	—	153	—
Pitch			mm	45	—	45	—	45	—	45	—	45	—	45	—	45	—
Number of pitches			—	4	—	4	—	4	—	4	—	4	—	4	—	4	—
Distance		E	mm	15	—	15	—	15	—	15	—	15	—	15	—	15	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups			—	—	5	—	5	—	5	—	5	—	5	—	5	—	5
Bar diameter			mm	—	10	—	10	—	10	—	10	—	10	—	10	—	10
Spacing			mm	—	45	—	45	—	45	—	45	—	45	—	45	—	45
Distance		F	mm	—	15	—	15	—	15	—	15	—	15	—	15	—	15
Minimum outer dimensions		B × B	mm	—	175	—	175	—	175	—	175	—	175	—	175	—	175
Centre spacing and edge distance																	
Minimum centre spacing		a _c , b _c	mm	195	195	195	195	195	195	195	195	195	195	195	195	195	195
Min. edge distance + c		a _e ¹ , b _e ¹	mm	90	90	90	90	90	90	90	90	90	90	90	90	90	90

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup
reinforcement – Centre spacing and edge distance

Annex 65
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

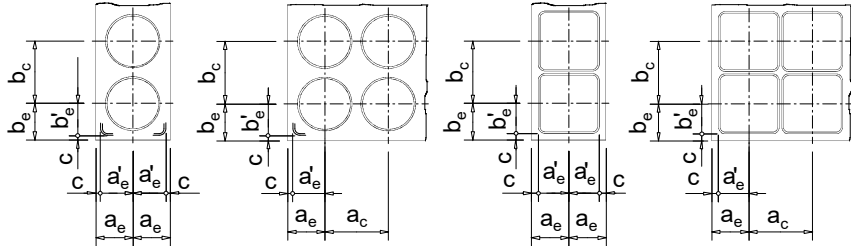

$a_e = a'_e + c$
 $b_e = b'_e + c$
c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A

Technical data of anchorages																	
BBR VT CONA CMI BT			0406								0506						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	600								750						
Char. maximum force	F _{pk}	kN	1 116								1 395						
Char. 0.1 % proof force	F _{p0.1}	kN	984								1 230						
Max. prestressing force	0.90 · F _{p0.1}	kN	886								1 107						
Max. overstressing force	0.95 · F _{p0.1}	kN	935								1 169						
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0}	MPa	38	43	53	60	38	43	53	60	38	43	53	60	38	43	53
Cylinder	f _{cm, 0}	MPa	31	35	43	50	31	35	43	50	31	35	43	50	31	35	43
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter	∅ A	mm	175	—	170	—	160	—	160	—	205	—	200	—	200	—	200
Bar diameter		mm	10	—	10	—	10	—	10	—	10	—	10	—	10	—	10
Length, approximately		mm	203	—	158	—	158	—	158	—	203	—	203	—	180	—	180
Pitch		mm	45	—	45	—	45	—	45	—	45	—	45	—	45	—	45
Number of pitches		—	5	—	5	—	4	—	4	—	5	—	5	—	5	—	5
Distance	E	mm	15	—	15	—	15	—	15	—	18	—	18	—	18	—	18
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups		—	—	6	—	5	—	5	—	5	—	6	—	6	—	6	—
Bar diameter		mm	—	12	—	12	—	12	—	12	—	12	—	12	—	12	—
Spacing		mm	—	45	—	45	—	45	—	45	—	45	—	45	—	45	—
Distance	F	mm	—	15	—	15	—	15	—	15	—	18	—	18	—	18	—
Minimum outer dimensions	B × B	mm	—	180	—	170	—	170	—	160	—	215	—	210	—	205	—
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	200	200	190	190	190	180	180	235	235	230	230	225	225	225	225
Min. edge distance + c	a _e ¹ , b _e ¹	mm	90	90	85	85	85	85	80	80	110	110	105	105	105	105	105

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup
reinforcement – Centre spacing and edge distance

Annex 66
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

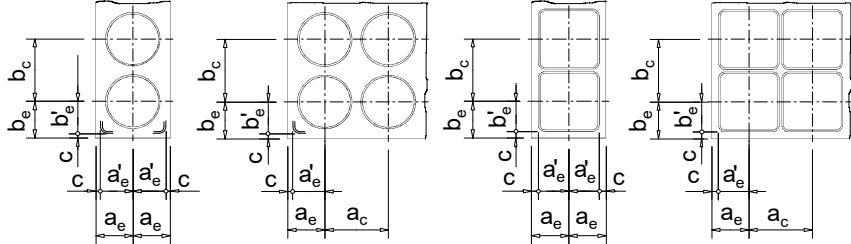

$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate E

Technical data of anchorages																	
BBR VT CONA CMI BT			0406								0506						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	600								750						
Char. maximum force	F _{pk}	kN	1 116								1 395						
Char. 0.1 % proof force	F _{p0.1}	kN	984								1 230						
Max. prestressing force	0.90 · F _{p0.1}	kN	886								1 107						
Max. overstressing force	0.95 · F _{p0.1}	kN	935								1 169						
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0}	MPa	38	43	53	60	38	43	53	60	38	43	53	60	38	43	53
Cylinder	f _{cm, 0}	MPa	31	35	43	50	31	35	43	50	31	35	43	50	31	35	43
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter	∅ A	mm	175	—	175	—	175	—	175	—	205	—	200	—	200	—	200
Bar diameter		mm	10	—	10	—	10	—	10	—	10	—	10	—	10	—	10
Length, approximately		mm	203	—	158	—	158	—	158	—	203	—	203	—	180	—	180
Pitch		mm	45	—	45	—	45	—	45	—	45	—	45	—	45	—	45
Number of pitches		—	5	—	5	—	4	—	4	—	5	—	5	—	5	—	5
Distance	E	mm	15	—	15	—	15	—	15	—	18	—	18	—	18	—	18
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups		—	—	6	—	5	—	5	—	5	—	6	—	6	—	6	—
Bar diameter		mm	—	12	—	12	—	12	—	12	—	12	—	12	—	12	—
Spacing		mm	—	45	—	45	—	45	—	45	—	45	—	45	—	45	—
Distance	F	mm	—	15	—	15	—	15	—	15	—	18	—	18	—	18	—
Minimum outer dimensions	B × B	mm	—	180	—	180	—	180	—	180	—	215	—	210	—	205	—
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	200	200	200	200	200	200	200	200	235	235	230	230	225	225	225
Min. edge distance + c	a _e ¹ , b _e ¹	mm	90	90	90	90	90	90	90	90	110	110	105	105	105	105	105

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 67
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

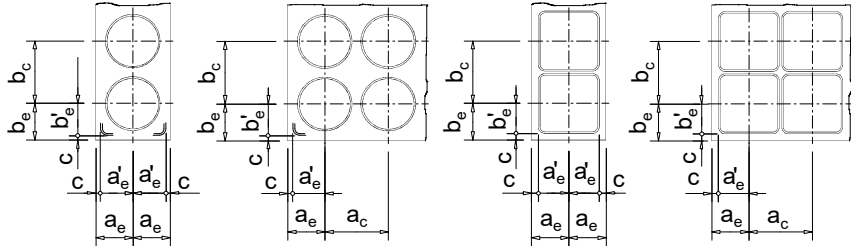

$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																	
BBR VT CONA CMI BT			0606								0706						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	900								1 050						
Char. maximum force	F _{pk}	kN	1 674								1 953						
Char. 0.1 % proof force	F _{p0.1}	kN	1 476								1 722						
Max. prestressing force	0.90 · F _{p0.1}	kN	1 328								1 550						
Max. oversteressing force	0.95 · F _{p0.1}	kN	1 402								1 636						
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0}	MPa	38	43	53	60	38	43	53	60	38	43	53	60	38	43	53
Cylinder	f _{cm, 0}	MPa	31	35	43	50	31	35	43	50	31	35	43	50	31	35	43
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter	∅ A	mm	200	—	200	—	200	—	200	—	205	—	205	—	205	—	210
Bar diameter		mm	10	—	10	—	10	—	10	—	12	—	12	—	12	—	10
Length, approximately		mm	203	—	203	—	180	—	180	—	230	—	207	—	207	—	248
Pitch		mm	45	—	45	—	45	—	45	—	45	—	45	—	45	—	45
Number of pitches		—	5	—	5	—	4.5	—	4.5	—	5.5	—	5	—	5	—	6
Distance	E	mm	18	—	18	—	18	—	18	—	18	—	18	—	18	—	20
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups		—	—	6	—	6	—	6	—	6	—	7	—	6	—	6	—
Bar diameter ²⁾		mm	—	12	—	12	—	12	—	12	—	14	—	14	—	14	—
Spacing		mm	—	45	—	45	—	45	—	45	—	45	—	45	—	45	—
Distance	F	mm	—	18	—	18	—	18	—	18	—	18	—	18	—	18	—
Minimum outer dimensions	B × B	mm	—	225	—	215	—	205	—	205	—	250	—	220	—	210	—
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	245	245	235	235	225	225	225	225	270	270	240	240	230	230	240
Min. edge distance + c	a _e ¹ , b _e ¹	mm	115	115	110	110	105	105	105	105	125	125	110	110	105	105	110

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ Bar diameter of 14 mm can be replaced by 16 mm.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 68
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

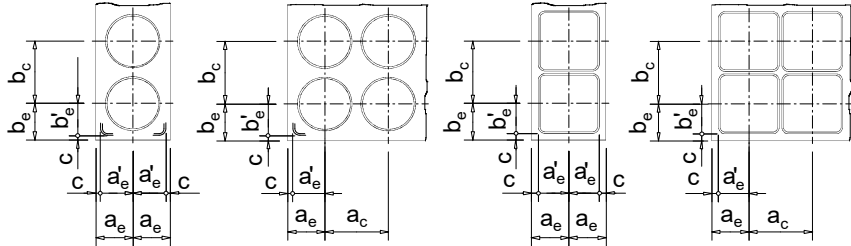

$a_e = a'_e + c$
 $b_e = b'_e + c$
c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																		
BBR VT CONA CMI BT			0806								0906							
Strand arrangement																		
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																		
Tendon																		
Cross-sectional area	A _p	mm ²	1 200								1 350							
Char. maximum force	F _{pk}	kN	2 232								2 511							
Char. 0.1 % proof force	F _{p0.1}	kN	1 968								2 214							
Max. prestressing force	0.90 · F _{p0.1}	kN	1 771								1 993							
Max. overstressing force	0.95 · F _{p0.1}	kN	1 870								2 103							
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																		
Minimum concrete strength																		
Cube	f _{cm, 0}	MPa	38	43	53	60	38	43	53	60	38	43	53	60	38	43	53	60
Cylinder	f _{cm, 0}	MPa	31	35	43	50	31	35	43	50	31	35	43	50	31	35	43	50
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																		
Outer diameter	∅ A	mm	245	—	235	—	235	—	230	—	275	—	275	—	275	—	275	—
Bar diameter		mm	12	—	12	—	12	—	12	—	12	—	12	—	12	—	12	—
Length, approximately		mm	252	—	230	—	227	—	227	—	270	—	248	—	223	—	233	—
Pitch		mm	45	—	45	—	50	—	50	—	45	—	45	—	50	—	55	—
Number of pitches		—	6	—	5.5	—	5	—	5	—	6.5	—	6	—	5	—	4.5	—
Distance	E	mm	20	—	20	—	20	—	20	—	20	—	20	—	20	—	20	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																		
Number of stirrups		—	—	7	—	6	—	6	—	6	—	7	—	6	—	6	—	6
Bar diameter		mm	—	16	—	16	—	16	—	16	—	16	—	16	—	16	—	16
Spacing		mm	—	50	—	50	—	50	—	50	—	50	—	50	—	50	—	50
Distance	F	mm	—	20	—	20	—	20	—	20	—	20	—	20	—	20	—	20
Minimum outer dimensions	B × B	mm	—	260	—	250	—	250	—	240	—	285	—	285	—	285	—	285
Centre spacing and edge distance																		
Minimum centre spacing	a _c , b _c	mm	280	280	270	270	270	270	260	260	305	305	305	305	305	305	305	305
Min. edge distance + c	a _e ['] , b _e [']	mm	130	130	125	125	125	125	120	120	145	145	145	145	145	145	145	145

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup
reinforcement – Centre spacing and edge distance

Annex 69
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

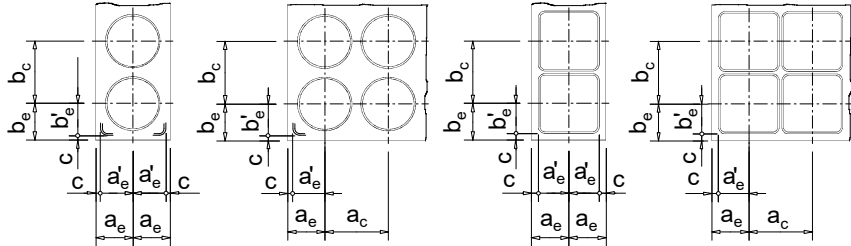

$a_e = a'_e + c$
 $b_e = b'_e + c$
c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																		
BBR VT CONA CMI BT			1206								1306							
Strand arrangement																		
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																		
Tendon																		
Cross-sectional area	A _p	mm ²	1 800								1 950							
Char. maximum force	F _{pk}	kN	3 348								3 627							
Char. 0.1 % proof force	F _{p0.1}	kN	2 952								3 198							
Max. prestressing force	0.90 · F _{p0.1}	kN	2 657								2 878							
Max. overstressing force	0.95 · F _{p0.1}	kN	2 804								3 038							
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																		
Minimum concrete strength																		
Cube	f _{cm, 0}	MPa	38		43		53		60		38		43		53		60	
Cylinder	f _{cm, 0}	MPa	31		35		43		50		31		35		43		50	
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																		
Outer diameter	∅ A	mm	280	—	280	—	280	—	280	—	300	—	300	—	300	—	300	—
Bar diameter ²⁾		mm	14	—	14	—	14	—	14	—	14	—	14	—	14	—	14	—
Length, approximately		mm	302	—	279	—	257	—	282	—	302	—	302	—	279	—	282	—
Pitch		mm	45	—	45	—	45	—	50	—	45	—	45	—	45	—	50	—
Number of pitches		—	7	—	6.5	—	6	—	6	—	7	—	7	—	6.5	—	6	—
Distance	E	mm	20	—	20	—	20	—	20	—	23	—	23	—	23	—	23	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																		
Number of stirrups		—	—	—	7	—	6	—	6	—	6	—	—	7	—	7	—	7
Bar diameter		mm	—	—	20	—	20	—	20	—	20	—	—	20	—	20	—	20
Spacing		mm	—	—	55	—	55	—	55	—	55	—	—	55	—	55	—	55
Distance	F	mm	—	—	20	—	20	—	20	—	20	—	—	23	—	23	—	23
Minimum outer dimensions	B × B	mm	—	—	305	—	290	—	290	—	290	—	—	325	—	320	—	310
Centre spacing and edge distance																		
Minimum centre spacing	a _c , b _c	mm	325	325	310	310	310	310	310	310	345	345	340	340	330	330	330	330
Min. edge distance + c	a _e ¹ , b _e ¹	mm	155	155	145	145	145	145	145	145	165	165	160	160	155	155	155	155

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ Bar diameter of 14 mm can be replaced by 16 mm.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 70
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

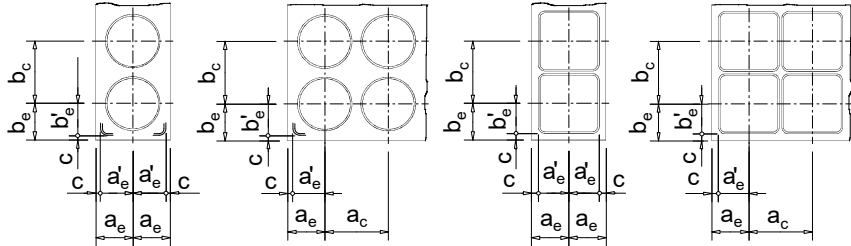

$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																	
BBR VT CONA CMI BT			1506								1606						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area	A _p	mm ²	2 250								2 400						
Char. maximum force	F _{pk}	kN	4 185								4 464						
Char. 0.1 % proof force	F _{p0.1}	kN	3 690								3 936						
Max. prestressing force	0.90 · F _{p0.1}	kN	3 321								3 542						
Max. overstressing force	0.95 · F _{p0.1}	kN	3 506								3 739						
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube	f _{cm, 0}	MPa	38		43		53		60		38		43		53		60
Cylinder	f _{cm, 0}	MPa	31		35		43		50		31		35		43		50
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter	∅ A	mm	320	—	320	—	320	—	320	—	320	—	320	—	320	—	320
Bar diameter ²⁾		mm	14	—	14	—	14	—	14	—	14	—	14	—	14	—	14
Length, approximately		mm	324	—	302	—	297	—	277	—	347	—	347	—	302	—	297
Pitch		mm	45	—	45	—	45	—	50	—	45	—	45	—	45	—	45
Number of pitches		—	7.5	—	7	—	7	—	6	—	8	—	8	—	7	—	7
Distance	E	mm	27	—	27	—	27	—	27	—	27	—	27	—	27	—	27
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups		—	—	7	—	7	—	7	—	7	—	8	—	8	—	7	—
Bar diameter		mm	—	20	—	20	—	20	—	20	—	20	—	20	—	20	—
Spacing		mm	—	55	—	55	—	55	—	55	—	55	—	55	—	55	—
Distance	F	mm	—	27	—	27	—	27	—	27	—	27	—	27	—	27	—
Minimum outer dimensions	B × B	mm	—	335	—	330	—	330	—	330	—	355	—	345	—	330	—
Centre spacing and edge distance																	
Minimum centre spacing	a _c , b _c	mm	355	355	350	350	350	350	350	350	375	375	365	365	350	350	350
Min. edge distance + c	a _e ¹ , b _e ¹	mm	170	170	165	165	165	165	165	165	180	180	175	175	165	165	165

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ Bar diameter of 14 mm can be replaced by 16 mm.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 71
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

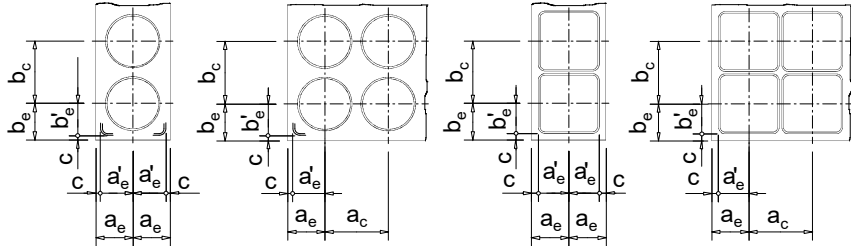

$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																	
BBR VT CONA CMI BT			1906									2206					
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area		A _p	mm ²	2 850									3 300				
Char. maximum force		F _{pk}	kN	5 301									6 138				
Char. 0.1 % proof force		F _{p0.1}	kN	4 674									5 412				
Max. prestressing force		0.90 · F _{p0.1}	kN	4 207									4 871				
Max. overstressing force		0.95 · F _{p0.1}	kN	4 440									5 141				
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube		f _{cm, 0}	MPa	38		43		53		60		38		43		53	60
Cylinder		f _{cm, 0}	MPa	31		35		43		50		31		35		43	50
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter		∅ A	mm	370	—	330	—	325	—	330	—	360	—	360	—	360	—
Bar diameter			mm	16	—	16	—	16	—	20	—	20	—	20	—	20	—
Length, approximately			mm	411	—	361	—	361	—	370	—	403	—	375	—	375	—
Pitch			mm	50	—	50	—	50	—	50	—	55	—	55	—	55	—
Number of pitches			—	9	—	7.5	—	7.5	—	7.5	—	7.5	—	7	—	7	—
Distance		E	mm	27	—	27	—	27	—	27	—	31	—	31	—	31	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups			—	—	8	—	8	—	8	—	8	—	9	—	9	—	9
Bar diameter			mm	—	20	—	20	—	20	—	20	—	20	—	20	—	20
Spacing			mm	—	55	—	55	—	50	—	50	—	50	—	50	—	45
Distance		F	mm	—	27	—	27	—	27	—	27	—	31	—	31	—	31
Minimum outer dimensions		B × B	mm	—	415	—	370	—	355	—	330	—	415	—	400	—	385
Centre spacing and edge distance																	
Minimum centre spacing		a _c , b _c	mm	435	435	390	390	375	375	360	350	435	435	420	420	405	405
Min. edge distance + c		a _e ¹ , b _e ¹	mm	210	210	185	185	180	180	170	165	210	210	200	200	195	195

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 72
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

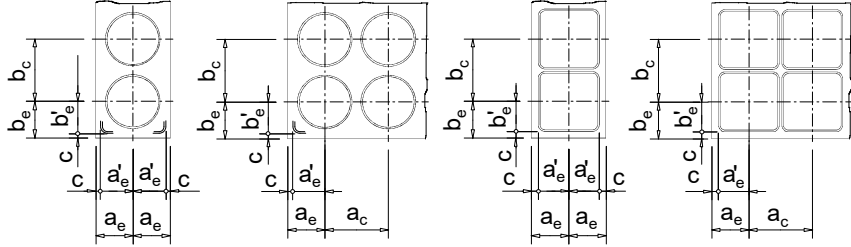

$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																		
BBR VT CONA CMI BT			2406								2506							
Strand arrangement																		
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																		
Tendon																		
Cross-sectional area	A _p	mm ²	3 600								3 750							
Char. maximum force	F _{pk}	kN	6 696								6 975							
Char. 0.1 % proof force	F _{p0.1}	kN	5 904								6 150							
Max. prestressing force	0.90 · F _{p0.1}	kN	5 314								5 535							
Max. oversteressing force	0.95 · F _{p0.1}	kN	5 609								5 843							
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																		
Minimum concrete strength																		
Cube	f _{cm, 0}	MPa	38		43		53		60		38		43		53		60	
Cylinder	f _{cm, 0}	MPa	31		35		43		50		31		35		43		50	
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																		
Outer diameter	∅ A	mm	375	—	375	—	375	—	385	—	410	—	410	—	410	—	410	—
Bar diameter		mm	20	—	20	—	20	—	20	—	20	—	20	—	20	—	20	—
Length, approximately		mm	430	—	430	—	405	—	386	—	465	—	465	—	366	—	366	—
Pitch		mm	55	—	55	—	60	—	55	—	60	—	60	—	60	—	60	—
Number of pitches		—	8	—	8	—	7	—	8	—	8	—	8	—	7	—	7	—
Distance	E	mm	32	—	32	—	32	—	32	—	35	—	35	—	35	—	35	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																		
Number of stirrups		—	—	10	—	9	—	9	—	9	—	10	—	10	—	9	—	9
Bar diameter		mm	—	20	—	20	—	20	—	20	—	20	—	20	—	20	—	20
Spacing		mm	—	50	—	50	—	50	—	50	—	50	—	50	—	50	—	50
Distance	F	mm	—	32	—	32	—	32	—	32	—	35	—	35	—	35	—	35
Minimum outer dimensions	B × B	mm	—	440	—	425	—	415	—	405	—	445	—	425	—	415	—	410
Centre spacing and edge distance																		
Minimum centre spacing	a _c , b _c	mm	460	460	445	445	435	435	425	425	465	465	445	445	435	435	430	430
Min. edge distance + c	a _e ', b _e '	mm	220	220	215	215	210	210	205	205	225	225	215	215	210	210	205	205

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup
reinforcement – Centre spacing and edge distance

Annex 73
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only





Stirrups only

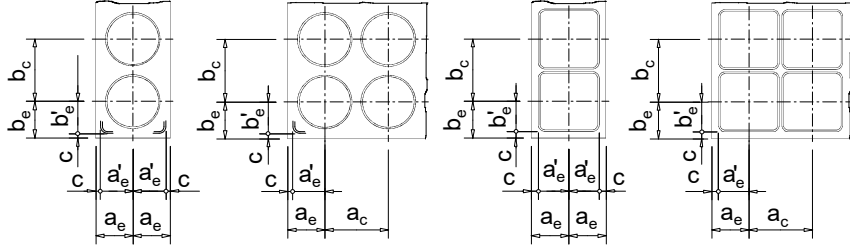

$a_e = a'_e + c$
 $b_e = b'_e + c$
c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages																	
BBR VT CONA CMI BT			2706								3106						
Strand arrangement																	
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm² Maximum characteristic tensile strength 1 860 MPa ¹⁾																	
Tendon																	
Cross-sectional area		A _p	mm ²	4 050								4 650					
Char. maximum force		F _{pk}	kN	7 533								8 649					
Char. 0.1 % proof force		F _{p0.1}	kN	6 642								7 626					
Max. prestressing force		0.90 · F _{p0.1}	kN	5 978								6 863					
Max. overstressing force		0.95 · F _{p0.1}	kN	6 310								7 245					
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																	
Minimum concrete strength																	
Cube		f _{cm, 0}	MPa	38		43		53		60		38		43		53	60
Cylinder		f _{cm, 0}	MPa	31		35		43		50		31		35		43	50
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Outer diameter		∅ A	mm	410	—	410	—	410	—	410	—	410	—	410	—	410	—
Bar diameter			mm	20	—	20	—	20	—	20	—	20	—	20	—	20	—
Length, approximately			mm	485	—	485	—	430	—	386	—	495	—	445	—	445	—
Pitch			mm	55	—	55	—	55	—	55	—	50	—	50	—	50	—
Number of pitches			—	9	—	9	—	8	—	8	—	10	—	9	—	9	—
Distance		E	mm	35	—	35	—	35	—	35	—	35	—	35	—	35	—
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																	
Number of stirrups			—	—	10	—	10	—	9	—	9	—	9	—	9	—	9
Bar diameter ²⁾			mm	—	20	—	20	—	20	—	20	—	24	—	24	—	24
Spacing			mm	—	50	—	50	—	50	—	50	—	60	—	60	—	55
Distance		F	mm	—	35	—	35	—	35	—	35	—	35	—	35	—	35
Minimum outer dimensions		B × B	mm	—	460	—	445	—	430	—	410	—	495	—	465	—	440
Centre spacing and edge distance																	
Minimum centre spacing		a _c , b _c	mm	480	480	465	465	450	450	430	430	515	515	485	485	460	460
Min. edge distance + c		a _e ', b _e '	mm	230	230	225	225	215	215	205	205	250	250	235	235	220	220

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used.
²⁾ Bar diameter of 24 mm can be replaced by 25 mm.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 74
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only



Stirrups only

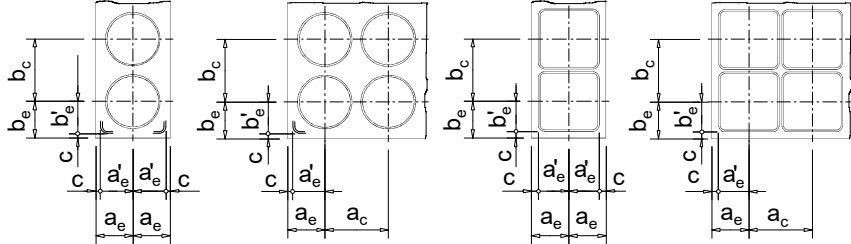


$$a_e = a'_e + c$$

$$b_e = b'_e + c$$

c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A and E

Technical data of anchorages									
BBR VT CONA CMI BT				3706					
Strand arrangement									
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm² – Maximum characteristic tensile strength 1 860 MPa ¹⁾									
Tendon									
Cross-sectional area	A _p	mm ²	5 550						
Char. maximum force	F _{pk}	kN	10 323						
Char. 0.1 % proof force	F _{p0.1}	kN	9 102						
Max. prestressing force	0.90 · F _{p0.1}	kN	8 192						
Max. oversteressing force	0.95 · F _{p0.1}	kN	8 647						
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance									
Minimum concrete strength									
Cube	f _{cm, 0}	MPa	38	43	53	60			
Cylinder	f _{cm, 0}	MPa	31	35	43	50			
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa									
Outer diameter	Ø A	mm	450	—	450	—	450	—	450
Bar diameter		mm	20	—	20	—	20	—	20
Length, approximately		mm	520	—	495	—	458	—	458
Pitch		mm	50	—	50	—	55	—	55
Number of pitches		—	10.5	—	10	—	8.5	—	8.5
Distance	E	mm	30	—	30	—	30	—	30
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa									
Number of stirrups		—	—	10	—	10	—	10	—
Bar diameter ²⁾		mm	—	24	—	24	—	24	—
Spacing		mm	—	55	—	55	—	55	—
Distance	F	mm	—	30	—	30	—	30	—
Minimum outer dimensions	B × B	mm	—	545	—	500	—	480	—
Centre spacing and edge distance									
Minimum centre spacing	a _c , b _c	mm	565	565	520	520	500	500	490
Min. edge distance + c	a _e ¹ , b _e ¹	mm	275	275	250	250	240	240	235

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used. ²⁾ Bar diameter of 24 mm can be replaced by 25 mm.





Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance

Annex 75
of European Technical Assessment
ETA-06/0147 of 26.06.2025




Stressing and fixed anchorage or coupler – Centre spacing and edge distance

Additional reinforcement

Helix only







Stirrups only

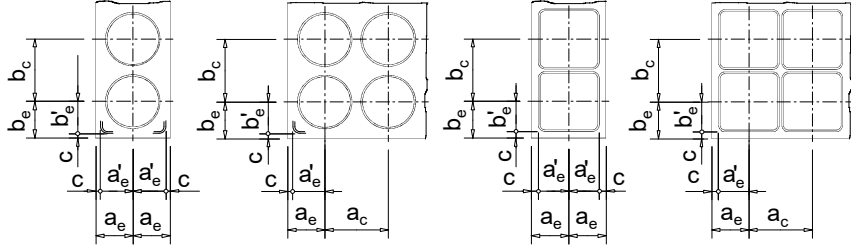

$a_e = a'_e + c$
 $b_e = b'_e + c$
 c ... Concrete cover of reinforcement in the same cross section

Bearing trumplate A, E, and N

Technical data of anchorages																				
BBR VT CONA CMI BT			4206				4306				4806				5506					
Strand arrangement																				
7-wire prestressing steel strand – Nominal diameter 15.7 mm – Nominal cross-sectional area 150 mm ² Maximum characteristic tensile strength 1 860 MPa ¹⁾																				
Tendon																				
Cross-sectional area		A _p	mm ²	6 300				6 450				7 200				8 250				
Char. maximum force		F _{pk}	kN	11 718				11 997				13 392				15 345				
Char. 0.1 % proof force		F _{p0.1}	kN	10 332				10 578				11 808				13 530				
Max. prestressing force		0.90 · F _{p0.1}	kN	9 299				9 520				10 627				12 177				
Max. oversteressing force		0.95 · F _{p0.1}	kN	9 815				10 049				11 218				12 854				
Minimum concrete strength / Additional reinforcement as helix or stirrups / Centre spacing and edge distance																				
Minimum concrete strength																				
Cube		f _{cm, 0}	MPa	53		60		53		60		53		60		53		60		
Cylinder		f _{cm, 0}	MPa	43		50		43		50		43		50		43		50		
Helix, ribbed reinforcing steel, R _e ≥ 500 MPa																				
Outer diameter		∅ A	mm	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
Bar diameter			mm	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
Length, approximately			mm	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
Pitch			mm	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
Number of pitches			—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
Distance		E	mm	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
Additional stirrup reinforcement, ribbed reinforcing steel, R _e ≥ 500 MPa																				
Number of stirrups			—	—	10	—	10	—	12	—	11	—	11	—	11	—	12 ³⁾	12 ³⁾	—	12
Bar diameter ²⁾			mm	—	24	—	24	—	20	—	20	—	24	—	24	—	24	20	—	24
Spacing			mm	—	60	—	60	—	55	—	60	—	60	—	60	—	60	60	—	60
Distance		F	mm	—	45	—	45	—	45	—	45	—	45	—	45	—	40	40	—	40
Minimum outer dimensions		B × B	mm	—	560	—	530	—	570	—	560	—	590	—	570	—	650	590	—	620
Centre spacing and edge distance																				
Minimum centre spacing		a _c , b _c	mm	—	580	—	550	—	590	—	580	—	610	—	590	—	670	—	—	640
Min. edge distance + c		a _e ', b _e '	mm	—	280	—	265	—	285	—	280	—	295	—	285	—	325	—	—	310

¹⁾ Prestressing steel strand with nominal diameter 15.3 mm, cross-sectional area 140 mm², or with characteristic tensile strength below 1 860 MPa may also be used. ³⁾ Placed as bundle of bars in the same plane.
²⁾ Bar diameter of 24 mm can be replaced by 25 mm.




Internal Post-tensioning System
Anchorage zone of CONA CMI BT
Minimum concrete strength – Helix or additional stirrup reinforcement – Centre spacing and edge distance


Annex 76
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Modification of centre spacing and edge distance

Additional reinforcement as helix only

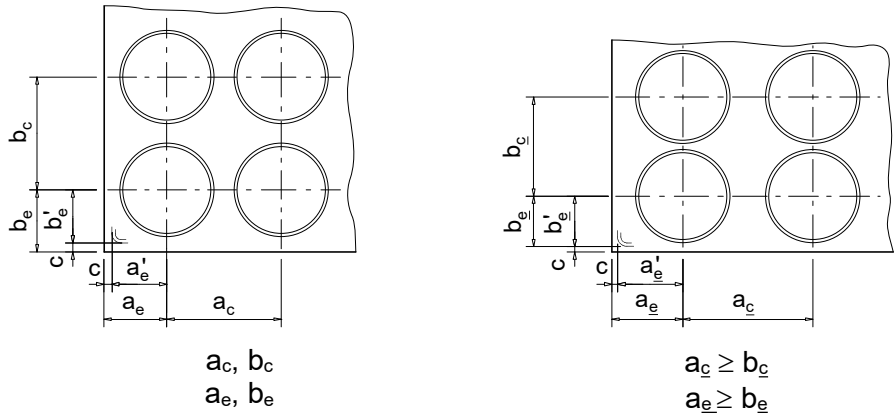

Additional reinforcement as stirrups only

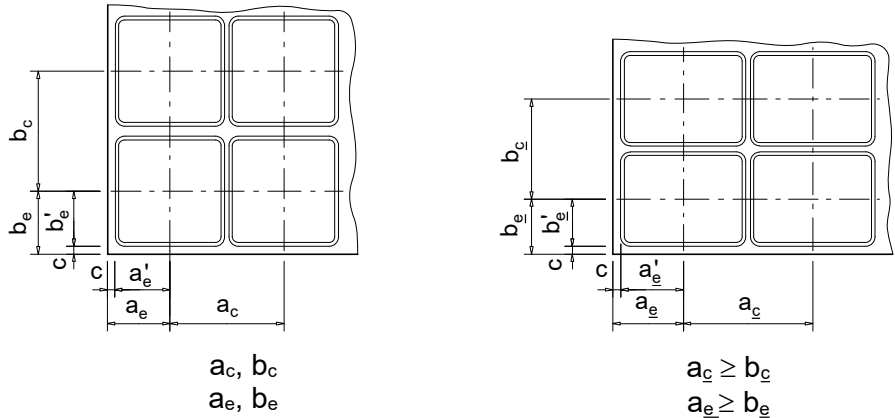

Modification of centre spacing and edge distance are in accordance with Clause 1.8.

$$b_c \geq \begin{cases} 0.85 \cdot b_c \\ \text{and} \\ \geq \text{Helix, outside diameter}^1) \end{cases}$$

$$a_c \geq \frac{A_c}{b_c}$$

$$A_c = a_c \cdot b_c \leq a_c \cdot b_c$$


Corresponding edge distances

$$a_e = \frac{a_c}{2} - 10 \text{ mm} + c \quad \text{and} \quad b_e = \frac{b_c}{2} - 10 \text{ mm} + c$$


c Concrete cover

¹⁾ Except the dimensions of helix, the outer dimensions of the additional stirrup reinforcement are adjusted accordingly. Further modifications of reinforcement are in accordance with the Clauses 1.12.8 and 2.2.3.5.


Stressing anchorage SA (SAE)

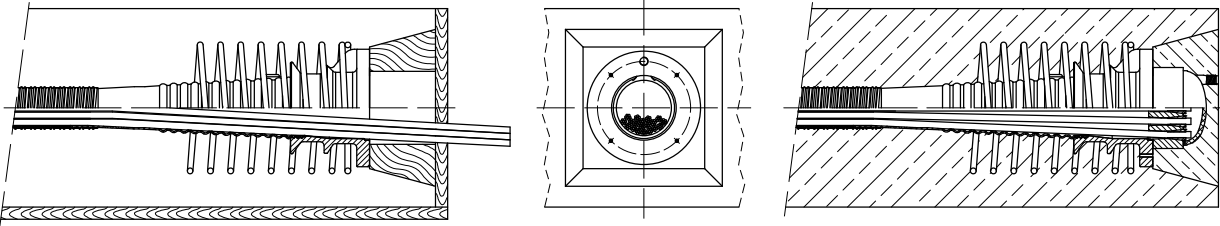


Fixed anchorage FA (FAE)

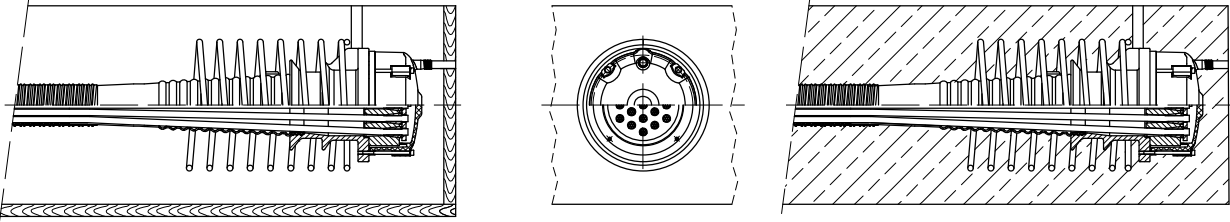


Exposed stressing anchorage SA (SAE)

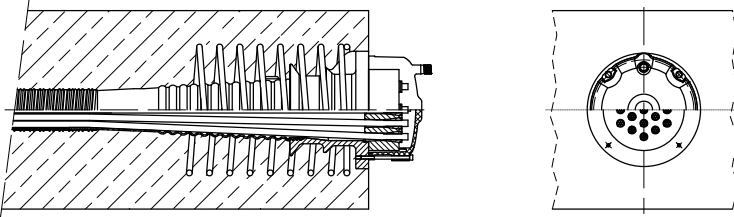


Fixed coupler FK

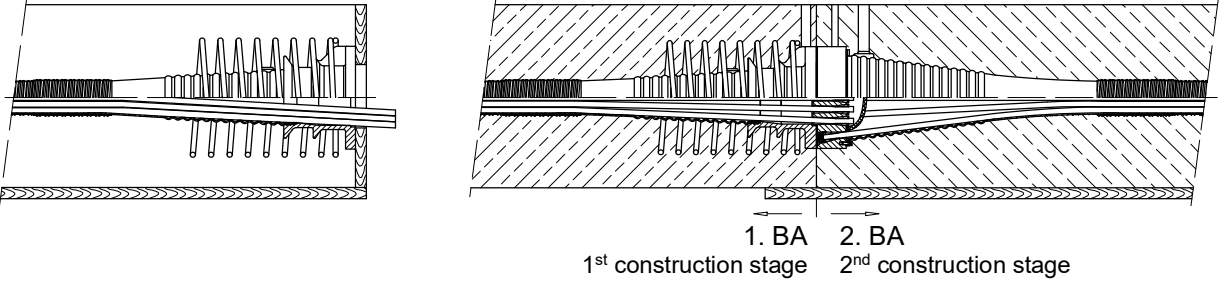


Fixed coupler FH

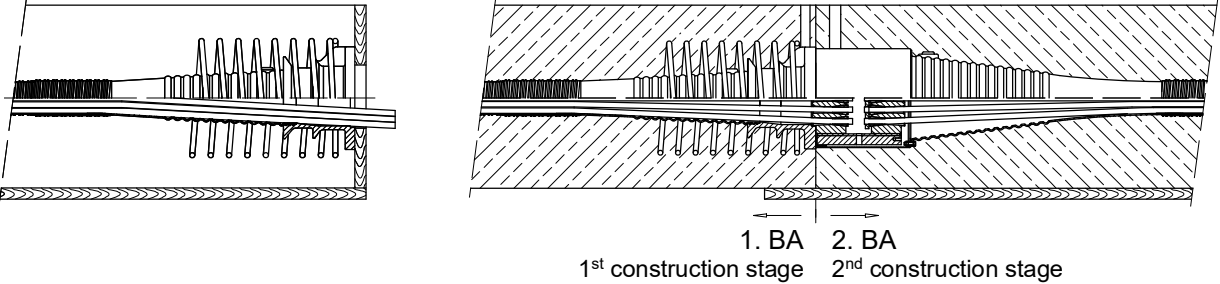


Stressing anchorage with monostrand, recessed

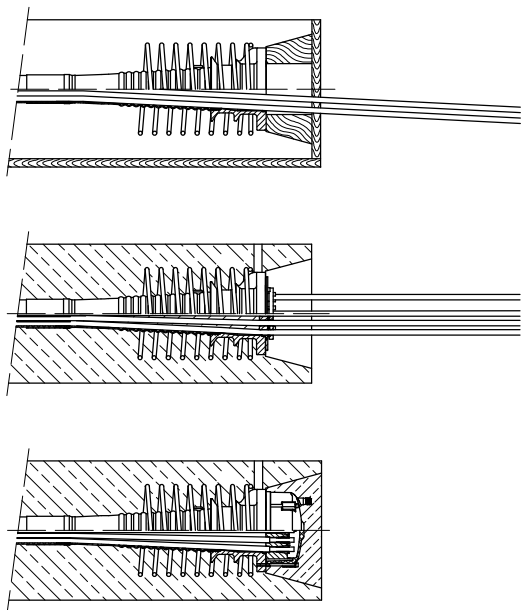


Stressing anchorage with monostrand, exposed

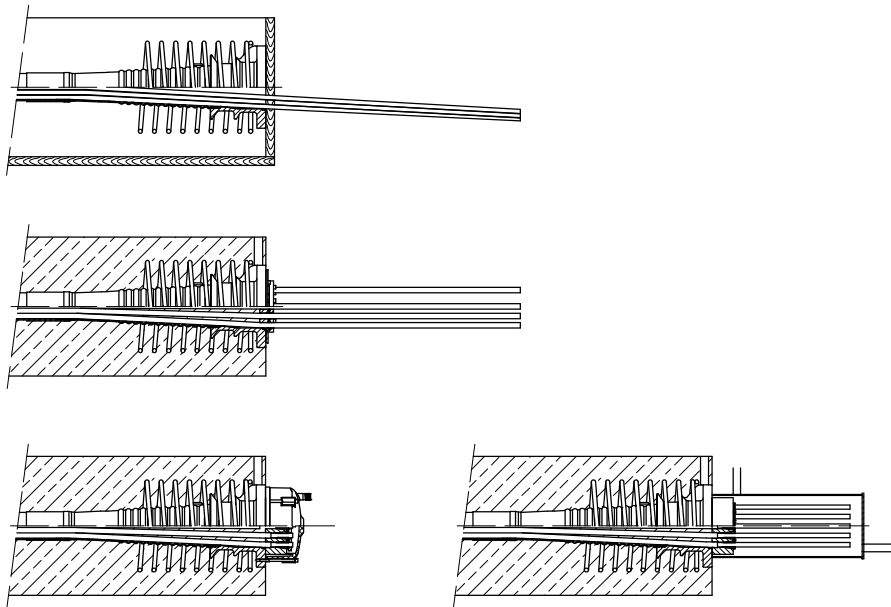


Recessed stressing anchorage SA

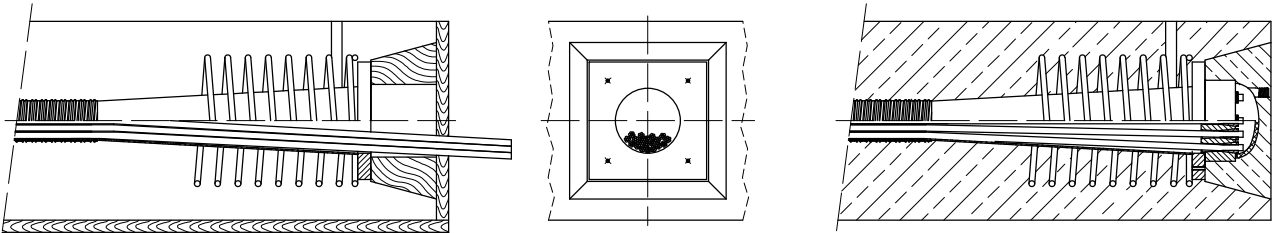


Fixed anchorage FA

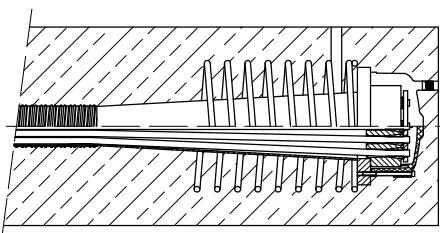


Exposed stressing anchorage SA

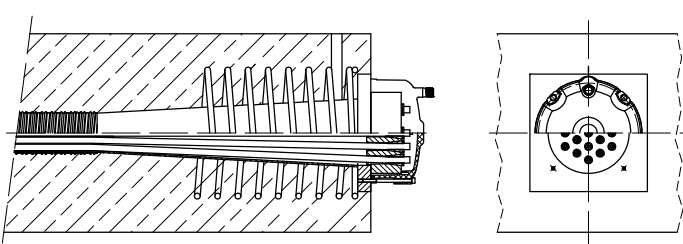


Fixed and stressing coupler FK, SK

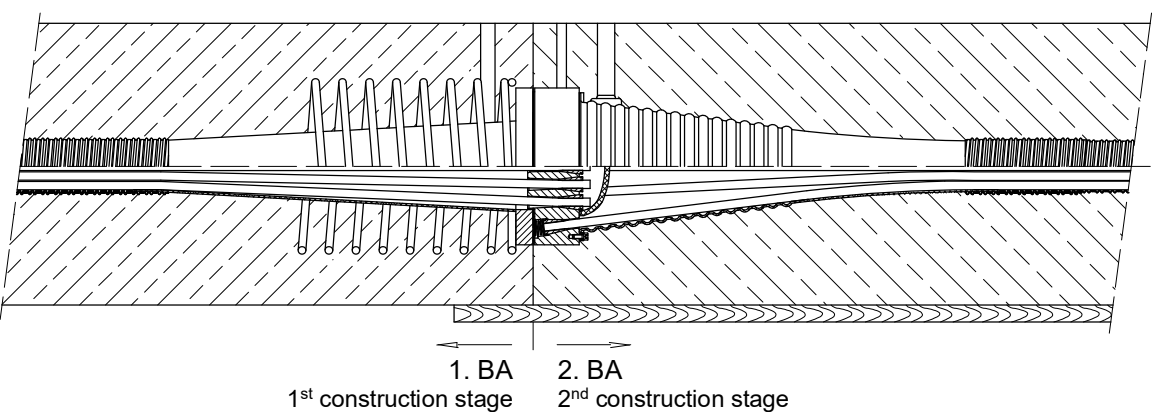


Fixed and stressing coupler FH, SH

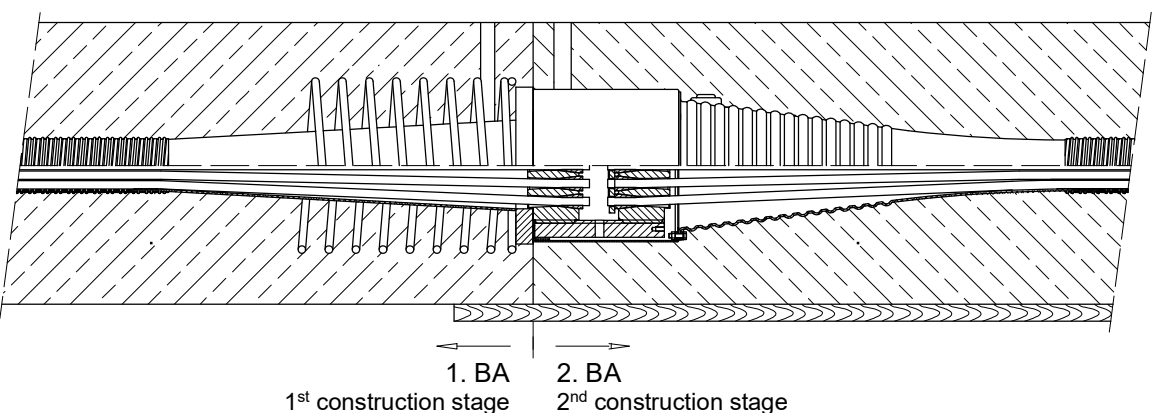


Stressing anchorage with monostrand, recessed

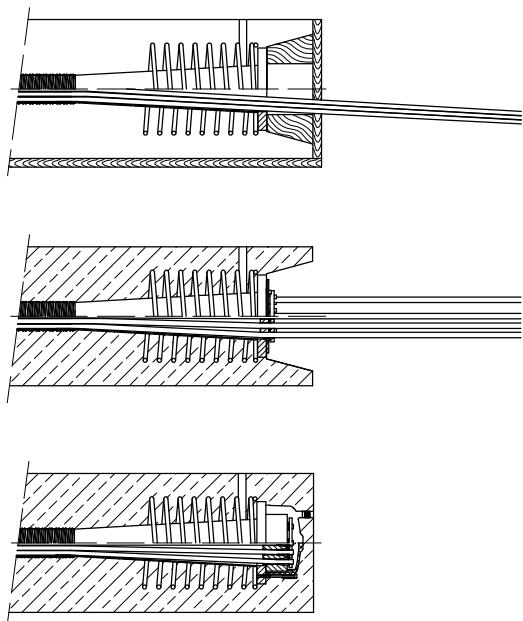

Stressing anchorage with monostrand, exposed

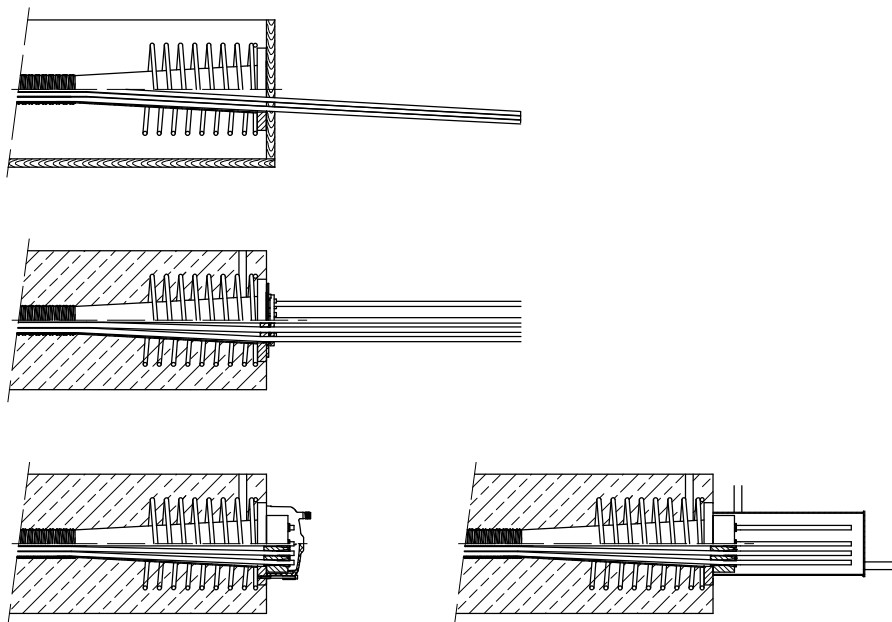

<div> <div>1</div> <div> Preparatory work <p>The components of the post-tensioning kit are stored so as to avoid any damage or corrosion.</p> </div> </div> <div> <div>2</div> <div> Anchorage recesses <p>Adequate space to accommodate and to use the prestressing jack is ensured, see also Clause 1.2.11 and Clause 2.2.4.2.</p> </div> </div> <div> <div>3</div> <div> Fastening the bearing trumplates or square plates <p>Four holes are provided to fasten the bearing trumplates or square plates to the formwork. The trumpet is screwed into the bearing trumplate if applicable. The helix is either welded to the bearing trumplate by means of radial bars or to the square plate, see also the Clauses 1.12.8, 2.2.3.5, and 2.2.4.6 or positioned by fixing it to the existing reinforcement.</p> </div> </div> <div> <div>4</div> <div> Placing of the sheaths <p>The sheaths are placed on supports with spacing according to Clause 1.6 and minimum radii of curvature according to Clause 1.9. The sheaths are jointed in a leak-proof way. The sheaths are supported such that any movement is prevented.</p> <p>The same applies for prefabricated tendons.</p> </div> </div> <div> <div>5</div> <div> Installation of tensile elements, prestressing steel <p>The prestressing steel is pushed or pulled into the sheath before or after concreting of the structure.</p> </div> </div> <div> <div>6</div> <div> Installation of the inaccessible fixed anchorages <p>After passing the strands through the anchor head, they are anchored individually in the cones by means of ring wedges. After assembling the wedges are secured with springs or a wedge retaining plate.</p> <p>An alternative is pre-locking each individual strand with $\sim 0.5 \cdot F_{pk}$ and applying a wedge retaining plate.</p> </div> </div> <div> <div>7</div> <div> Installation of fixed coupler anchor head 2.BA <p>The function of the fixed coupler is to connect two tendons, whereas the first tendon is stressed before the second tendon is installed and stressed.</p> <p>The coupling is achieved by pushing the strands into the already stressed coupler anchor head K, side 2.BA in the outer pitch circle, whereby the strands are marked to check the correct depth of engagement.</p> <p>The coupler anchor head H, 2.BA is assembled with ring wedges and a wedge retaining plate. It is connected to the already stressed coupler anchor head H, 1.BA by means of a threaded coupler sleeve.</p> </div> </div>		
---	--	--

	<div> Internal Post-tensioning System Description of installation </div>	<div> Annex 82 of European Technical Assessment ETA-06/0147 of 26.06.2025 </div>
---	--	---

8 Assembly of movable coupler

The movable coupler serves to lengthen unstressed tendons. The axial movement during stressing is ensured by a sheathing box suitable to the expected elongation at the position of the coupler.

The assembly of the coupler anchor heads is performed in accordance with Point 7 and the Clauses 1.2.4 and 2.2.4.1. The transverse forces at the end of the trumpet are covered by steel tension rings.

9 Checking the tendons before concreting

Before concreting the structure, position and fastening of the entire tendon are checked and corrected if necessary. The sheaths are checked for any damage.

10 Assembly of anchor head/coupler anchor head 1.BA

After passing the strands through the anchor head, they are anchored individually in the cones by means of ring wedges. The same applies for the coupler anchor head in case of fixed couplers in the first construction stage.

11 Stressing

At the time of stressing the mean concrete compressive strength is at least according to Table 6 and the data of Clause 1.10. Stressing and possible wedging are carried out with a suitable prestressing jack and in accordance with Clause 2.2.4.2.


Elongation of the tendon and prestressing forces are checked and recorded systematically during the stressing operation.

Restressing the tendons is permitted in accordance with Clause 2.2.4.3.


12 Grouting the tendons

The grout is injected through the inlet holes until it escapes from the outlet tubes with the same consistency. All vents and grouting inlets are sealed immediately after grouting, see also Clause 2.2.4.5.


More detailed information on installation can be obtained from the ETA holder.

	Internal Post-tensioning System Description of installation	Annex 83 of European Technical Assessment ETA-06/0147 of 26.06.2025
---	---	---

Construction stages of precast segmental coupler

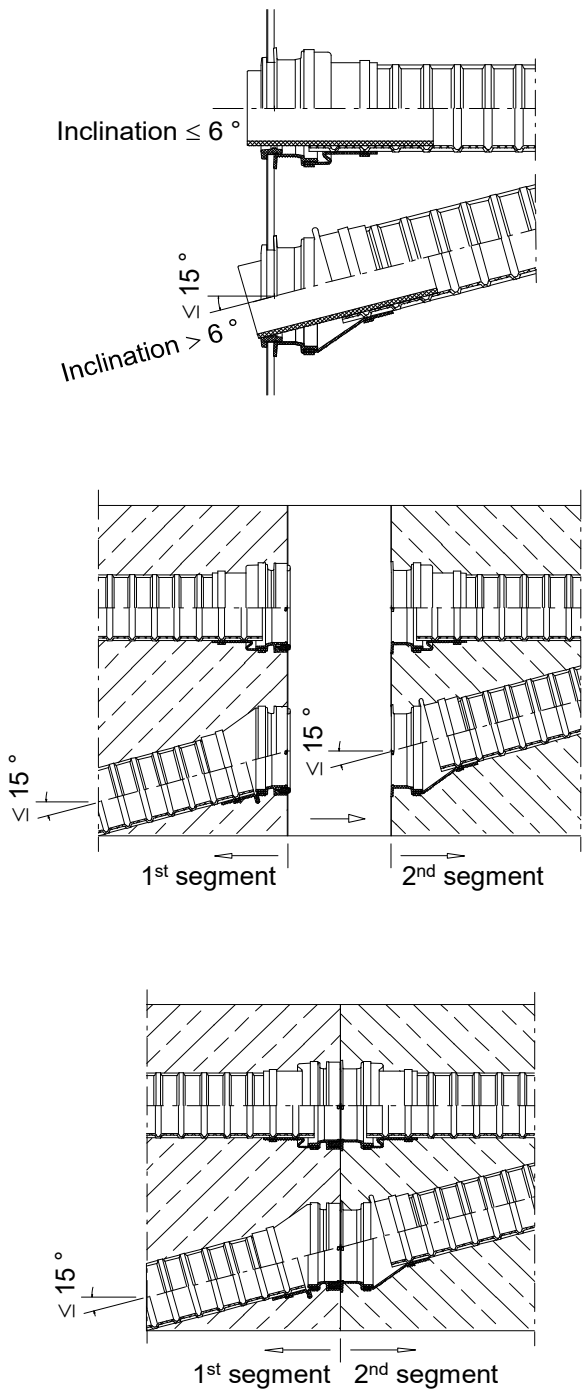


Construction stages of precast segmental coupler for closure pours – Solution 1

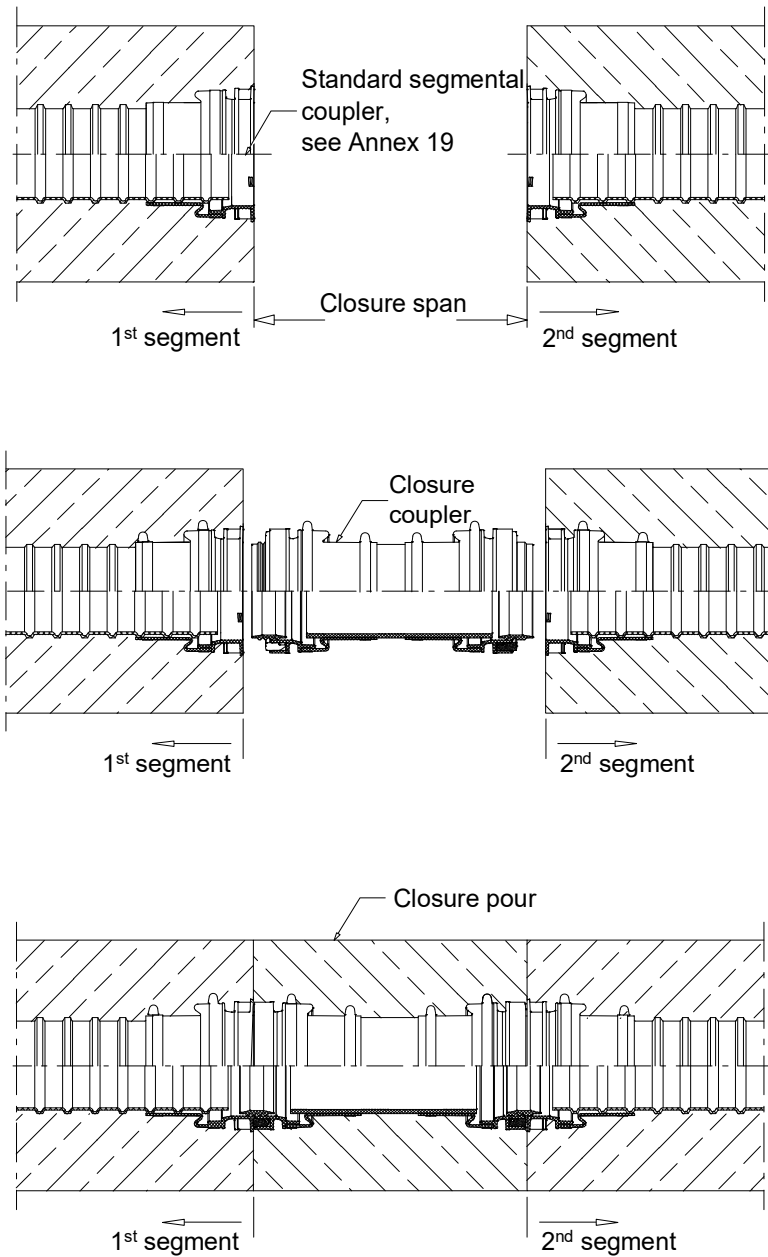

	Internal Post-tensioning System Construction stages of precast segmental coupler for closure pours – Solution 1	Annex 85 of European Technical Assessment ETA-06/0147 of 26.06.2025
---	---	---

Construction stages of precast segmental coupler for closure pours – Solution 2

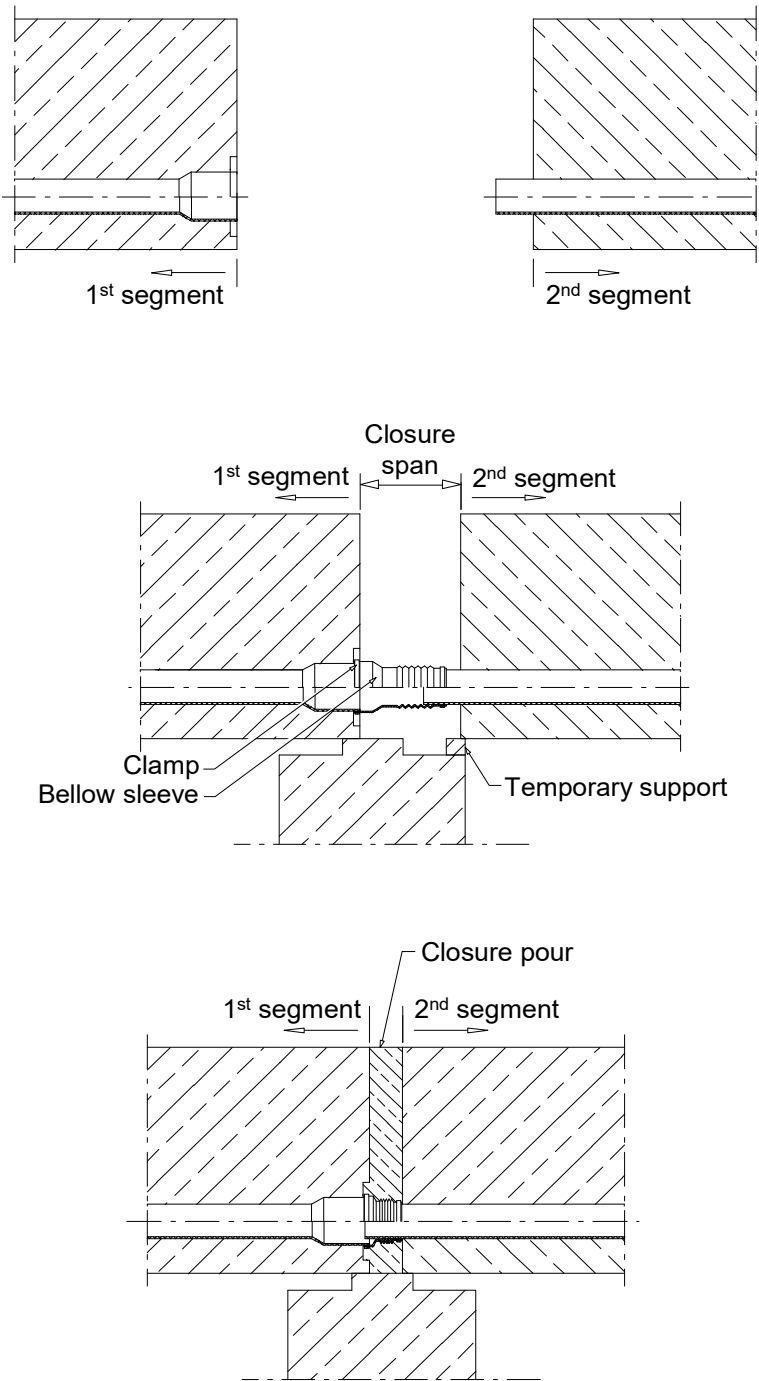

Contents of the prescribed test plan

Component	Item	Test / Check	Trace-ability	Minimum frequency	Documen-tation
Bearing trumplate A Bearing trumplate E Bearing trumplate N	Material	Check	Full	100 %	"3.1" ¹⁾
	Detailed dimensions	Test		3 % ≥ 2 specimens	Yes
	Visual inspection ²⁾	Check		100 %	No
Square plate	Material	Check	Full	100 %	"2.2" ³⁾
	Detailed dimensions	Test		3 % ≥ 2 specimens	Yes
	Visual inspection ²⁾	Check		100 %	No
Anchor head A Anchor head N Coupler anchor head H, K	Material	Check	Full	100 %	"3.1" ¹⁾
	Detailed dimensions ⁴⁾	Test		5 % ≥ 2 specimens	Yes
	Visual inspection ^{2), 5)}	Check		100 %	No
Ring wedge H, F, G, N	Material	Check	Full	100 %	"3.1" ¹⁾
	Treatment, hardness ^{6), 7)}	Test		0.5 % ≥ 2 specimens	Yes
	Detailed dimensions	Test		5 % ≥ 2 specimens	Yes
	Visual inspection ^{2), 8)}	Check		100 %	No
Steel ring E	Material	Check	Bulk	100 %	"2.2" ³⁾
	Detailed dimensions	Test		0.5 % ≥ 2 specimens	Yes
	Visual inspection ²⁾	Check		100 %	No
Coupler sleeve H	Material	Check	Full	100 %	"3.1" ¹⁾
	Detailed dimensions	Test		5 % ≥ 2 specimens	Yes
	Visual inspection ²⁾	Check		100 %	No
Steel strip sheath	Material	Check	"CE"	100 %	"CE"
	Visual inspection ²⁾	Check		100 %	No
Prestressing steel strand ⁹⁾	Material	Check	Full	100 %	"CE" ⁹⁾
	Diameter	Test		Each coil	No
	Visual inspection ²⁾	Check		Each coil	No
Constituents of filling material as per EN 447	Cement	Check	Full	100 %	"CE"
	Admixtures, additions	Check	Bulk	100 %	"CE"
Components for electrically isolated tendon	Material	Check	Full	100 %	MC ¹⁰⁾
	Visual inspection ²⁾	Check		100 %	No
BBR VT Plastic Duct	According to <i>fib</i> Bulletin				

¹⁾ "3.1": Inspection certificate type "3.1" according to EN 10204

²⁾ Visual inspections include e.g., main dimensions, gauge testing, correct marking or labelling, appropriate performance, surface, fins, kinks, smoothness, corrosion, coating, etc., as detailed in the prescribed test plan.

³⁾ "2.2": Test report type "2.2" according to EN 10204

⁴⁾ Other dimensions than ⁵⁾

⁵⁾ Dimensions: All conical bores of the anchor heads and coupler anchor heads regarding angle, diameter and surface condition, thread dimensions of all anchor heads and coupler anchor heads

⁶⁾ Geometrical properties

⁷⁾ Surface hardness

⁸⁾ Teeth, cone surface

⁹⁾ As long as the basis for CE marking of prestressing steel is not available, an approval or certificate according to the respective standards and regulations in force at the place of use accompanies each delivery.

¹⁰⁾ Certificate of the manufacturer of the material that allow for proof of conformity.

Full..... Full traceability of each component to its raw materials

Bulk..... Traceability of each delivery of components to a defined point



Internal Post-tensioning System
Contents of the prescribed test plan

Annex 87
of European Technical Assessment
ETA-06/0147 of 26.06.2025

Audit testing

Component	Item	Test / Check	Sampling ²⁾ Number of components per visit
Anchor head A Anchor head N Coupler anchor head H, K Coupler sleeve H Bearing trumplate A Bearing trumplate E Bearing trumplate N Square plate Steel ring E	Material according to specification	Test / Check	1
	Detailed dimensions	Test	
	Visual inspection ¹⁾	Check	
Ring wedge	Material according to specification	Test / Check	2
	Treatment	Test	2
	Detailed dimensions	Test	1
	Main dimensions, surface hardness and surface finish	Test	5
	Visual inspection ¹⁾	Check	5
Single tensile element test	Single tensile element test according to EAD 160004-00-0301, Annex C.7	Test	1 series
BBR VT Plastic Duct	According to <i>fib</i> Bulletin		

¹⁾ Visual inspections means e.g., main dimensions, gauge testing, correct marking or labelling, appropriate performance, surface, fins, kinks, smoothness, corrosion protection, corrosion, coating, etc., as given in the prescribed test plan.

²⁾ All samples are randomly selected and clearly identified.

Essential characteristics for the intended uses

No	Essential Characteristic	Clause	Intended use Line No according to Clause 2.1, Table 8						
			1	2	3	4	5	6	7
1	Resistance to static load	3.2.1.1	+	+	+	+	+	+	+
2	Resistance to fatigue	3.2.1.2	+	+	+	+	+	+	+
3	Load transfer to the structure	3.2.1.3	+	+	+	+	+	+	+
4	Friction coefficient	3.2.1.4	+	+	+	+	+	+	+
5	Deviation, deflection (limits)	3.2.1.5	+	+	+	+	+	+	+
6	Assessment of assembly	3.2.1.6	+	+	+	+	+	+	+
7	Resistance to static load under cryogenic conditions for applications with anchorage / coupling outside the possible cryogenic zone	3.2.1.7	—	—	+	—	—	—	—
8	Resistance to static load under cryogenic conditions for applications with anchorage / coupling inside the possible cryogenic zone	3.2.1.8	—	—	—	+	—	—	—
9	Material properties, component performance, system performance of plastic duct (PL1)	3.2.1.9	—	—	— ¹⁾	— ¹⁾	+	—	—
10	Material properties, component performance, system performance of plastic duct to provide an encapsulated tendon (PL2)	3.2.1.10	—	—	— ¹⁾	— ¹⁾	—	+	—
11	Material properties, component performance, system performance of plastic duct to provide an electrically isolated tendon (PL3)	3.2.1.11	—	—	— ¹⁾	— ¹⁾	—	—	+
12	Corrosion protection	3.2.1.12	+	+	+	+	+	+	+
13	Reaction to fire	3.2.2.1	+	+	+	+	+	+	+
14	Content, emission, and/or release, of dangerous substances	3.2.3.1	+	+	+	+	+	+	+

Key

+ Essential characteristic relevant for the intended use

— Essential characteristic not relevant for the intended use

¹⁾ Essential characteristic relevant for cryogenic applications where plastic duct are used.

For combinations of intended uses, the essential characteristics of all intended uses composing the combination are relevant.



Internal Post-tensioning System
Essential characteristics for the intended uses

Annex 89
of European Technical Assessment
ETA-06/0147 of 26.06.2025


Reference documents

European Assessment Document

EAD 160004-00-0301	Post-Tensioning Kits for Prestressing of Structures
EAD 160027-00-0301	Special filling products for post-tensioning kits

Standards

EN 206, 12.2013	Concrete – Specification, performance, production and conformity
EN 206/A2, 03.2021	
EN 445, 10.2007	Grout for prestressing tendons – Test methods
EN 446, 10.2007	Grout for prestressing tendons – Grouting procedures
EN 447, 10.2007	Grout for prestressing tendons – Basic requirements
EN 523, 08.2003	Steel strip sheaths for prestressing tendons – Terminology, requirements, quality control
EN 1561, 12.2023	Founding – Grey cast irons
EN 1563, 08.2018	Founding – Spheroidal graphite cast irons
Eurocode 2	Eurocode 2 – Design of concrete structures
Eurocode 3	Eurocode 3 – Design of steel structures
Eurocode 6	Eurocode 6 – Design of masonry structures
EN 10025-2, 08.2019	Hot rolled products of structural steels – Part 2: Technical delivery conditions for non-alloy structural steels
EN 10204, 10.2004	Metallic products – Types of inspection documents
EN 10210-1, 04.2006	Hot finished structural hollow sections of non-alloy and fine grain steels – Part 1: Technical delivery conditions
EN 10216-1, 12.2013	Seamless steel tubes for pressure purposes – Technical delivery conditions – Part 1: Non-alloy steel tubes with specified room temperature properties
EN 10217-1, 04.2019	Welded steel tubes for pressure purposes – Technical delivery conditions – Part 1: Electric welded and submerged arc welded non-alloy steel tubes with specified room temperature properties
EN 10219-1, 04.2006	Cold formed welded structural hollow sections of non-alloy and fine grain steels – Part 1: Technical delivery conditions
EN 10255+A1, 04.2007	Non-Alloy steel tubes suitable for welding and threading – Technical delivery conditions
EN 10270-1, 02.2024	Steel wire for mechanical springs – Part 1: Patented cold drawn unalloyed spring steel wire
EN 10305-3, 12.2023	Steel tubes for precision applications – Technical delivery conditions – Part 3: Welded cold sized tubes
EN ISO 683-1, 06.2018	Heat-treatable steels, alloy steels and free-cutting steels – Part 1: Non-alloy steels for quenching and tempering
EN ISO 683-2, 06.2018	Heat-treatable steels, alloy steels and free-cutting steels – Part 2: Alloy steels for quenching and tempering
EN ISO 683-3, 02.2022	Heat-treatable steels, alloy steels and free-cutting steels – Part 3: Case-hardening steels
EN ISO 683-7, 10.2024	Heat-treatable steels, alloy steels and free-cutting steels – Part 7: Bright products of non-alloy and alloy steels

<p>EN ISO 17855-1, 10.2014</p> <p>EN ISO 19069-1, 03.2015</p> <p>prEN 10138-3, 09.2000</p> <p>prEN 10138-3, 08.2009</p>	<p>Plastics – Polyethylene (PE) moulding and extrusion materials – Part 1: Designation system and basis for specifications</p> <p>Plastics – Polypropylene (PP) moulding and extrusion materials – Part 1: Designation system and basis for specifications</p> <p>Prestressing steels – Part 3: Strand</p> <p>Prestressing steels – Part 3: Strand</p>		
<p>Other documents</p>			
<p>CWA 14646, 01.2003</p> <p><i>fib</i> bulletin 75, 12.2014</p> <p><i>fib</i> bulletin 33, 12.2005</p> <p>98/456/EC</p>	<p>Requirements for the installation of post-tensioning kits for prestressing of structures and qualification of the specialist company and its personnel</p> <p>Polymer-duct systems for internal bonded post-tensioning</p> <p>Durability of post-tensioning tendons</p> <p>Commission decision 98/456/EC of 3 July 1998 on the procedure for attesting the conformity of construction products pursuant to Article 20 (2) of Council Directive 89/106/EEC as regards posttensioning kits for the prestressing of structures, Official Journal of the European Communities L 201 of 17 July 1998, p. 112</p>		
<p>305/2011</p>	<p>Regulation (EU) № 305/2011 of the European Parliament and of the Council of 9 March 2011 laying down harmonised conditions for the marketing of construction products and repealing Council Directive 89/106/EEC, OJ L 088 of 04.04.2011, p. 5, amended by Commission Delegated Regulation (EU) № 568/2014 of 18 February 2014, OJ L 157 of 27.05.2014, p. 76, Commission Delegated Regulation (EU) № 574/2014 of 21 February 2014, OJ L 159 of 28.05.2014, p. 41, and Regulation (EU) 2019/1020 of the European Parliament and of the Council of 20 June 2019, OJ L 169 of 25.06.2019, p. 1</p>		
<p>568/2014</p>	<p>Commission Delegated Regulation (EU) № 568/2014 of 18 February 2014 amending Annex V to Regulation (EU) № 305/2011 of the European Parliament and of the Council as regards the assessment and verification of constancy of performance of construction products, OJ L 157 of 27.05.2014, p. 76</p>		
	<table> <tr> <td data-bbox="383 1937 1093 2092"> <p>Internal Post-tensioning System</p> <p>Reference documents</p> </td><td data-bbox="1093 1937 1477 2092"> <p>Annex 91</p> <p>of European Technical Assessment</p> <p>ETA-06/0147 of 26.06.2025</p> </td></tr> </table>	<p>Internal Post-tensioning System</p> <p>Reference documents</p>	<p>Annex 91</p> <p>of European Technical Assessment</p> <p>ETA-06/0147 of 26.06.2025</p>
<p>Internal Post-tensioning System</p> <p>Reference documents</p>	<p>Annex 91</p> <p>of European Technical Assessment</p> <p>ETA-06/0147 of 26.06.2025</p>		

Materialprüfungsamt Nordrhein-Westfalen

Prüfen • Überwachen • Zertifizieren

Certificate of constancy of performance**0432-CPR-00299-1.1 (EN)**

Version 05

In compliance with Regulation (EU) No 305/2011 of the European Parliament and of the Council of 9 March 2011 (the Construction products Regulation or CPR), this certificate applies to the construction product

**BBR VT CONA CMI – Internal Post-tensioning
System with 01 to 61 Strands**

Post-tensioning kit for prestressing of structures with internal bonded or unbonded strands

placed on the market under the name or trade mark of

BBR VT International LtdRingstr. 2
CH-8603 Schwerzenbach

and produced in the manufacturing plant(s)

BBR VT International LtdRingstr. 2
CH-8603 Schwerzenbach

This certificate attests that all provisions concerning the assessment and verification of constancy of performance described in the

ETA-06/0147, issued on 26.06.2025

and

EAD 160004-00-0301


under **system 1+** for the performance set out in the ETA are applied and that the factory production control conducted by the manufacturer is assessed to ensure the

constancy of performance of the construction product.

This certificate was first issued on 17.08.2016 and will remain valid until 04.04.2029 as long as neither the ETA, the EAD, the construction product, the AVCP methods nor the manufacturing conditions in the plant are modified significantly, unless suspended or withdrawn by the notified product certification body.

Dortmund, 07.07.2025

by order


Dipl.-Ing. Becker
Head of Certification Body (Dep. 21)

This Certificate consists of 1 page.

This Certificate replaces the Certificate no. 0432-CPR-00299-1.1 dated
13.05.2024, Version 04.

The original of this document was issued in German language.
In case of doubt only the German version is valid.



BBR VT International Ltd
Ringstrasse 2
8603 Schwerzenbach (ZH)
Switzerland

Tel +41 44 806 80 60
Fax +41 44 806 80 50

www.bbrnetwork.com
info@bbnetwork.com

BBR VT International Ltd
Technical Headquarters and Business Development Centre
Switzerland



A Global Network of Experts
www.bbrnetwork.com